

MIL-STD-271F(SH)
27 June 1986
SUPERSEDING
MIL-STD-271E(SHIPS)
31 October 1973
(See 9.2)

MILITARY STANDARD
REQUIREMENTS FOR NONDESTRUCTIVE
TESTING METHODS



AMSC N/A
DISTRIBUTION STATEMENT A Approved for public release; distribution unlimited
AREA NDTI

MIL-STD-271F(SH)

27 June 1986

DEPARTMENT OF THE NAVY
NAVAL SEA SYSTEMS COMMAND

Washington, DC 20362-5101

Requirements for Nondestructive Testing Methods.

1. This Standard is approved for use by the Naval Sea Systems Command (NAVSEA) and is available for use by all Departments and Agencies of the Department of Defense.
2. For contracts or acquisition orders which invoke prior issues of this document, the contractor shall not use this issue without prior contractual approval.
3. Beneficial comments (recommendations, additions, deletions) and any pertinent data which may be of use in improving this document should be addressed to: Commander, Naval Sea Systems Command, SEA 55Z3, Department of the Navy, Washington, DC 20362-5101 by using the self-addressed Standardization Document Improvement Proposal (DD Form 1426) appearing at the end of this document or by letter.

MIL-STD-271F(SH)
27 June 1986

FOREWORD

This standard covers nondestructive testing method requirements for radiographic, magnetic particle, liquid penetrant, ultrasonic, eddy current and visual inspections. These requirements are designed to ensure the integrity and reliability of inspections performed. This standard does not contain acceptance criteria for the inspection methods defined.

MIL-STD-271F(SH)
27 June 1986

CONTENTS

		<u>Page</u>
Paragraph	1. SCOPE	1
	1.1 General	1
	1.2 Classification	1
	1.3 Acceptance standards	1
	1.4 Time of inspection	1
	1.5 General definitions	2
	1.5.1 Authorized representative of the Naval Sea Systems Command (NAVSEA)	2
	1.5.2 Government inspector	2
	1.5.3 Activity	2
	1.5.4 Nominal thickness	2
	1.5.5 Nondestructive test examiner	2
	1.5.6 Nondestructive test operator	2
	1.5.7 Nondestructive test inspector	2
	1.6 Nondestructive test personnel certification	2
	1.6.1 Personnel qualification requirements	3
	1.6.1.1 Hours of training and experience	3
	1.6.1.2 Other methods	3
	1.6.2 Certification of personnel	3
	1.6.3 Recertification	3
	1.6.5 Vision tests	3
	1.6.5.1 General	3
	1.6.5.2 Brightness discrimination	4
	1.6.6 Records	4
	1.7 Procedure qualification and approval	4
	1.8 Maintenance of inspection records	5
	2. APPLICABLE DOCUMENTS	5
	2.1 Government documents	5
	2.1.1 Specifications and standards	5
	2.2 Other publications	5
	2.3 Order of precedence	6
	3. RADIOGRAPHY	6
	3.1 Definitions	6
	3.1.1 Energy	6
	3.1.2 Film holders or cassettes	6
	3.1.3 Filters	7
	3.1.4 Intensifying screens	7
	3.1.5 Material thickness (T_m)	7
	3.1.6 Maximum effective radiation source dimension	7
	3.1.7 Multiple film technique	7
	3.1.8 Penetrameter	7
	3.1.9 Penetrameter sensitivity	7
	3.1.10 Radiograph	7
	3.1.11 Radiographic film density	7
	3.1.12 Radiographic inspection	8
	3.1.13 Radiographically similar materials	8
	3.1.14 Shielding	8

MIL-STD-271F(SH)
27 June 1986

CONTENTS - Continued

		<u>Page</u>	
Paragraph	3.1.15	Source	8
	3.1.16	Source-to-film distance	8
	3.1.17	Specimen thickness (T_s)	8
	3.2	General requirements	8
	3.2.1	Extent of radiographic inspection	8
	3.2.1.1	Radiographic Shooting Sketch (RSS) for castings	8
	3.2.2	Radiographic procedure	9
	3.2.2.1	Minimum radiographic procedure requirements ...	9
	3.2.2.2	Survey of radiographic facilities	9
	3.3	Radiography requirements	9
	3.3.1	Direction of radiation	9
	3.3.2	Screens, filters, and masking	9
	3.3.3	Film	10
	3.3.3.1	Film quality	10
	3.3.3.2	Film density	10
	3.3.3.3	Multiple film techniques	11
	3.3.4	Filmless techniques	11
	3.3.5	Radiation sources	11
	3.3.6	Source-to-film distance	11
	3.3.7	Radiographic location markers	12
	3.3.8	Film identification	12
	3.3.9	Maintenance of radiographic records	12
	3.3.10	Darkroom facilities	12
	3.3.11	Film viewing facilities	12
	3.3.12	Surface preparation of components and welds prior to radiography	13
	3.3.13	Safety	13
	3.3.14	Interpretation of radiographs	13
	3.3.15	Radiographic records	13
	3.4	Penetrameters	14
	3.4.1	Penetrameter material	14
	3.4.1.1	Dissimilar metal welds	14
	3.4.1.2	Other metals	15
	3.4.2	Penetrameter dimensions	15
	3.4.3	Penetrameter identification	15
	3.4.4	Penetrameter selection	17
	3.4.4.1	Welds	17
	3.4.4.2	Castings and forgings	17
	3.4.5	Acceptance standards	17
	3.4.6	Number, location, and placement of pene- traters	17
	3.4.6.1	Penetrameter location	17
	3.4.6.1.1	Film-side penetrameter technique (double- wall exposure)	17
	3.4.6.1.2	Film-side penetrameter technique (single- wall exposure)	18
	3.4.6.1.3	Separate block penetrameter technique	18
	3.4.6.2	Requirements for casting and forgings	18

MIL-STD-271F(SH)
27 June 1986

CONTENTS - Continued

		<u>Page</u>
Paragraph 3.4.6.3	Requirements for welds	18
3.5	Shims	20
3.5.1	Shims for backing ring welds	20
3.5.2	Shims for consumable insert welds	20
3.6	Radiographic quality levels	20
3.6.1	X-ray radiography	21
3.6.2	Radioisotope radiography	21
3.7	Single-wall and double-wall radiography	22
3.7.1	Single-wall radiography	22
3.7.2	Double-wall radiography	22
3.7.2.1	Double-wall exposure/single-wall viewing	22
3.7.2.2	Double-wall exposure/double-wall viewing	23
3.8	Radiography of parts	23
3.9	Radiography of repair welds	23
3.10	Radiography of castings and forgings	23
3.11	Radiographic film ownership	23
4.	MAGNETIC PARTICLE TESTING	23
4.1	Intended use	23
4.2	Definitions	24
4.2.1	Arc strikes	24
4.2.2	Black light	24
4.2.3	Circular method	24
4.2.4	Continuous method	24
4.2.5	Fluorescence	24
4.2.6	Longitudinal method	24
4.2.7	Magnetic particles	24
4.2.8	Residual method	25
4.2.9	Relevant indications	25
4.2.10	Indication	25
4.2.11	Non-relevant indications	25
4.3	Magnetic particle inspection requirements	25
4.3.1	General requirements	25
4.3.1.1	Method	25
4.3.1.1.1	Lighting in test area	25
4.3.1.2	Procedure	25
4.3.1.3	Surface preparation	26
4.3.1.3.1	Cleaning and masking	26
4.3.1.3.2	Cleaning solution	26
4.3.1.4	Direction of magnetization	26
4.3.1.5	Demagnetizing apparatus	27
4.3.1.5.1	Demagnetization	27
4.3.1.6	Equipment accuracy	27
4.3.1.6.1	Dc portable prod and stationary magnetic particle equipment	27
4.3.1.6.2	Yoke equipment	27
4.3.1.7	Magnetizing current	27

MIL-STD-271F(SH)

27 June 1986

CONTENTS - Continued

		<u>Page</u>	
Paragraph	4.3.2	Wet method	27
	4.3.2.1	General requirements	27
	4.3.2.1.1	Equipment	28
	4.3.2.2	Vehicles	28
	4.3.2.2.1	Cleaning and drying	28
	4.3.2.3	Magnetic particles	28
	4.3.2.4	Suspensions	28
	4.3.2.5	Procedure	28
	4.3.2.5.1	Continuous methods	28
	4.3.2.5.2	Residual method	28
	4.3.2.5.3	Circular magnetization; central conductor (indirect method)	29
	4.3.2.5.4	Circular magnetization; item as conductor (direct method)	29
	4.3.2.5.5	Circular magnetization; magnetizing current	29
	4.3.2.5.6	Longitudinal magnetization	29
	4.3.2.5.7	Longitudinal magnetizing current	29
	4.3.2.6	Maintenance of suspension	29
	4.3.2.6.1	Concentration of suspension test	30
	4.3.3	Dry powder method	30
	4.3.3.1	General requirements for magnetic particles	30
	4.3.3.2	Applying particles	30
	4.3.3.2.1	Removal of excess particles	31
	4.3.3.3	Magnetizing procedures	31
	4.3.3.3.1	Circular magnetization	31
	4.3.3.3.2	Longitudinal magnetization	31
	4.3.3.3.3	Yoke magnetization	31
	4.3.3.3.4	Magnetizing current (prod methods)	31
	4.3.3.4	Magnetizing technique (yoke and prod)	31
	4.3.3.4.1	Weld inspection	31
	4.3.3.4.2	Base metal	31
	4.3.3.4.3	Continuous method	31
	4.4	Non-relevant indications	32
	4.5	Final cleaning	32
	4.6	Arc strikes	32
	5.	LIQUID PENETRANT TESTING	32
	5.1	Intended use	32
	5.2	Definitions	32
	5.2.1	Developers	32
	5.2.2	Black light	32
	5.2.3	Emulsifier	32
	5.2.4	Self-emulsifiable	32
	5.2.5	Post-emulsifiable	33
	5.2.6	Penetrant remover	33
	5.2.7	Fluorescence	33

MIL-STD-271F(SH)
27 June 1986

CONTENTS - Continued

	<u>Page</u>
Paragraph 5.3	33
5.3.1	33
5.4	34
5.4.1	34
5.4.2	34
5.4.2.1	34
5.5	34
5.5.1	34
5.5.2	34
5.6	35
5.6.1	35
5.6.2	35
5.6.3	35
5.6.3.1	35
5.6.4	36
5.6.4.1	36
5.6.4.3	36
5.6.4.4	36
5.6.5	36
5.6.5.1	36
5.6.5.2	36
5.6.6	37
5.6.6.1	37
5.6.6.2	37
5.6.6.3	37
5.6.7	37
5.6.8	37
5.6.9	37
5.7	38
6.	38
6.1	38
6.1.1	38
6.1.2	38
6.1.3	38
6.1.4	38
6.1.5	38
6.1.6	38
6.1.7	38
6.1.8	38
6.1.9	39
6.1.10	39
6.1.11	39
6.1.12	39
6.1.13	39
6.1.14	39
6.1.15	39
6.1.16	39

MIL-STD-271F(SH)
27 June 1986

CONTENTS - Continued

	<u>Page</u>
Paragraph 6.1.17	Discontinuity 39
6.1.18	Disregard level (DRL) 39
6.1.19	Frequency 39
6.1.20	Full screen height 39
6.1.21	Gain control 39
6.1.22	IIW block 39
6.1.23	Indication 39
6.1.24	Initial pulse 40
6.1.25	Interface 40
6.1.26	Linearity 40
6.1.27	Longitudinal wave 40
6.1.28	Megahertz (MHz) 40
6.1.29	Peak indication 40
6.1.30	Reference calibration standard 40
6.1.31	Reflection 40
6.1.32	Resolution 40
6.1.33	Scanning 40
6.1.34	Search unit 40
6.1.35	Sensitivity 40
6.1.36	Shear waves 40
6.1.37	Skip distance angle beam testing 41
6.1.38	Test surface 41
6.1.39	Transducer 41
6.1.40	Ultrasonic test sensitivity 41
6.1.41	Ultrasonically sound material 41
6.2	Procedure and test methods 41
6.2.1	Test method selection 41
6.2.2	Surface finish 41
6.2.3	Testing speed 41
6.2.4	Couplant 41
6.2.5	Test symbols 42
6.2.6	Calibration 42
6.3	Equipment 42
6.4	General requirements 42
6.4.1	Equipment requirements 42
6.4.1.1	Basic instrument qualification - pulse echo ... 42
6.4.1.2	Shear wave transducer 43
6.4.1.3	Basic instrument qualification - thickness gauge 43
6.4.1.4	Frequency of basic instrument qualification ... 43
6.4.2	Inspection procedure 43
6.4.2.1	Procedure requalification 44
6.4.3	Discontinuity evaluation 44
6.4.4	Records 44
6.5	Test methods 44
6.5.1	Forgings, wrought and extruded material 44
6.5.1.1	Test calibration, longitudinal wave 44

MIL-STD-271F(SH)
27 June 1986

CONTENTS - Continued

	<u>Page</u>
Paragraph 6.5.1.2	Ring forgings 45
6.5.1.2.1	Test calibration, shear wave 45
6.5.1.2.2	Test 46
6.5.1.2.3	Longitudinal wave tests of ring forgings .. 46
6.5.1.2.3.1	Test calibration, longitudinal wave 46
6.5.1.2.3.2	Testing - longitudinal wave 46
6.5.1.3	Rectangular forgings 46
6.5.1.3.1	Test calibration, longitudinal wave 46
6.5.1.3.2	Testing - longitudinal wave 46
6.5.1.4	Round and multisided forged or wrought bars including disc or pancake forgings .. 47
6.5.1.4.1	Test calibration, longitudinal wave 47
6.5.1.4.2	Testing - longitudinal wave 47
6.5.2	Plate and sheet 47
6.5.2.1	Surface preparation 47
6.5.2.2	Shear wave testing technique 47
6.5.2.2.1	Test calibration 47
6.5.2.2.2	Grid test procedure 48
6.5.2.2.3	Continuous scanning procedure 48
6.5.2.3	Longitudinal wave testing technique 48
6.5.2.3.1	Testing calibration 48
6.5.2.3.2	Test procedures 48
6.5.2.3.2.1	Continuous method 48
6.5.2.3.2.2	Static method 48
6.5.3	Pipes and tubes - seamless 48
6.5.3.2	Test calibration, radial defects detection 49
6.5.3.3	Test, radial defects 49
6.5.4	Ultrasonic inspection of weldments 49
6.5.4.1	Scope 49
6.5.4.2	General requirements 49
6.5.4.2.1	Scanning 49
6.5.4.2.2	Surface finish 49
6.5.4.2.3	Limitations 49
6.5.4.2.4	Reference calibration standards 50
6.5.4.2.4.1	Butt welds, corner welds and tee welds for discontinuities into the through member .. 50
6.5.4.2.4.2	Detection of lack of penetration in full penetration tee welds 50
6.5.4.3	Specific requirements for butt and corner welds 50
6.5.4.3.1	Instrument 50
6.5.4.3.2	Search units 50
6.5.4.3.3	Calibration 50
6.5.4.3.3.1	Class I welds 50
6.5.4.3.3.2	Class II and III welds 51
6.5.4.3.4	Procedure 51
6.5.4.3.4.1	Longitudinal discontinuities 51

MIL-STD-271F(SH)
27 June 1986

CONTENTS - Continued

	<u>Page</u>
Paragraph 6.5.4.3.4.2	Transverse discontinuities 51
6.5.4.3.4.3	Compressional wave 52
6.5.4.3.4.4	Discontinuity evaluation 52
6.5.4.4	Specific requirements for welds of tee joints 52
6.5.4.4.1	Detection of lack of penetration in full penetration tee welds 52
6.5.4.4.1.1	Search units 52
6.5.4.4.1.2	Calibration 52
6.5.4.4.1.3	Procedure 53
6.5.4.4.2	Detection of discontinuities into the through member 53
6.5.4.4.2.1	Inspection zone 53
6.5.4.4.2.2	Search units 53
6.5.4.4.2.3	Calibration 53
6.5.4.4.2.4	Procedure 54
6.5.4.5	Record of inspection results 54
6.6	Thickness measurements 55
6.6.1	Scope 55
6.6.2	Calibration 55
6.6.3	Method 55
6.7	Bonding 55
6.7.1	Scope 55
6.7.1.1	Method 55
6.7.2	Transducers 55
6.7.3	Calibration of test equipment 55
6.7.4	Scanning 56
6.7.4.1	Continuous scanning 56
6.7.4.2	Intermittent scanning 56
6.7.4.3	Calibration for ultrasonic testing of nonparallel surfaces 57
6.7.4.4	Continuous scanning of nonparallel surface 57
6.7.5	Marking 57
6.7.6	Flaw plotting 57
7.	EDDY CURRENT TESTING 57
7.1	Scope 57
7.2	Definitions 57
7.2.1	End (edge) effect 57
7.2.2	Lift-off effect 57
7.2.3	Stand-off 57
7.3	Eddy current inspection requirements 58
7.3.1	General requirements 58
7.3.1.1	Method 58
7.3.1.2	Surface finish 58
7.3.2	Procedure 58
7.3.3	Records 58
7.4	Equipment requirements 58

MIL-STD-271F(SH)
27 June 1986

CONTENTS - Continued

		<u>Page</u>
Paragraph	7.4.1 Eddy current instrument	59
	7.4.2 Performance verification reference block	59
	7.5 On-site verification/standardization	59
	7.5.1 Verification	59
	7.5.2 Standardization	59
	7.6 Test technique	59
	7.6.1 Toe of weld scan	59
	7.6.2 Weld scan	59
	7.6.3 Inspection of surfaces other than welds	60
	8. VISUAL INSPECTION	60
	8.1 Scope	60
	8.2 Reference standard	60
	8.3 Procedure requirements	60
	8.4 Inspection techniques	60
	8.5 Dimensional inspection accuracy	60
	8.6 Lighting	60
	9. NOTES	61
	9.1 Subject term (key word) listing	61
	9.2 Changes from previous issue	61
FIGURES		
Figure	1. Recommended X-ray voltage settings and radio- isotope sources to be used with various steel and similar alloys	62
	2. Recommended X-ray voltage settings and radioisotope sources to be used with various copper-base and similar alloys	63
	3. Recommended X-ray voltage settings and radioisotope sources to be used with various aluminum, magnesium and similar alloys	64
	4. Penetrameter designs	65
	4A. Penetrameter identification notching	66
	4B. Maximum allowed Ug	67
	4C. Recommended increase in source-to-film distance for various radioisotope sources with lengths greater than 1/8 inch	68
	5. Examples of material thickness (T_m) and specimen thickness (T_s)	69-72
	6. Magnetic field indicator	73
	7. Skip distance example	74
	7A. Accepted scanning techniques for butt welds	75
	8. Typical ultrasonic calibration plot for vertical linearity	76
	9. Typical reference calibration standard (sensitivity)	77

MIL-STD-271F(SH)

27 June 1986

FIGURES - Continued

		<u>Page</u>
Figure	10. Typical viewing screen calibration (butt welds) (with dB control)	78
	11. Typical viewing screen calibration (butt welds) (without dB control)	78
	12. Scanning procedures for welds	79
	13. Scanning procedure for tee welds	80
	14. Typical viewing screen calibration (tee welds) (with dB control)	81
	15. Typical viewing screen calibration (tee welds) (without dB control)	81
	16. Surface opposite attachment member accessible	82
	17. Surface opposite attachment member not accessible	82
	18. Ultrasonic weld inspection record	83
	19. Recommended probe-to-weld attitude for eddy current standardization and scanning operations	84

TABLES

Table	I. Examples of penetrameter identification	16
	II. Penetrameter placement for welds	19
	III. Allowable film-side penetrameters	20
	IV. Definition of radiographic quality levels	21
	V. Minimum radiographic quality levels for Iridium-192 radiography of nonstructural welds	22
	VI. Calibration hole size for longitudinal test	45
	VII. Calibration reference notch dimensions of square and "U" bottom notch	47

MIL-STD-271F(SH)
27 June 1986

1. SCOPE

1.1 General. This standard covers the requirements for conducting nondestructive tests used in determining the presence of surface and internal discontinuities in metals. It also contains the minimum requirements necessary to qualify nondestructive test and inspection personnel, procedures, and nondestructive test equipment. This standard does not contain acceptance criteria for nondestructive tests.

1.1.1 Areas to be tested shall be specified in the applicable drawings, specifications, contract or purchase order. Nondestructive test markings incorporated in drawings shall be in accordance with AWS A2.4.

1.1.2 Since calibration procedures are self-contained in this document, the test instruments and standards contained herein are not included in Calibration Programs defined by MIL-STD-45662 with the exception of linear measuring tools such as mechanical calipers and micrometers.

1.2 Classification. This standard covers the following types of test methods:

- (a) Radiography
- (b) Magnetic particle
- (c) Liquid penetrant
- (d) Ultrasonic
- (e) Eddy current
- (f) Visual inspection

1.3 Acceptance standards. The standards for acceptance shall be as specified in the applicable specification, contract, or order.

1.4 Time of inspection. Unless otherwise specified herein or in the applicable specification, acceptance inspection shall be performed on an item in the final surface condition and final heat treated condition, except as specified in 1.4.1, 1.4.2, 1.4.3 and 1.4.4.

1.4.1 Radiographic inspection may be performed at the following times:

- (a) Before or after stress relief.
- (b) Before or after heat treatment where the heat treatment does not require quenching of the item in a liquid medium.

1.4.2 Casting or forgings may be radiographed in the as-cast, as-forged, or rough machined conditions, provided the requirements of 3.4.4.2 are met.

1.4.3 Weldments that require contouring or machining may be radiographed in the as-welded condition provided the surface condition does not interfere with the interpretation of the radiographs and the penetrometer selection is based on the requirements of 3.4.4.

1.4.4 The final magnetic particle inspection may be accomplished within 1/32 inch of the final machined base metal surface, provided a half wave rectified direct current (dc) direct magnetization method is used for the inspection.

MIL-STD-271F(SH)

27 June 1986

1.5 General definitions.

1.5.1 Authorized representative of the Naval Sea Systems Command (NAVSEA). Unless otherwise specified, the Commander of a Naval Shipyard, the Supervisor of Shipbuilding or their delegated representative.

1.5.2 Government inspector. Government official who is charged with the responsibility for assuring that the materials, processes, fabrication technique and testing personnel meet specification and contractual requirements. In this regard, he or she may be as follows:

- (a) For Government shipyards: The Shipyard Commander or his delegated representative.
- (b) For commercial shipyards: The Supervisor of Shipbuilding or his delegated representative.
- (c) For other organizations: The cognizant Government inspector, his representative or the representative of another Government agency designated by or through the cognizant Government inspector.
- (d) For Forces Afloat: The squadron commander or his delegated representative.
- (e) For Naval Repair Facilities: The commanding officer or his delegated representative.

1.5.3 Activity. A particular site of any commercial or Government activity performing work within the scope of this standard.

1.5.4 Nominal thickness. That thickness specified on plans or drawings without application of any allowed tolerance.

1.5.5 Nondestructive test examiner. Personnel to whom the activity assigns the responsibility and authority to examine and certify nondestructive test personnel to insure that their personnel are competent and qualified to perform the applicable tests in conformance with contractual requirements. This is the individual to whom the activity assigns the responsibility of approving nondestructive test procedures and workmanship standards.

1.5.6 Nondestructive test operator. The individual performing or actually applying the test method.

1.5.7 Nondestructive test inspector. The individual who accepts or rejects the inspected part by comparison of the test results with the acceptance standards.

1.6 Nondestructive test personnel certification. Personnel performing nondestructive testing shall be certified in accordance with the guidelines of ASNT Recommended Practice No. SNT-TC-1A, 1980 Edition. Each activity shall develop a written practice, as required by ASNT Recommended Practice No. SNT-TC-1A, 1980 Edition, identifying the requirements relative to the guidelines. The written practice shall be made available to the Government Inspector upon request. The guidelines of ASNT Recommended Practice No. SNT-TC-1A, 1980 Edition shall be considered as minimum requirements, except as modified herein.

MIL-STD-271F(SH)

27 June 1986

1.6.1 Personnel qualification requirements. Nondestructive test examiner personnel shall be qualified by examinations administered by the Employing Activity, American Society for Nondestructive Testing (ASNT), or other outside agency. The specific examination shall be prepared and administered by the employing activity or an outside agency. The employing activity shall identify minimum passing grade requirements when the basic and method examinations are administered by ASNT, which issues grades on a pass/fail basis. In this case, the passing grade for the basic and method examination shall be assigned a numerical score of 80 percent.

1.6.1.1 Hours of training and experience. The number of hours of training and experience for all nondestructive test personnel shall be in accordance with ASNT Recommended Practice No. SNT-TC-1A, 1980 Edition. However, the hours for personnel who perform only one operation of a nondestructive test method that consists of more than one operation, or perform nondestructive test examinations of limited scope, may be less than those specified in ASNT Recommended Practice No. SNT-TC-1A, 1980 Edition, provided the time of training and experience is described in the written practice, and any limitation or restriction on the certification is described in the written practice and in certification records.

1.6.1.2 Other methods. For nondestructive test methods not covered by ASNT Recommended Practice No. SNT-TC-1A, 1980 Edition, personnel shall be qualified to comparable levels of competency by the administration of comparable examinations on the particular method involved.

1.6.2 Certification of personnel. The employing activity is responsible for the adequacy of the program and is responsible for the certification of all levels of nondestructive test personnel.

1.6.3 Recertification. Nondestructive test personnel shall be recertified by examination at 3-year intervals (as a minimum) in accordance with the activity's written practice. This re-examination shall be as comprehensive as that employed in the initial certification. In addition, personnel who perform production NDT shall be recertified by examination if they have not performed tests (for which they are certified) for a period of 6 months; this re-examination need only consist of an approved operational examination administered by the activity's test examiner.

1.6.4 The Government Inspector may request an operational or written examination be administered if there is reason to believe that an individual is unable to competently perform at the level that the individual is certified.

1.6.5 Vision tests.

1.6.5.1 General. All nondestructive test personnel shall be required to pass a vision test. The vision test must be current at the time of examination and vision tests shall be conducted annually. Vision testing shall be conducted by a qualified technician, using standard test methods for determining visual acuity. The standard of acceptance for vision tests shall be:

MIL-STD-271F(SH)
27 June 1986

- (a) Natural or corrected near distance acuity such that the individual is capable of reading J1 letters on the Standard Jaeger's Test type chart for near vision, or equivalent type test. This requirement must be met by one or both eyes.
- (b) Ability to distinguish between colors when required by the work.

1.6.5.2 Brightness discrimination. All radiographic personnel as defined in 1.5.7, shall additionally be tested for brightness discrimination, using test radiographs containing randomly distributed penetrameters, with varying densities and sizes.

1.6.5.3 The corrective aids used for vision tests must be used during certification examination and all subsequent inspections and tests performed.

1.6.6 Records. Employing activities shall maintain individual nondestructive test personnel records including the following:

- (a) Training and experience.
- (b) Results of all current examinations which can be correlated to the examination administered and a master copy of each examination. When ASNT is used for examiner certification, the ASNT letter may be used for the basic and method examinations.
- (c) A record of vision tests noting corrective aids used.
- (d) Records shall be maintained for the current and preceding certification period unless otherwise stated.

All of the above records shall be made available to the Government Inspector upon request.

1.6.7 Transfer of NDT certifications to other activities is prohibited except as authorized by NAVSEA.

1.7 Procedure qualification and approval. Nondestructive testing methods specified herein shall be performed in accordance with written procedures.

1.7.1 Activities performing NDT shall develop and maintain a written procedure for each method performed and certify that each procedure is in accordance with the requirements of this standard. This certification statement shall be part of each written procedure and signed by the cognizant examiner of the activity.

1.7.2 Each procedure shall have been qualified by proving that known discontinuities, either natural or artificial, can be reliably detected and evaluated. Data documenting this procedure demonstration shall be provided to the Government Inspector upon request. This requirement does not apply to procedures approved under prior revisions of this standard.

1.7.3 Procedures shall be approved by the cognizant examiner of the activity and reviewed by the Government Inspector. The Government Inspector may request demonstration of the procedure during initial review of the procedure or at any time there is reason to believe it is unable to provide adequate results.

MIL-STD-271F(SH)
27 June 1986

1.7.4 Procedures shall not be transferred from one activity to another without the specific approval of NAVSEA.

1.8 Maintenance of inspection records. Records shall be maintained as specified in the applicable ship specifications, fabrication specifications and other documents invoking this standard.

2. APPLICABLE DOCUMENTS

2.1 Government documents.

2.1.1 Specifications and standards. Unless otherwise specified, the following specifications and standards of the issue listed in that issue of the Department of Defense Index of Specifications and Standards (DoDISS) specified in the solicitation form a part of this standard to the extent specified herein.

SPECIFICATIONS

FEDERAL

P-D-680 - Dry Cleaning Solvent.

MILITARY

MIL-I-25135 - Inspection Materials, Penetrants.

STANDARDS

MILITARY

MIL-STD-278 - Fabrication Welding and Inspection; and Casting Inspection and Repair for Machinery, Piping and Pressure Vessels in Ships of the United States Navy.

MIL-STD-792 - Identification Marking Requirements for Special Purpose Components.

MIL-STD-45662 - Calibration Systems Requirements.

(Copies of specifications and standards required by contractors in connection with specific acquisition functions should be obtained from the contracting activity or as directed by the contracting officer.)

2.2 Other publications. The following documents form a part of this standard to the extent specified herein. Unless otherwise specified, the issues of the documents which are DoD adopted shall be those listed in the issue of the DoDISS specified in the solicitation. The issues of documents which have not been adopted shall be those in effect on the date of the cited DoDISS.

AMERICAN SOCIETY FOR TESTING AND MATERIALS (ASTM)

D 3699 - Standard Specification for Kerosine. (DoD adopted)

(Application for copies should be addressed to the American Society for Testing and Materials, 1916 Race Street, Philadelphia, PA 19103.)

MIL-STD-271F(SH)

27 June 1986

AMERICAN WELDING SOCIETY (AWS)

A2.4 - Symbols for Welding and Nondestructive Testing Including
Brazeing. (DoD adopted)

(Application for copies should be addressed to the American Welding
Society, Inc., 550 NW LeJeune Road, P.O. Box 351040, Miami, FL 33135.)

SOCIETY OF AUTOMOTIVE ENGINEERS (SAE)

AMS 3161 - Inspection Oil, Odorless

(Application for copies should be addressed to the Society of Automotive
Engineers, 400 Commonwealth Drive, Warrendale, PA 15096.)

AMERICAN SOCIETY FOR NONDESTRUCTIVE TESTING (ASNT)

SNT-TC-1A. - Recommended Practice for Nondestructive Testing
Personnel Qualification and Certification.

Supplement A - Radiographic Testing Method.

Supplement B - Magnetic Particle Testing Method.

Supplement C - Ultrasonic Testing Method.

Supplement D - Liquid Penetrant Testing Method.

Supplement E - Eddy Current Testing Method.

(Application for copies should be addressed to the American Society for
Nondestructive Testing, Inc., 4153 Arlingate Plaza, Columbus, OH 43228-0518.)

(Nongovernment standards are generally available for reference from
libraries. They are also distributed among nongovernment standards bodies and
using Federal agencies.)

The documents cited in this section are for guidance and information.

2.3 Order of precedence. In the event of a conflict between the text of
this standard and the references cited herein, the text of this standard shall
take precedence.

3. RADIOGRAPHY

3.1 Definitions. The following definitions are applicable to
radiography:

3.1.1 Energy. A property of radiation which determines its penetrating
ability. In X-ray radiography, energy is usually determined by the
accelerating voltage applied to the anode and is expressed as kilovolts (kV)
or million electronvolts (MeV). In gamma-ray radiography, energy is a
characteristic of the source.

3.1.2 Film holders or cassettes. Lightproof containers for holding
radiographic film with or without intensifying screens. These film holders or
cassettes may be rigid or flexible.

MIL-STD-271F(SH)
27 June 1986

3.1.3 Filters. Sheets of lead or other materials placed in the radiation beam, either at the X-ray tube between the specimen and the film, or behind the film to improve image quality by selectively removing low energy components from the radiation beam.

3.1.4 Intensifying screens. Sheets of lead or layers of fluorescent crystals between which the film is placed to decrease the exposure time.

3.1.5 Material thickness (T_m). The thickness of material upon which the penetrameter is based for piping system welds, including repair welds. The material thickness is the nominal thickness or actual thickness, if measured, of the strength member, and does not include reinforcements, backing rings or strips. The strength member is defined as the thinner of the sections being joined (see 3.4.4).

3.1.6 Maximum effective radiation source dimension. The maximum source or focal spot dimension projected on the center of the radiographic film. For example, a cylindrical isotope source whose length is greater than its diameter will have a greater effective radiation source dimension when oriented coaxially in the center of a pipe for a panoramic exposure than when the axis of the source is positioned at right angles to the pipe.

3.1.7 Multiple film technique. A procedure in which two or more films of the same or different speed are used in the same film holder, and exposed simultaneously.

3.1.8 Penetrameter. A device whose image in a radiograph is used to determine radiographic quality level. It is not intended for use in judging the size nor for establishing acceptance of discontinuities.

3.1.9 Penetrameter sensitivity. An indication of the ability of the radiographic procedure to demonstrate a certain difference in specimen thickness (usually 2 percent). It is the ratio expressed as a percentage of the thickness of a penetrameter whose outline is discernible in a radiograph to the material thickness (T_m) of the specimen radiographed.

3.1.10 Radiograph. A visible image on film produced by the penetration of radiation through the material being tested. When two superimposed films are exposed simultaneously in the same film holder, to be viewed later as a superimposed pair, the superimposed pair of exposed film constitutes the radiograph.

3.1.11 Radiographic film density. A quantitative measure of film blackening, defined by the equation:

$$d = \log_{10} \frac{I_o}{I_t}$$

Where:

d = density.
 I_o = the light intensity incident on the film.
 I_t = the light intensity transmitted through the film.

MIL-STD-271F(SH)

27 June 1986

3.1.12 Radiographic inspection. The use of X-rays and gamma-rays, or both, to detect discontinuities in material by presenting their images on recording medium suitable for interpretation by a qualified inspector (see 1.5.7).

3.1.13 Radiographically similar materials. Materials which have similar X-ray or gamma-ray absorption characteristics, regardless of chemical composition.

3.1.14 Shielding. Sheets of lead or other material used to absorb scattered radiation.

3.1.15 Source. A machine or radioactive material which emits penetrating radiation.

3.1.16 Source-to-film distance. The distance between the radiation source and the film.

3.1.17 Specimen thickness (T_s). The total thickness to be radiographed. This is the thickness upon which the source-to-film distance is based, and is also the thickness upon which penetrameters are based for structural castings, and structural welds.

3.2 General requirements. The radiographic method of testing is used for determining the presence of discontinuities in all ferrous and nonferrous metals. Radiographic inspection specified herein is intended to apply to all items requiring radiographic inspection in compliance with applicable specifications, drawings, contracts, or purchase orders, and one of the following shall be used:

- (a) X-ray machine.
- (b) Iridium-192.
- (c) Cobalt-60.
- (d) Cesium-137.
- (e) The use of other radiation sources requires specific NAVSEA approval.

3.2.1 Extent of radiographic inspection. All procurement documents, drawings, or both shall specify the extent of radiographic inspection, when it is required. This information shall include the number of areas and items to be radiographed, the point in fabrication when radiography shall be performed, the quality level of inspection and the acceptance standard to be applied. Drawings specifying radiographic coverage requirements shall employ radiographic symbols that are in accordance with AWS A2.4.

3.2.1.1 Radiographic Shooting Sketch (RSS) for castings. The casting designer shall select and identify, in accordance with AWS A2.4, areas requiring radiography on the engineering drawing. The contractor or activity performing the inspection shall prepare the RSS which shows film placements and radiation directions to assure adequate radiographic coverage as specified by the engineering drawing. The RSS shall be validated by a signature of a certified radiographic inspector. The requirements of 3.3.14 herein provide specific detailed requirements which shall be contained on the RSS.

MIL-STD-271F(SH)

27 June 1986

3.2.2 Radiographic procedure. Radiographic inspection procedures shall contain as a minimum, the following elements:

3.2.2.1 Minimum radiographic procedure requirements.

- (a) X-ray machine information.
 - (1) Model and type
 - (2) Manufacturer
 - (3) Focal spot size
 - (4) Voltage rating
- (b) Isotope source information
 - (1) Type of isotope
 - (2) Source strength (maximum)
 - (3) Source dimensions
- (c) Film processing methods
- (d) Personnel qualifications
- (e) Film type
- (f) Viewing facilities
- (g) Film density requirements including density measuring equipment used
- (h) Method of providing film identification in accordance with 3.3.8
- (i) The requirements of this standard that apply

3.2.2.2 Survey of radiographic facilities. The Government Inspector shall perform radiographic facilities and procedure surveys of activities to ensure that the organization is performing radiographic inspection in accordance with the requirements of this standard. The surveys may be conducted at 12-month intervals unless the quality of radiographic performance dictates a need for more frequent surveillance. The Government Inspector shall maintain a record of the results of each survey. The records shall include sufficient information to establish that the activity is performing radiographic inspection in accordance with its procedure and this standard.

3.3 Radiography requirements.

3.3.1 Direction of radiation. Unless otherwise specified, the direction of the central beam of radiation shall be as nearly central to the area being examined and perpendicular to the surface of the film as possible.

3.3.2 Screens, filters, and masking. All radiographs produced with a source of 150 kV or greater shall employ a front and back lead screen in contact with the film. Intensifying screens and filters shall be as follows:

- (a) Intensifying screens. Lead oxide or lead foil shall be used as intensifying screens. Lead oxide, however, shall only be used for energies between 100 and 300 kV. Intimate contact between the screens and the films should be maintained during exposure.
- (b) Front filters. When using radiation sources with energies of 0.7 MeV or greater (including Cobalt-60), a lead filter with a minimum thickness of 0.010 inch shall be placed between the specimen and the film. The filter may be located either in

MIL-STD-271F(SH)
27 June 1986

the film holder and may be combined with the intensifying screen, or may be located in front of the film holder. However, if the filter is located in front of the film holder, the screens shall be placed in contact with the film, as in (a) above.

- (c) Back filters. Lead filters shall be used behind the film holder to prevent scattered radiation from the floor, walls, air, or other surrounding objects from fogging the film. Each holder shall have a lead letter "B" a minimum of 1/2 inch high and a minimum of 1/16 inch thick positioned behind the film and within the area of film to be read. When performing panoramic exposures, one lead letter "B" may be placed in each quadrant. The lead letter "B" is not required for radiography of circumferential welds with an inside diameter less than 3/4 inch which are performed by the single wall exposure technique. If the image of the letter "B" shows a light image on a darker background, the radiograph shall be rejected. A darker image of the letter "B" on a lighter background is not cause for rejection provided the darker image does not interfere with the film evaluation.

3.3.3 Film. Radiographs shall be made on fine grain, extra-fine grain or ultra-fine grain, safety base film. High-speed, medium or coarse grain films shall be used only when authorized by NAVSEA or its authorized representative.

3.3.3.1 Film quality. Radiographs presented for interpretation shall be free from blemishes or film artifacts which might mask or be confused with defects in the material being examined. If doubt exists concerning the true nature of an indication on the film, the radiograph shall be rejected. Typical blemishes are as follows:

- (a) Fogging caused by light leaks in the processing room or cassettes, defective safelights, exposure marks caused by improper processing, or old film.
- (b) Mechanical processing defects such as streaking, air bells, water marks, or chemical stains.
- (c) Blemishes caused by dirt in cassettes, particularly between intensifying screens and the film.
- (d) Pressure or lead marks, scratches, gouges, finger marks, crimp marks, or static electricity marks.
- (e) Loss of detail caused by poor film-to-screen contact in localized areas.

3.3.3.2 Film density. The density shall be 1.5 to 4.0 for single film viewing and 2.0 to 4.0 for superimposed film viewing in the area being examined for acceptance. For castings and forgings, the density shall be 1.5 to 4.0 in the area being examined for acceptance for both the single and superimposed film viewing. When the thickness of the part varies considerably in the area under examination, two or more films, either of equal or of different speeds may be exposed simultaneously in the same film holder and the resultant radiograph submitted for interpretation either as single or superimposed film, whichever

MIL-STD-271F(SH)

27 June 1986

is better suited for the interpretation of any small portion of the area covered by the exposure. For the small portion of the area under immediate examination, the density of either the single or the superimposed film shall be in accordance with the aforementioned requirements.

3.3.3.3 Multiple film techniques. Film techniques with two or more films of the same or different speeds in the same film holder shall be permitted, provided the applicable radiographic quality level for a specific area is demonstrated.

3.3.4 Filmless techniques. The use of filmless techniques shall be limited to in-process inspection and shall not be permitted for final acceptance inspection unless specifically authorized by NAVSEA.

3.3.5 Radiation sources. Recommended X-ray machine voltage settings and gamma-ray sources to be used with various specimen thicknesses are shown on figures 1, 2 and 3. Cobalt-60 sources shall not be used on nominal material thicknesses less than 1 inch. Other voltage settings or sources may be used provided the required quality levels are maintained.

3.3.6 Source-to-film distance.

3.3.6.1 The source-to-film distance shall be such that the geometric unsharpness (U_g) values of figure 4B are not exceeded. Source-to-film distance (SFD) shall be calculated as follows:

$$SFD = t + \frac{Ft}{U_g}$$

Where:

U_g = Geometric unsharpness

F = Maximum effective radiation source dimension in inches (see 3.1.6)

t = Specimen thickness T_s in inches

SFD = Distance, in inches, between radiation source and source side of specimen

3.3.6.2 When a gap between the specimen and film holder is unavoidable, the SFD shall be increased by the ratio of:

$$\frac{t + \text{gap}}{t}$$

3.3.6.3 When using radioisotope sources whose lengths are greater than 1/8-inch, the SFD shall be increased in accordance with figure 4C to compensate for increased dispersion caused by side effects.

3.3.6.4 When accessibility does not permit compliance with the above, a shorter source-to-film distance is allowed provided the following conditions are met:

MIL-STD-271F(SH)
27 June 1986

- (a) The required quality level is obtained.
- (b) The greatest possible source-to-film distance is used.
- (c) The radiographic record shows what accessibility conditions limited the source-to-film distance and indicates the actual source-to-film distance used.

3.3.7 Radiographic location markers. The images of the location markers for the coordination of the part with the film shall appear on the film without interfering with the interpretation and with such an arrangement that it is evident that complete coverage was obtained. These marker positions shall be marked on the part and the position of the markers shall be maintained on the part during radiography. When using a technique in which radiation passes through two walls and the welds in both walls are viewed for acceptance, and the entire image of the object being radiographed is shown on the radiograph, only one location marker is required on the base metal at the center of the area being examined. Markings shall be in accordance with MIL-STD-792.

3.3.8 Film identification. A system of positive identification of the film shall be used and each film shall have a unique identification relating it to the item being inspected. As a minimum, the following additional information shall appear on each radiograph or in the records accompanying each radiograph:

- (a) Identification of the organization making the radiograph.
- (b) Date of exposure.
- (c) Identification of the part, component or system and, where applicable, the weld joint in the part, component or system.
- (d) Whether the radiograph is of the original area or a repair area.

3.3.9 Maintenance of radiographic records. Radiographic records shall be maintained in accordance with 1.8.

3.3.10 Darkroom facilities. Darkroom facilities, including equipment and materials, shall be capable of producing uniform, blemish-free radiographic negatives.

3.3.11 Film viewing facilities. Viewing facilities shall be so constructed as to afford the exclusion of objectionable background lighting of an intensity that may cause reflection on the radiographic film.

3.3.11.1 Equipment used for radiographic interpretation shall provide the following minimum features:

- (a) A light source of sufficient intensity controlled to allow the selection of optimum intensities for viewing film densities specified in 3.3.3.2. The required intensity range may be provided by the use of a separate high intensity viewing port. The light enclosure shall be so designed to provide a uniform level of illumination over the entire viewing surface.
- (b) A suitable fan, blower or other cooling device to provide stable temperature at the viewing port such that film emulsions shall not be damaged during 1 minute of continuous contact with the viewing surface.

MIL-STD-271F(SH)

27 June 1986

- (c) An opal glass front in each viewing port, except for high intensity viewers used for high density film.
- (d) A set of opaque masks to suit the sizes of radiographs to be viewed.
- (e) Densitometers (MacBeth Model TD-102, or equal) shall be provided for assuring conformance with film density requirements.

3.3.12 Surface preparation of components and welds prior to radiography. Metal components shall be free of scale, surface slag, adhering or imbedded sand, or other surface conditions which may interfere with proper interpretation of radiographs. With the exception of undercuts at the toe of the weld which are within specification allowances, the contour of welds shall be blended smoothly and gradually into the base metal. Excessive weld ripples or weld surface irregularities on the outside (and inside, if accessible) shall be removed by any suitable mechanical process to such a degree that the resulting radiographic contrast due to any irregularity cannot mask or be confused with the image of a defect.

3.3.13 Safety. Radiographic tests shall be performed under protected conditions such that personnel shall not receive a whole-body radiation dosage exceeding the maximum permitted by city, state or national codes.

3.3.14 Interpretation of radiographs. To aid in the proper interpretation of radiographs, a sketch, drawing, written procedure or equivalent record shall be prepared to show the setup used to make each radiograph. The information shall accompany each radiograph (or a group of radiographs if the same information applies). Reference to a standard setup is acceptable if descriptions of this standard setup are made available. The information shall include:

- (a) Number of films and film type.
- (b) Location of each film on the radiographed item.
- (c) Orientation of location markers.
- (d) Location of radiation source, including source-to-film distance and approximate angle of beam.
- (e) The kilovoltage and focal spot size (for X-ray machines).
- (f) The isotope type, intensity (in curies), and physical dimensions.
- (g) Type of material, and material thickness.
- (h) Type of weld joint, for example, butt with backing ring.
- (i) Whether original or repair.
- (j) Part and drawing number.
- (k) Material groups and penetrameter sizes and the required quality level.
- (l) Single or double wall viewing.
- (m) Type and thickness of intensifying screens and filters.
- (n) Applicable acceptance standards.
- (o) Signature of the radiographic operator.

3.3.15 Radiographic records. Radiographic records shall contain the following:

- (a) The information specified in 3.3.14.
- (b) Notation of acceptable and rejectable discontinuities. Any

MIL-STD-271F(SH)
27 June 1986

questionable discontinuity in the area of interest which is due to a surface condition shall be visually verified and noted.

- (c) Date of interpretation.
- (d) Disposition (accept/reject) of the item radiographed.
- (e) Signature of the radiographic inspector.

3.3.16 Radiographs and records shall be made available to the Government Inspector upon request.

3.4 Penetrameters. Penetrameters shall be employed for all radiographs, except as specified in 3.8, and the penetrameter image will be employed to determine the radiographic quality level.

3.4.1 Penetrameter material. Material grouping for penetrameter material shall be as follows, except that penetrameters of a lower group number may be used for any material group of a higher number providing the applicable quality level is maintained. For material not listed, the penetrameter material shall be as specified in 3.4.1.2.

Material, Group I

Carbon steel
Alloy steel
Stainless steel
Manganese-nickel-aluminum bronze

Penetrameters, Group I

Penetrameters made of any of these materials may be used interchangeably.

Material, Group II

Aluminum bronze
Nickel-aluminum-bronze

Penetrameters, Group II

Penetrameters made of any of these materials may be used interchangeably.

Material, Group III

Nickel-chromium-iron alloy

Penetrameters, Group III

Nickel-chromium-iron alloy.

Material, Group IV

Nickel-copper alloys
Copper-nickel alloys

Penetrameters, Group IV

Penetrameters made of any of these materials may be used interchangeably.

Material, Group V

Tin bronze
Gun metals
Valve bronze

Penetrameters, Group V

Penetrameters made of any of these materials may be used interchangeably.

3.4.1.1 Dissimilar metal welds.

3.4.1.1.1 For welds made between dissimilar metals in any one group, the grade penetrameters for that group or penetrameters of a lower grade number shall be used, provided the quality level as applicable is maintained.

MIL-STD-271F(SH)

27 June 1986

3.4.1.1.2 For welds made between dissimilar metals not of the same materials group, two penetrameters shall be used, one on each side of the joint. Each penetrameter shall be of the grade number representing the base metal upon which it is placed, or a lower grade number penetrameter may be used. Quality level, as applicable, shall be the same as would be applicable for single penetrameters of weld joints of similar base metals.

3.4.1.2 Other metals. For radiography of materials not herein covered, penetrameters of the same material may be used, or penetrameters of any other material may be used if the following requirements are met. Two blocks of equal thickness, one of the material to be radiographed and one of the material of which the penetrameters are made, shall be radiographed on the same film by one exposure at the lowest energy level to be used for the production radiographs. Densitometer readings for both materials shall be read from the film and shall be between 2.0 and 4.0 density for both materials. If the film density for the material to be radiographed is within plus 15 percent or less than the film density for the penetrameter material, the penetrameter material may be used for radiography of the production material.

3.4.2 Penetrameter dimensions. The dimensions of the penetrameter shall conform to those shown on figure 4.

3.4.3 Penetrameter identification. Penetrameters shall be identified with lead numbers or engraved lead strips indicating the material thickness (T_m or T_s as applicable) to which the penetrameter applies as specified in table I.

- (a) Rectangular penetrameters shall be identified with lead numbers attached to the penetrameters, as shown on figure 4.
- (b) The lead numbers shall indicate the nominal material thickness (T_m) in hundredths of an inch up to 1 inch, and in inches to the nearest tenth of an inch over 1 inch.
- (c) Each penetrameter shall be further identified by permanently marking its metal or principal alloy composition into the surface of the penetrameter, and by notches in accordance with figure 4A.

3.4.3.1 Lead numbers shall be placed adjacent to the circular penetrameters to provide identification of the penetrameter on the film.

3.4.3.2 For the special levels 1-1T and 1-2T, this lead number shall indicate one-half the minimum thickness to which the penetrameter is applicable, and for level 4-2T, this lead number shall indicate twice the minimum thickness to which the penetrameter is applicable.

MIL-STD-271F(SH)
27 June 1986

TABLE I. Examples of penetrameter identification.

Penetrameter identification number ²	Penetrameter thickness Inch	Min material thickness T_m ¹ Inches
25	0.005	0.25
50	.010	.50
75	.015	.75
1.0	.020	1.0
1.5	.030	1.5
2.0	.040	2.0
3.0	.060	3.0
5.5	.110	5.5
9.0	.180	9.0
10.0	.200	10.0

¹ The 0.005-inch penetrameter shall be used for material thickness less than 0.25 inch unless otherwise specified in the applicable specification or purchase order.

² For 2 percent penetrameter sensitivity:

(a) Standard radiographic quality levels.

(1) 2-2T: This requires that a penetrameter whose thickness (T) is no greater than 2 percent (1/50) of the material thickness of the item being radiographed and a hole drilled through the penetrameter with a diameter equal to twice the thickness of the penetrameter (2T) shall be visible.

(b) Special radiographic quality levels.

(1) Quality level 1-1T radiography. The 1T hole in a penetrameter whose thickness (T) is no greater than 1 percent (1/100) of the material thickness shall be visible.

(2) Quality level 2-1T radiography. The 1T hole in a penetrameter whose thickness (T) is no greater than 2 percent (1/50) of the material thickness shall be visible.

(3) Quality level 1-2T radiography. The 2T hole in a penetrameter whose thickness (T) is no greater than 1 percent (1/100) of the material thickness shall be visible.

(4) Quality level 2-4T radiography. The 4T hole in a penetrameter whose thickness (T) is no greater than 2 percent (1/50) of the material thickness shall be visible.

MIL-STD-271F(SH)

27 June 1986

- (5) Quality level 4-2T radiography. The 2T hole in a penetrameter whose thickness (T) is no greater than 4 percent (1/25) of the material thickness shall be visible.

3.4.4 Penetrameter selection.

3.4.4.1 Welds. Penetrameter selection shall be based on the following:

- (a) Structural welds: The penetrameter shall be based on specimen thickness T_S as defined in 3.1.17.
- (b) Piping, machinery and pressure vessel welds: The penetrameter shall be based on material thickness T_m as defined in 3.1.5.

3.4.4.2 Castings and forgings. Castings or forgings may be radiographed in the as-cast, as-forged, or rough machined conditions provided the surface condition does not mask respectable defects and the following requirements for penetrameter selection are met:

- (a) Structural castings. The penetrameter shall be based on the actual or nominal thickness being radiographed.
- (b) Other castings. The penetrameter thickness shall be based on the actual or nominal thickness being radiographed. However, if the thickness to be radiographed exceeds the nominal thickness of the finished piece, the penetrameter size shall be based on a thickness which does not exceed the nominal thickness of the finished piece by more than 20 percent or 1/4 inch, whichever is greater. The penetrameter size shall not be based on a thickness greater than the actual thickness to be radiographed. For areas in castings which have been end-prepared for welding, the penetrameter shall be selected based on the actual or nominal thickness of the area adjacent to, but exclusive of, the weld end-preparation.

3.4.5 Acceptance standards. Acceptance standards shall be based on the nominal thickness of the finished part except that, for structural casting, the acceptance standards may be based on the actual thickness being radiographed.

3.4.6 Number, location, and placement of penetrameters.

3.4.6.1 Penetrameter location. The penetrameter shall be placed on the source side of the section being examined. In the inspection of irregular objects, the penetrameter shall be placed on the part of the object farthest from the film. When performing double-wall radiography, the penetrameter shall be placed on the surface of the wall or walls being evaluated nearest the source of radiation (see figure 5). Where this is not practicable, the film side technique specified in 3.4.6.1.1, 3.4.6.1.2, or the separate block technique of 3.4.6.1.3 may be employed.

3.4.6.1.1 Film-side penetrameter technique (double-wall exposure). The film-side penetrameter placement technique shall be as shown on figure 5-7. The radiographic technique shall be demonstrated in a similar section with the applicable penetrameter placed on the source side of the wall for which radiography is desired, and a series of penetrameters, ranging in thickness from

MIL-STD-271F(SH)

27 June 1986

that of the penetrameter required on the source side to one-fourth that thickness, shall be placed on the film side. If the proper penetrameter on the source side indicates the required quality level, the image of the smallest hole in the thinnest penetrameter clearly visible on the film side shall be used to determine the penetrameter and the penetrameter hole to be applied in evaluating production radiographs. Technique radiographs shall be made available for review upon request by the Government Inspector. Table III contains a list of film side penetrameters which may be used in lieu of performing technique radiography and selection of penetrameters as described above.

3.4.6.1.2 Film-side penetrameter technique (single-wall exposure).

For large diameter pipe (8-inch and over) where the diameters are such that the source may be placed inside the pipe for simultaneous single-wall radiography of welds but source-side penetrameter placement is not feasible, a film-side penetrameter technique may be employed provided the requirements of 3.3.6 and the radiographic quality level of the source-side penetrameter being 2-2T as required by 3.6. When using an Iridium-192 source, the required source-side penetrameter may be selected from table V for the applicable wall thickness for single-wall viewing technique, or 2-4T for welds less than 3/4 inch thick, whichever is less restrictive, and the film-side penetrameter selected from table III.

3.4.6.1.3 Separate block penetrameter technique.

The penetrameter may be positioned on a block of radiographically similar material placed as close as possible to the area being radiographed. The block shall be of thickness equal to or greater than the thickness of the item being radiographed and, in piping 1-inch nominal pipe size and larger, shall be positioned so that the penetrameter is at the same distance from the film as it would be if placed on the source side of the item being radiographed. The film density of the block image shall be not greater than 15 percent more than the film density of the area of interest. It may be less dense than the density of the area of interest.

3.4.6.2 Requirements for casting and forgings.

One penetrameter shall represent an area within which radiographic densities do not vary more than plus 30 percent to minus 15 percent from the density measured adjacent to the penetrameter. At least one penetrameter per radiograph shall be used except as specified in 3.8. If a shim is positioned under the penetrameter, density measurements shall be made on that part of the shim adjacent to the penetrameter. When the film density varies by more than minus 15 to plus 30 percent, two penetrameters used as follows will be satisfactory. If one penetrameter shows an acceptable sensitivity at the most dense portion of the radiograph, and the second penetrameter shows an acceptable sensitivity at the least dense portion of the radiograph, these two penetrameters shall serve to qualify the radiograph within the density limits. For components where there are changes in wall thickness and wall alignment, and the use of two penetrameters is not practical, the use of one penetrameter is approved. The required penetrameter density tolerance need not be met; however, the density in areas of interest shall be between 1.5 and 4.0. Where only one penetrameter is used, the penetrameter size shall be based on the thinnest wall being radiographed and shall be placed on the thickest wall section.

3.4.6.3 Requirements for welds.

The number and placement of penetrameters for specific configurations shall be as specified in table II, and the following:

MIL-STD-271F(SH)

27 June 1986

3.4.6.3.1 The image of the penetrameter or the shim on which the penetrameter is placed shall not be superimposed on the weld in the area being evaluated.

3.4.6.3.2 The image of the penetrameter shall be not greater than 1-1/4 inch from the edge of the weld as shown on the radiograph.

3.4.6.3.3 Penetrameters may be placed on the weld outside the area to be read for acceptance.

3.4.6.3.4 Penetrameters may be placed with the long axis either parallel or perpendicular to the length of the weld.

TABLE II. Penetrameter placement for welds.

Configuration	Inspected weld length (inches)	Minimum no. of penetrameter	Penetrameter placement
Welds in curved surfaces less than 24 inches in diameter	5 and less	1	At the center of the area of interest
	Greater than 5	2	One at the extremity and one at the center of the area of interest
Welds in flat surfaces and curved surfaces 24 inches and greater diameter (includes longitudinal welds in pipes and pressure vessels)	Less than 10	1	At the center of the area of interest
	10 up to and including 17	2	One placed at each extremity of the area of interest
	Greater than 17	3	One placed at each extremity and one at the center of the area of interest
Essential circular (non-cylindrical welds on one film)	Unlimited	2	Approximately 180 degrees apart at the extremity of the area being inspected
Cylindrical welds radiographed simultaneously using a series of film or a single length of roll film (panoramic exposure)	Unlimited	4	One in each quadrant
Repairs in cylindrical welds initially radiographed using panoramic exposure technique	Unlimited	1	One in each affected quadrant, provided the technique used is the same as the initial radiography

MIL-STD-271F(SH)

27 June 1986

TABLE III. Allowable film-side penetrameters.

Required source-side penetrameter		Allowed film-side penetrameter		Required source-side penetrameter		Allowed film-side penetrameter	
Size	Sensitivity	Size	Sensitivity	Size	Sensitivity	Size	Sensitivity
25	2T	25	2T	70	4T	65	4T
30	2T	25	4T	75	2T	70	2T
35	2T	30	4T	80	2T	75	2T
40	2T	35	4T	85	2T	80	2T
45	2T	40	4T	90	2T	85	2T
50	2T	45	2T	95	2T	90	2T
50	4T	45	4T	1.0	2T	95	2T
55	2T	50	2T	1.2	2T	1.0	2T
55	4T	50	4T	1.5	2T	1.0	2T
60	2T	55	2T	1.7	2T	1.0	2T
60	4T	55	4T	2.0	2T	1.0	2T
65	2T	60	2T	2.2	2T	1.2	2T
65	4T	60	4T	2.5	2T	1.2	2T
70	2T	65	2T	2.7	2T	1.5	2T

3.5 Shims. When a weld reinforcement or backing ring or backing strip are not removed, a shim of material which is radiographically similar to the backing ring or strip shall be placed under the penetrameter to provide the same thickness of material under the penetrameter as the average thickness of the weld reinforcement plus the wall thickness and the backing ring. The shim shall exceed the penetrameter dimensions by at least 1/8 inch on at least three sides, and shall be placed so as not to overlap the backing strip or ring or reinforcement. The film density of the shim image shall not be greater than 15 percent more than the film density of the area of interest. It may be less dense than the film density of the area of interest.

3.5.1 Shims for backing ring welds. When weld images are superimposed, the thickness of the shims shall be equal to twice the average thickness of the weld reinforcement plus twice the thickness of the backing ring.

3.5.2 Shims for consumable insert welds. When weld images are superimposed, the thickness of the shims shall be equal to twice the average thickness of the outside reinforcement plus twice the average thickness of the inside reinforcement.

3.6 Radiographic quality levels. Unless otherwise specified in the applicable specification, contract or drawing, the radiographic quality level shall be 2-2T, except as noted in 3.6.1 and 3.6.2. Penetrameter identification, definition of radiographic quality level, and design are specified in tables I and IV, and figures 4 and 4A, respectively.

MIL-STD-271F(SH)

27 June 1986

TABLE IV. Definition of radiographic quality levels.

Radiographic quality level	Max penetrameter thickness ¹ (percent)	Min perceptible hole diameter ²	Equivalent penetrameter sensitivity ³ (percent)
1-1T	1	1T	0.7
1-2T	1	2T	1.0
2-1T	2	1T	1.4
2-2T	2	2T	2.0
2-4T	2	4T	2.8
4-2T	4	2T	4.0

¹ Expressed as a percentage of the material thickness (T_m) or (T_s), as applicable.

² Expressed as multiple of thickness of penetrameter (T).

³ Equivalent penetrameter sensitivity is that thickness of the penetrameter, expressed as a percentage of the material thickness, in which a 2T hole would be visible under the same radiographic conditions.

3.6.1 X-ray radiography. For welds under the following conditions, a 2-4T quality level is acceptable:

- (a) For butt welds with permanent backing, where the material thickness (T_m) is less than 1/2 inch.
- (b) For penetration and connection welds (figures 5-8 and 5-9) where the T_{m1} thickness is less than 2 inches.

3.6.2 Radioisotope radiography. When radioisotopes are used, the quality level and selection of penetrameter shall, as a minimum, be in accordance with table V. For welds and components not specified in table V, the 2-4T quality level is acceptable under the following conditions:

- (a) Penetration and connection welds (figures 5-8 and 5-9) when the T_{m1} thickness is less than 2 inches (applicable to all isotopes).
- (b) Components and welds, other than above, when the T_m is less than 3/4 inch (applicable to Iridium-192 only).

MIL-STD-271F(SH)
27 June 1986

TABLE V. Minimum radiographic quality levels for Iridium-192 radiography of nonstructural welds.

Design material thickness (inches)	Type of exposure and viewing technique	Source-side penetrameter number ¹	Nominal penetrameter thickness (inches)	Minimum perceptible hole	Nominal diameter of penetrameter hole (inches)
Up to 0.199	Double-wall exposure Double-wall viewing	50	0.010	4T	0.040
0.200 - .235		55	.011	4T	.044
.236 - .275		60	.012	4T	.048
.276 - .298		65	.013	2T	.026
.299 - .321		70	.014	2T	.028
.322 - .343		75	.015	2T	.030
.344 - .359		80	.016	2T	.032
.360 - .375		85	.017	2T	.034
.376 - .432		90	.018	2T	.036
.433 - .489		95	.019	2T	.038
.490 - .547		1.0	.020	2T	.040
Up to 0.500	Single-wall viewing (Single- or double-wall exposure)	50	0.010	4T	0.040
0.501 - .555		55	.011	4T	.044
.556 - .600		60	.012	4T	.048
.601 - .642		65	.013	2T	.026
.643 - .684		70	.014	2T	.028
.685 - .725		75	.015	2T	.030
.726 - .816		80	.016	2T	.032
.817 - .906	85	.017	2T	.034	

¹ This penetrameter is to be used for both insert and backing ring joints regardless of the amount of reinforcement or thickness of backing ring.

3.7 Single-wall and double-wall radiography.

3.7.1 Single-wall radiography. Radiographs shall be made through single wall to the greatest extent practicable. Shims under the penetrameter shall be in accordance with 3.5.

3.7.2 Double-wall radiography.

3.7.2.1 Double-wall exposure/single-wall viewing. For welds in pipe greater than 3-1/2 inch nominal pipe size, only the weld closest to the film shall be viewed for acceptance. The source shall be positioned in such a location that the source-side weld image does not obscure the image of the film-side weld. Shims under the penetrameter shall be provided in accordance with 3.5. The minimum source-to-film distance shall be calculated based on the T_s value illustrated on figure 5-7 and 3.3.6.

MIL-STD-271F(SH)
27 June 1986

3.7.2.2 Double-wall exposure/double-wall viewing. Welds in pipe or tube 3-1/2 inches or less nominal pipe size may be radiographed using a technique in which the radiation passes through two walls and the weld in both walls is viewed for acceptance on the same film. The radiation beam may be offset from the plane of the weld at an angle sufficient to separate the images of source-side and film-side portions of the weld. Shims under the penetrometer shall be provided in accordance with 3.5. The minimum source-to-film distance shall be calculated using the outside diameter of the pipe or section as the specimen thickness T_s (see figure 5-6 and 3.3.6).

3.8 Radiography of parts. Penetrameters are not required on each film when placement of the penetrometer on the part would obscure part or all of the area of interest, and where it would not be practicable to place the penetrometer on a block adjacent to the part, as specified in 3.4.6.1.3. However, an initial technique shot with the applicable penetrometer on the part shall demonstrate the specified penetrometer hole, and subsequent exposure without a penetrometer shall be made, only if exposed in the same manner as the technique shot. Whenever the setup is changed, and at least once each work shift, additional technique shots shall be made in proper sequence to assure that the process is being properly controlled. The technique shots shall accompany the subsequently exposed film when presented for interpretation by the radiographic inspector of each organization or for review by the Government inspector. If multiple parts or components are exposed simultaneously, at least one penetrometer shall be required on each film plus additional penetrameters as required by table II.

3.9 Radiography of repair welds. When weld repairs are made to castings and forgings, to remove defects revealed by radiography, the original radiographs of the previously defective areas shall be submitted for review with the final acceptance radiographs. For those items where radiography is required for the repair, a sketch showing the location, size, and shape of the repair weld shall accompany the radiograph. Penetrameters, location markers or film identification shall not be placed in the weld repair areas being inspected.

3.10 Radiography of castings and forgings. Whenever possible a single-wall technique shall be used; however, for casting and forging areas with nominal internal dimensions 4 inches or less a double-wall technique may be used. The minimum source-to-film distance shall be calculated using the outside diameter of the item radiographed as specimen thickness T_s .

3.11 Radiographic film ownership. Unless otherwise specified, radiographic film and the associated inspection records of an item shall become the property of the purchaser of the item. Maintenance of radiographic records shall be in accordance with 1.8.

4. MAGNETIC PARTICLE TESTING

4.1 Intended use. The inspection process is intended for the detection of surface or near surface discontinuities in magnetic materials. Drawings specifying magnetic particle inspection shall employ symbols in accordance with AWS A2.4.

MIL-STU-271F(SH)

27 June 1986

4.2 Definitions.

4.2.1 Arc strikes. Any localized heat-affected zone with a change in the contour of the surface of the finished weld or adjacent base metal resulting from an arc or heat generated by the passage of electrical energy between the surface of the finished weld or base metal and magnetic particle inspection electrodes.

4.2.2 Black light. Black light is the term popularly applied to the invisible radiant energy in that portion of the ultraviolet spectrum just beyond the blue of the visible spectrum. It is the range between 320 and 400 nanometers in wave length.

4.2.3 Circular method. The circular method consists of inducing a circular magnetic field in the piece such that the magnetic lines of force (in any one plane normal to the axis of the current) take the form of concentric rings about the axis of the current. This is accomplished by passing the current directly through the piece or through a conductor which passes into or through a hole in the piece. The circular method is applicable for the detection of defects with axis approximately parallel or radial to the direction of the current through the piece.

4.2.4 Continuous method. The continuous method of examination consists of applying or otherwise making available on the surface of the piece an ample amount of ferromagnetic particles to form satisfactory indications while the magnetizing current is being applied.

4.2.5 Fluorescence. Fluorescence is a term used to describe the effect produced by certain chemical products which exhibit the property of emitting visible light during activation by black light. These materials absorb the invisible energy, alter its wave length, and emit the energy in the form of light which is visible to the eye.

4.2.6 Longitudinal method. The longitudinal method consists of inducing a magnetic field in the piece such that the magnetic lines of force extending through the piece are approximately parallel to the axis of the magnetizing coil, or to a line connecting the two poles when electromagnets are used, and tend to follow the contour of the piece. This method is applicable for detection of defects with axes approximately transverse to the axis of the coil or to a line connecting the two points of application of the electromagnets.

4.2.7 Magnetic particles. The magnetic particles used for obtaining patterns of discontinuities shall be of a nontoxic, finely divided ferromagnetic material of high permeability and low retentivity, free from deleterious rust, grease, paint, dirt or other material which might interfere with their proper functioning. Particles shall be of such size, shape and color as to provide adequate sensitivity and contrast for the intended use. Particles to be used at elevated temperature shall provide adequate contrast and particle mobility at the maximum temperature at which inspection is to be performed.

MIL-STD-271F(SH)

27 June 1986

4.2.8 Residual method. In the residual method of examination, the magnetic particles are applied to the piece after it has been magnetized and the magnetizing current is off.

4.2.9 Relevant indications. Accumulations of magnetic particles caused by discontinuities in the item tested which shall be evaluated to the applicable acceptance criteria.

4.2.10 Indication. Any magnetically held magnetic particle pattern on the surface of a part being tested.

4.2.11 Non-relevant indications. Accumulations of magnetic particles held to a particular area caused by conditions which have no bearing on the suitability of the part for service. Examples of such indications are as follows:

- (a) Magnetic writing. Indication is fuzzy and will be destroyed by demagnetization. These indications are caused by contact with other steel or magnets while magnetized.
- (b) Change in section. Indications are broad and fuzzy caused by concentration of magnetic field.
- (c) Flow lines. These are large groups of parallel indications which occur in forgings under excessive currents.
- (d) Change in permeability.

4.3 Magnetic particle inspection requirements.

4.3.1 General requirements.

4.3.1.1 Method. Magnetic particle inspection may be performed by either the wet or dry method. Where practical, the wet method shall be used on machined surfaces (250 ra or smoother).

4.3.1.1.1 Lighting in test area. The test area may be adequately illuminated for proper evaluation of indications revealed on the test surface. When fluorescent magnetic particle material is used, the inspection shall be accomplished in a darkened area using black light (ultraviolet light). The black light source shall be a 100-watt or greater clear mercury floodlight (Westinghouse type B44-4 JM Lifeguard, or equal) fitted with a heat-resisting black light filter (Kopp no. 41 or Corning no. 5874, or equal) which filters out visible light and transmits ultraviolet light. A minimum of 5 minutes shall be allowed for the lamp to obtain full brilliance before beginning the inspection. The light-to-test-surface distance shall not exceed 15 inches for 100-watt source. The maximum distance for greater light source shall be prorated. The light bulb and the filter shall be free of dust and stain to assure adequate black light intensity.

4.3.1.2 Procedure. The magnetic particle inspection procedure shall have the proven ability to detect a 1/16-inch long by 0.006-inch wide by 0.02-inch deep notch (maximum dimensions) oriented 90 degrees to the magnetic flux. The notch shall be cut in a 3/8-inch low alloy steel plate and shall be filled flush

MIL-STD-271F(SH)
27 June 1986

with a nonconducting material, such as epoxy, to prevent mechanical holding of the indicating medium. The procedure shall include as a minimum the following information:

- (a) Material, shapes, and sizes to be tested.
- (b) Type and direction of magnetization to be used.
- (c) Equipment to be used for magnetization.
- (d) Surface preparation (finishing and cleaning).
- (e) Whether wet or dry method is to be used.
- (f) Type of magnetic particles to be used.
- (g) Whether continuous or residual method is used.
- (h) Magnetizing current (amperage, ac or dc).
- (i) Demagnetization.
- (j) Test for concentration of particle suspension (if any).
- (k) Sketches or a chart showing the typical inspection grid to be used.
- (l) Method of particle application and removal.
- (m) Applicable acceptance standards.

4.3.1.3 Surface preparation. Prior to inspection, surfaces shall be dry and free from any contamination which might interfere with the proper formation or interpretation of the magnetic particle patterns. With the exception of undercuts which are within specification allowances, the contour of welds shall be blended smoothly and gradually into the base metal. Surface irregularities shall be removed to the extent that they will not interfere with interpretation of the test results. The final magnetic particle inspection shall be performed in the final surface and heat-treated conditions as specified in 1.4.

4.3.1.3.1 Cleaning and masking. Grease or other matter which might interfere with the proper distribution and concentration, or with the intensity, character, or definition of magnetic particle indications shall be removed from the surface undergoing the tests. All openings shall be plugged to prevent accumulation of magnetic particles or other matter where it cannot be completely or readily removed by washing and air blasting.

4.3.1.3.2 Cleaning solution. Chlorinated solvents shall not be used on parts containing crevices.

4.3.1.4 Direction of magnetization. To insure detection of discontinuities having axes in any direction, at least two separate inspections shall be carried out on each area. The second inspection shall be with the magnetic field at right angles to that used in the first inspection. A different means of magnetizing may be employed for the second inspection of the area.

MIL-STD-271F(SH)

27 June 1986

4.3.1.5 Demagnetizing apparatus. Demagnetizing equipment shall consist of units, such as the open coil or box-type demagnetizer, with sufficient capacity to demagnetize the item.

4.3.1.5.1 Demagnetization. All items shall be demagnetized at the following stages to obtain satisfactory indications of discontinuities:

- (a) Prior to testing, if the material contains strong remnant fields from some previous operation and inspection.
- (b) After all magnetic particle testing is completed, if the remnant field interferes with the removal of the magnetic particles in cleaning the part or when specified in the appropriate equipment specification.

4.3.1.6 Equipment accuracy. Magnetic particle testing equipment shall be checked for accuracy at the time of purchase and at an interval not to exceed 6 months and whenever electrical maintenance is performed which may affect the equipment accuracy.

4.3.1.6.1 Dc portable prod and stationary magnetic particle equipment. To check the equipment ammeter, a suitable calibrated ammeter shall be connected in series with suitable shunts and the current through the electrodes measured. The amperage measured by the dc ammeter during the test shall simultaneously be compared to that indicated on the meter of the magnetic particle unit. The equipment meter shall agree within 5 percent of the current measured by the calibration meter.

4.3.1.6.2 Yoke equipment. The yoke equipment shall be checked for adequacy of magnetization strength. With the pole spacing set to the maximum, the lifting power, as applied to carbon or alloy steel, shall be 10 pounds minimum for ac electromagnetic yokes and 40 pounds minimum for permanent magnet yokes. Yokes with pole spacing greater than 8 inches are to be specifically approved for use by NAVSEA.

4.3.1.7 Magnetizing current. The magnetizing current shall be based on formulas provided herein or the current shall be determined by means of a segmented magnetic field indicator as shown on figure 6. Where examination is being performed on complex shapes, the field indicator shall be used to determine the adequacy of the field. The current or technique shall be modified as necessary to ensure that an adequate field is present on all surfaces to be examined. Suitable magnetic flux is indicated when the indicator is laid, copper side up, on the work piece in the area of interest and after application of the magnetic particles (and removal of excess particles for the dry powder method), and the lines at 45 and 90 degrees to the applied field are clearly visible.

4.3.2 Wet method.

4.3.2.1 General requirements. Finely divided magnetic particles shall be suspended in a liquid vehicle as the indicating material. The magnetic particles may be either fluorescent or nonfluorescent.

MIL-STD-271F(SH)
27 June 1986

4.3.2.1.1 Equipment. The magnetizing apparatus shall be capable of inducing, in the item under test, a magnetic flux of suitable intensity in the desired direction by either the circular or the longitudinal method.

4.3.2.2 Vehicles. The liquid used as a vehicle for both nonfluorescent and fluorescent magnetic particles shall comply with the following:

- (a) Petroleum distillate conforming to the following specifications shall be used:
 - (1) P-D-680 - Dry cleaning solvent (type 2 Stoddard solvent).
 - (2) ASTM D 3699 - Kerosene.
 - (3) SAE AMS 3161 - Kerosene, deodorized.
- (b) Tap water with suitable rust inhibitors and wetting and antifoaming agents may be substituted for the petroleum distillate.
- (c) Liquid vehicles used with fluorescent magnetic particles shall be nonfluorescent.

4.3.2.2.1 Cleaning and drying. Prior to the application of the suspension, all oil, grease, or other foreign matter shall be thoroughly removed from the surface to be tested. Following the removal of the suspension, the piece shall be thoroughly cleaned and dried.

4.3.2.3 Magnetic particles. Magnetic particles shall be nontoxic and shall exhibit good visual contrast. Fluorescent magnetic particles shall be readily visible when exposed to a filtered black light, as specified in 4.3.1.1.1.

4.3.2.4 Suspensions. Suspensions shall consist of the liquid vehicle and either fluorescent or nonfluorescent magnetic particles, but both types of particles shall not be used simultaneously. Viscosity of the suspension shall be limited to a maximum of 5.0 centistokes at ambient temperature. Concentration of the suspensions shall be maintained in accordance with 4.3.2.6.1.

4.3.2.5 Procedure. Suspensions shall be applied to items being tested by spraying or immersion to ensure thorough coverage of areas requiring tests.

4.3.2.5.1 Continuous methods. For the continuous method, the magnetizing circuit shall be energized just before diverting the stream of suspension from the item being tested, or just before removing the item from the suspension if testing is by immersion, and allowed to remain energized for at least 1/5 second, with the result that the magnetizing current is applied while the item is still covered with a film of suspension sufficient to give satisfactory indications.

4.3.2.5.2 Residual method. For the residual method, the item shall be magnetized by the application of current for at least 1/5 second, after which the magnetizing current shall be turned off and the suspension shall be applied either by spraying or by immersion in the suspension. For application by

MIL-STD-271F(SH)

27 June 1986

immersion, the item shall be removed carefully from the suspension to avoid washing off the indications. The residual method shall be used only for inspection of small parts, such as nuts, bolts, pins, gears, and others.

4.3.2.5.3 Circular magnetization; central conductor (indirect method). A central conductor shall be used in all cases where testing of internal surfaces of enclosed or cylindrically shaped items of small diameter is required. A central conductor may also be used for circular magnetization of other shapes, when applicable. The conductors shall be as near the inside diameter as practicable. Items shall be spaced to avoid contact, and if warranted by the quantity of work involved, suitable fixtures shall be used for proper orientation.

4.3.2.5.4 Circular magnetization; item as conductor (direct method). Where it is necessary to pass current through the item, care shall be exercised to prevent arcing or overheating at the electrode contact areas. Contact areas shall be clean, items shall be mounted horizontally between contact plates, and suitable head pressure exerted to ensure uniform magnetization. When practicable, large and heavy items shall be mounted in suitable fixtures to ensure proper orientation. When protective coatings would interfere with the flow of current, they shall be removed at the area of contact. After tests, the coating shall be repaired.

4.3.2.5.5 Circular magnetization; magnetizing current. The magnetizing current required for an item depends on its shape, configuration, and size. The optimum current setting shall be determined by means of a segmented magnetic field indicator tested in accordance with 4.3.1.7.

4.3.2.5.6 Longitudinal magnetization. When a solenoid is used to magnetize items, the solenoid shall be no larger than necessary to accommodate the item, and items shall be orientated within the solenoid to ensure adequate field strength.

4.3.2.5.7 Longitudinal magnetizing current. For longitudinal magnetization using a solenoid, the magnetizing force in ampere-turns should be determined in the following manner for general applications:

The ampere-turns used shall be $10,000/L/D$ to $30,000/L/D$, where L is the length and D is the diameter of the part. The L/D ratio for parts being magnetized shall be two or more. Coils are usually effective in magnetizing the part for about 8 to 12 inches from each end of the coil. If longer parts are to be inspected, several magnetizing shots will be required. Either the inside or the outside diameter may be used depending on which surface is being inspected. When both surfaces are to be inspected, the larger diameter shall be used. Magnetic field indicator shall be used as specified in 4.3.2.5.5.

4.3.2.6 Maintenance of suspension. The suspension in use shall be tested for content of magnetic particles at intervals depending upon frequency of use, discoloration and contamination, but in any event at a minimum of once each day. When the suspension becomes discolored by oil or contaminated with lint or other foreign material to the extent that proper distribution and

MIL-STD-271F(SH)

27 June 1986

concentration of the suspension or the intensity, character, or definition of the deposit of the magnetic particles are interfered with, the container shall be drained, thoroughly cleaned and refilled with clean suspension.

4.3.2.6.1 Concentration of suspension test. The test method shall be determined by the organization. If for any reason the Government Inspector doubts the adequacy of the method employed, he shall request the concentration to be checked by the following tests:

- (a) Fill a standard 100-milliliter (mL) graduate to the 100 mL mark with the suspension directly from the hose or other device used for pouring it over the piece in making a test, or from an immersion tank after the suspension has been thoroughly agitated. Let the suspension stand for 30 minutes to precipitate, or until the solid matter is apparently all down.
- (b) Decant the clean liquid as far as practicable without loss of magnetic substance.
- (c) Refill graduate above magnetic substance with type II Stoddard Solvent in accordance with P-D-680 or acetone for water-base suspension. Shake well and let stand for 30 minutes to precipitate a second time.
- (d) Read the height or volume of the precipitate in the graduate. The readings shall be as follows:
 - (1) The nonfluorescent magnetic particles: 1.2 to 2.4 mL.
 - (2) The fluorescent magnetic particles: 0.1 to 0.7 mL.
- (e) If the concentration was checked daily, steps (b) and (c) may be omitted.

4.3.3 Dry powder method.

4.3.3.1 General requirements for magnetic particles. The magnetic particles used for obtaining patterns of discontinuities shall be of a nontoxic, finely divided ferromagnetic material of high permeability and low retentivity, free from deleterious rust, grease, paint, dirt, or other material which might interfere with their proper functioning. Particles shall be of such size, shape and color as to provide adequate sensitivity and contrast for the intended use. Upon receipt, each lot of magnetic particles shall be tested for their ability to detect in the vertical position known linear defects 1/16 inch and longer in a weldment. Where lot identification is not available, the magnetic particles of each container must be subjected to the above test.

4.3.3.2 Applying particles. Dry magnetic particles shall be applied in such a manner that a light, uniform, dust-like coating settles upon the surface under test. Automatic powder applicators shall not be used for the application of dry magnetic particles unless specifically approved by NAVSEA. Only hand powder applicators are permitted.

MIL-STD-271F(SH)
27 June 1986

4.3.3.2.1 Removal of excess particles. Excess dry particles shall be removed by means of a dry air current of sufficient force to remove excess particles without removing relevant indications formed during powder application. Removal of excess particles shall comply with the procedure of 4.3.1.2 and must be accomplished while the magnetic field is applied to the item under test.

4.3.3.3 Magnetizing procedures.

4.3.3.3.1 Circular magnetization. The method of magnetization and the magnetizing current shall be as specified in 4.3.2.5.3, 4.3.2.5.4 and 4.3.2.5.5, as applicable.

4.3.3.3.2 Longitudinal magnetization. The method of magnetization and the magnetizing current shall be as specified in 4.3.2.5.6 and 4.3.2.5.7.

4.3.3.3.3 Yoke magnetization. Magnetic yokes may be used for magnetization, provided the sensitivity to detect surface defects is demonstrated as specified in 4.3.1.2.

4.3.3.3.4 Magnetizing current (prod methods). For prods, the magnetizing current, direct or rectified, shall be computed on the basis of 100 to 125 amperes per inch of prod spacing. Prod distances of less than 2 inches are not recommended, however, prod spacing of less than 2 inches may be used, provided prior concurrence of the Government Inspector is obtained.

4.3.3.4 Magnetizing technique (yoke and prod).

4.3.3.4.1 Weld inspection. The magnetic field shall be induced with the prods or yoke legs placed diagonally, 30 to 45 degrees, to the longitudinal axis at the weld, and repeating this test along the opposite diagonal of the weld. During inspection of adjacent areas of the weld, the prods or yoke legs shall overlap the previous placement by a minimum of 1 inch. As an alternative, the magnetic fields may be induced by placing the prods or yoke legs parallel to the longitudinal axis of the weld, overlapping the previous placement by a minimum of 1 inch. Subsequent to the longitudinal placement, the weld shall be inspected by placing the prods or yoke legs perpendicular to the weld. When this alternative is used, the area to be inspected shall be limited to one-fourth of the prod or yoke leg spacing on either side of a line joining the prods or yoke legs.

4.3.3.4.2 Base metal. Base metal shall be inspected using the prod and yoke leg placement requirements of 4.3.3.4.1 to establish a grid pattern that assures two-directional coverage of inspection areas.

4.3.3.4.3 Continuous method. Inspection shall be carried out by the continuous method; that is, the magnetizing current shall remain on during the period the magnetic particles are being applied and while excess particles are being removed.

MIL-STD-271F(SH)
27 June 1986

4.4 Non-relevant indications. All indications revealed by magnetic particle inspection do not necessarily represent defects since non-relevant indications are sometimes encountered. If any indications are believed to be non-relevant, the following methods may be used to prove non-relevancy:

- (a) At least 10 percent of each type of indication shall be explored by removing the surface roughness believed to have caused the type of indication to determine if defects are present. The absence of indications under reinspection by magnetic particle inspection after removal of the surface roughness shall be considered to prove that the indications were non-relevant with respect to actual defects. If reinspection reveals any indications, these and all of the original indications shall be considered relevant.
- (b) A liquid penetrant inspection after grinding to remove the surface roughness believed to have caused the indication.
- (c) Other methods approved by the authorized NAVSEA representative.

4.5 Final cleaning. After completion of inspection all magnetic particles shall be removed from all parts. All temporary plugs shall be removed from holes and cavities.

4.6 Arc strikes. Arc strikes shall be ground out and reinspected, using the prod or yoke method, or visually inspected at 5X minimum magnification.

5. LIQUID PENETRANT TESTING

5.1 Intended use. The liquid penetrant test method is used for detecting the presence of surface discontinuities in ferrous and nonferrous materials. Drawings specifying liquid penetrant testing shall employ nondestructive test symbols in accordance with AWS A2.4.

5.2 Definitions.

5.2.1 Developers. The developers specified herein may be wet or dry material which draws or absorbs penetrants from a surface crack or defect to such an extent that evidence of the defect is visible under natural, white, or black light, as applicable.

5.2.2 Black light. Black light as specified herein applies to the invisible radiant energy in that portion of the spectrum just beyond the blue of the visible spectrum and which has a wave length of between 320 and 400 nanometers.

5.2.3 Emulsifier. An emulsifier as defined herein is an agent which will, when added or applied to an oil-like penetrant material, make the penetrant removable from surfaces by water rinsing.

5.2.4 Self-emulsifiable. A self-emulsifiable material is an oil-like material containing an emulsifying agent which makes it water washable as applied.

MIL-STD-271F(SH)
27 June 1986

5.2.5 Post-emulsifiable. A post-emulsifiable material is an oil-like material which, after application to a surface, can be made water washable by application of an emulsifier.

5.2.6 Penetrant remover. A penetrant remover as specified herein is a solvent-type liquid which is used to clean dye penetrants from the surface of a material.

5.2.7 Fluorescence. Fluorescence is a term used to describe the effects produced by certain chemical products which exhibit the property of emitting visible light by the activation of black light. These materials absorb the invisible energy, alter its wave length, and emit the energy in the form of light which is visible to the eye.

5.3 Inspection methods. The inspection method designation shall correspond to and use the material group numbers specified in 5.3.1.

5.3.1 Type of liquid penetrant material. Unless otherwise specified, liquid penetrant material shall meet the requirements of MIL-I-25135, and the total halogens and sulphur of each material shall not exceed 1 percent by weight of the residue. Each group of material shall be furnished complete by one manufacturer:

- Group I - Consisting of a solvent-removable visible dye penetrant with associated penetrant remover (solvent) and a non-aqueous wet developer.
- Group II - Consisting of postemulsifiable visible dye penetrant with associated emulsifier and a dry, wet, or nonaqueous wet developer.
- Group III - Consisting of a water-washable visible dye penetrant with associated dry, wet, or nonaqueous wet developer.
- Group IV - Consisting of a water-washable fluorescent penetrant and associated dry, wet, or nonaqueous wet developer.
- Group V - Consisting of a postemulsifiable fluorescent penetrant and associated emulsifier and dry, wet, or nonaqueous wet developer.
- Group VI - Consisting of a high intensity postemulsifiable fluorescent penetrant and associated emulsifier and dry, wet, and nonaqueous wet developer.
- Group VII - Consisting of a solvent-removable fluorescent penetrant with associated penetrant remover (solvent) and dry, wet, or nonaqueous wet developer.

MIL-STD-271F(SH)

27 June 1986

5.4 General requirements. Penetrant testing shall be performed in accordance with a written procedure. Group I penetrant material shall be used for all welds, except casting inspections and weld repairs to casting where an appropriate group listed in 5.3.1 may be used. The use of other than group I penetrant materials for welds not stated herein shall require approval by NAVSEA authorized representative.

5.4.1 Equipment requirements. The test equipment operated by qualified nondestructive test personnel shall be capable of consistently obtaining results of specified level of sensitivity.

5.4.2 Procedure. The liquid penetrant inspection procedures shall contain, as a minimum, the following information:

- (a) Brand name and specific group type, number and letter designation, or both, of penetrant, emulsifier, penetrant remover, and developer.
- (b) Details of method of precleaning and drying, including cleaning materials used and time allowed for drying.
- (c) Details of method of penetrant application, the length of time that the penetrant remains on the surface, and the temperature of the surface and penetrant during penetration.
- (d) Details of method of removing excess penetrant from the surface, and of drying the surface before applying the developer.
- (e) Details of the method of applying the developer and the length of developing time before inspection.
- (f) Method of post-test cleaning.
- (g) The applicable acceptance standards.

5.4.2.1 Change of penetrant materials. When the brand or type of penetrant, penetrant remover (solvent) or developer differs from that specified in the procedure, a new procedure shall be prepared which includes all the information required by 5.4.2.

5.5 Surface preparation.

5.5.1 General requirements. Surfaces to be inspected shall be free from scale, slag and adhering or imbedded sand or other extraneous materials. With the exception of undercuts which are within specification allowances, the contour of welds shall blend smoothly and gradually into the base metal. Weld surface irregularities shall be removed to the extent that they will not interfere with interpretation of the test results. The final liquid penetrant inspection shall be performed in the final surface condition as specified in 1.4 herein. Peening, shot, sand, grit, and vapor blasting shall not be performed on surfaces which are to be liquid penetrant inspected unless specifically approved by the authorized representative of NAVSEA.

5.5.2 Finished surfaces. Surfaces, for which a specific finish is required, shall be given such surface finish prior to the final liquid penetrant inspection prescribed by the applicable specifications. Inspection at intermediate stages of fabrication shall be as specified in the applicable specification.

MIL-STD-271F(SH)
27 June 1986

5.6 Test procedures.

5.6.1 Pre-test cleanliness. All surfaces being tested shall be thoroughly cleaned of extraneous material. If a nonvolatile liquid is used for cleaning, the surface shall be heated or dried with hot air to assure complete removal of the cleaner. As a final cleaning operation each surface shall be dipped, sprayed, wiped, or brushed with trichloroethylene, trichloroethane, perchloroethylene, acetone, denatured ethanol, isopropanol or 1, 1, 2, trichloro - 1, 2, 2, trifluoroethane (Freon TF, PCA grade, or equal) and thoroughly dried by removing the excess with a clean dry cloth or absorbent paper, and allowing the remainder to evaporate for a minimum of 5 minutes. Prior to liquid penetrant inspection, the surface to be tested and any adjacent area within 1 inch of the surface to be tested shall be dry and free of dirt, grease, lint, scale and salts, coatings, or other extraneous matter that would obscure surface openings or otherwise interfere with the test. In addition, all liquid penetrant tests shall be performed prior to ultrasonic inspections on the same surfaces to avoid interference between the penetrant dye and any residual couplant.

5.6.2 Temperature. Maximum penetration into extremely small openings requires that the penetrant and the test surface be maintained at the temperature recommended by the penetrant manufacturer but shall in no case be less than 50 degrees Fahrenheit ($^{\circ}$ F). The temperature of the penetrant and the test surface shall not exceed 100° F, except that for group I materials the temperature of the test surface may be a maximum of 150° F or the maximum temperature recommended by the manufacturer, whichever is less. Due to the flammable nature of liquid penetrant inspection materials, the use of an open flame for heating purposes shall be prohibited. Special conditions requiring deviation from the above requirement require approval by an authorized representative of NAVSEA.

5.6.3 Penetration time. The surface to be tested shall be thoroughly and uniformly coated with penetrant by flooding, brushing, immersion, or spraying. Unless otherwise recommended by the manufacturer, and approved by the authorized representative of NAVSEA, or when specified in the applicable material or equipment specification, the penetrant dwelling time for the various penetrant groups shall be as follows:

<u>Penetrant (group)</u>	<u>Minimum penetration time (minutes)</u>	<u>Maximum penetration time (minutes)</u>
I	15	20
II	15	20
III	25	30
IV	25	30
V	15	20
VI	10	15
VII	15	20

5.6.3.1 Application of emulsifier (groups II, V and VI). The emulsifier shall be applied in accordance with the manufacturer's instruction and in accordance with 5.4.2.

MIL-STD-271F(SH)

27 June 1986

5.6.4 Removal of penetrant.

5.6.4.1 Groups I and VII materials. The excess penetrant shall be removed from all surfaces as follows:

- (a) As much excess penetrant as possible shall be removed by first wiping the surface thoroughly with a clean dry cloth or absorbent paper.
- (b) The remaining excess penetrant shall be removed by wiping the surface with a clean cloth or absorbent paper dampened with a penetrant remover specified by the penetrant material manufacturer.

5.6.4.2 Flushing of the surface with any liquid following application of the penetrant and prior to developing shall be prohibited.

5.6.4.3 Groups II, V and VI. After a specified penetration time (see 5.6.3), the emulsifier shall be applied. The dwelling time of the emulsifier shall be in accordance with the manufacturer's instruction and in accordance with 5.4.2. Subsequent to completion of emulsification, the emulsifier shall be removed from the surface of the part by employing a warm water spray not exceeding 120°F and 40 pounds per square inch (psi) pressure. After washing, items to be inspected using groups V and VI shall be checked under a black light to ensure complete cleaning. Alternatively, the penetrant shall be removed by use of the cleaner specified by the manufacturer of the penetrant.

5.6.4.4 Groups III and IV only. The penetrant shall be removed from surfaces by swabbing with a clean lint-free cloth saturated with clear water or by spraying with water not exceeding 120°F and 40 psig. After washing, items to be inspected using group IV shall be checked under a black light to ensure complete cleaning.

5.6.5 Surface drying.

5.6.5.1 Groups I and VII. The drying of test surfaces after the removal of the excess penetrant shall be accomplished only by normal evaporation, or by blotting with absorbent paper or clean, lint-free cloth. Forced air circulation in excess of normal ventilation in the inspection area shall not be used. Unless otherwise specified by the penetrant manufacturer, the time for surface drying after removal of excess penetrant and prior to application of the developer shall be limited to a maximum of 10 minutes.

5.6.5.2 Groups II through VI. The drying of test surfaces shall be accomplished by using circulating air, blotting with paper towels or clean lint-free cloth or by normal evaporation. It is important that during the drying operation, no contaminating material be introduced onto the surface which may cause misinterpretation during the inspection operation. The time for surface drying operation shall be in accordance with the manufacturer's instructions.

MIL-STD-271F(SH)
27 June 19865.6.6 Application of developer.

5.6.6.1 Nonaqueous wet developer. A nonaqueous wet developer specified by the penetrant manufacturer shall be used. Immediately prior to application the developing liquid shall be kept agitated in order to prevent settling of solid particles dispersed in the liquid. The developer shall be uniformly applied in a thin coating to the test surface by spraying. If the geometry of the item being inspected precludes the use of a spray, a brush or similar applicator shall be used provided it results in a uniform, thin coating of developer. Pools of wet developer in cavities on the inspection surface shall not be permitted since these pools will dry to an excessively heavy coating in such areas resulting in the masking of indications. Inspection shall be made a minimum of 7 minutes and no later than 30 minutes after the developer has dried. For groups I and VII penetrant material, only the nonaqueous wet developer shall be used.

5.6.6.2 Dry developer. Dry developing powder shall be applied only on dry surfaces so that matting will be prevented. The powder shall be thinly but uniformly applied to provide a dusty appearance immediately after drying of the test surface. Time for development of indications after the developing powder has been applied shall be controlled and kept to a minimum.

5.6.6.3 Aqueous wet developer. This type of developer shall be uniformly applied to surfaces by dipping, spraying or brushing, as soon as possible after removal of all excess penetrant but in no case to exceed 10 minutes. When using liquid-type developers, it is necessary that they be continually agitated in order to prevent settling of solid particles dispersed in the liquid. Concentrations of wet developer in cavities on the inspection surface shall not be permitted since these pools will dry to an excessively heavy coating in such areas resulting in the masking of indications.

5.6.7 Lighting in test area. When using the dye penetrant inspection, groups I, II, and III, the test area shall be adequately illuminated for proper evaluation of indications revealed on the test surface. When the fluorescent penetrant is used, the inspection shall be accomplished in a darkened area using a black light. The black light source shall be a 100-watt or greater clear mercury floodlight (Westinghouse type H44-4 JM Lifeguard, or equal) fitted with a heat-resisting black light filter (Kopp no. 41 or Corning no. 5874, or equal) which filters out visible light and transmits ultraviolet light. A minimum of 5 minutes shall be allowed for the lamp to obtain full brilliance before beginning the inspection. The light-to-test-surface distance shall not exceed 15 inches for 100-watt source. The maximum distance for greater light source shall be prorated. The light bulb and the filter shall be free of dust and stain to assure adequate black light intensity.

5.6.8 Final cleaning. When the inspection is concluded, the penetrant materials shall be removed as soon as possible by means of water or solvents in accordance with 5.6.1 and with applicable cleaning specifications.

5.6.9 Safety precautions. Penetrant inspection materials shall be used in accordance with all applicable safety regulations.

MIL-STD-271F(SH)
27 June 1986

5.7 Test results.

5.7.1 All indications in weld craters shall be considered relevant and shall be evaluated in accordance with the applicable acceptance standards. For other indications which are believed to be nonrelevant, such as those which may occur on casting surfaces, 10 percent of each type of indication shall be explored by removing the surface condition believed to have caused the indications and retested. Confirmation of nonrelevancy also may be made by other methods when approved by the Government Inspector. The location of nonrelevant indications and the method of confirmation shall be recorded in the inspection report.

6. ULTRASONIC TESTING

6.1 Definitions. The following definitions are applicable to ultrasonic testing.

6.1.1 Acoustically similar material. The same type of material as that to be inspected or another material which has been experimentally proven to have an acoustical velocity within plus or minus 3 percent for thickness testing, and for amplitude comparison test the back reflection amplitude from equal thicknesses shall be within plus or minus 10 percent of each other as measured on the CRT. This test shall be conducted on samples having equal contour and surface finish for both the sound entrant and reflective surfaces.

6.1.2 Amplitude. When referring to an indication on the cathode ray tube, amplitude is the vertical height of the indication measured from the lowest to the highest point on the indication.

6.1.3 Amplitude rejection level (ARL). The horizontal level on the cathode ray tube which is established as either a percentage of full scale height or as a decibel (dB) level based on the peak amplitude of the signal received from the applicable reflective surface in the calibration standard.

6.1.4 Angle beam testing. A testing technique in which the transducer is at an angle other than perpendicular (90 degrees) to the test surface and the ultrasonic waves enter the material (via a wedge or other medium), in a direction angular to the test surface.

6.1.5 A-scan. A method of data presentation on a cathode ray tube utilizing a horizontal base line which indicates elapsed time when reading from left to right. A vertical deflection in the base line indicates reflected signal amplitude.

6.1.6 As-welded condition. The condition of weld metal, welded joints, and weldments after welding and removal of slag, spatter, and so forth, prior to any thermal or mechanical treatment.

6.1.7 Attenuation. Loss of ultrasonic intensity as the beam passes through the material.

6.1.8 Back reflection. Indication of the echo from the far boundary of the material under test.

MIL-STD-271F(SH)
27 June 1986

6.1.9 Calibration. Adjustment of the ultrasonic system to give desired indication height and position from known reflecting standards as required for the inspection being performed.

6.1.10 Calibration standard. See reference calibration standard.

6.1.11 Cathode ray tube. An electron tube in which a controlled beam of electrons from the cathode is used to reproduce an image on a fluorescent screen at the end of the tube.

6.1.12 Class of weld. Weld classes I, II and III are used to differentiate between critical and less critical welds and relate to acceptance criteria. Weld classes are defined by applicable fabrication documents.

6.1.13 Compressional wave. Those waves in which the particle motion of the atoms of the material is essentially in the same direction as the wave propagation.

6.1.14 Continuous scan. A scanning practice in which each pass with the transducer overlaps the previous pass by at least 25 percent.

6.1.15 Couplant. Any material, usually a liquid or semi-liquid, used between the face of the search unit and the test surface to permit or improve transmission of the ultrasonic wave from the search unit to the material under test.

6.1.16 Delay control. A means of positioning the desired pattern to the left or right on the cathode ray tube.

6.1.17 Discontinuity. Anything within a material which will cause a detectable interruption or change in an ultrasonic beam.

6.1.18 Disregard level (DRL). The horizontal level on the cathode ray tube established at a given level below the amplitude rejection level (ARL).

6.1.19 Frequency. The number of cycles the wave completes per unit of time.

6.1.20 Full screen height. The highest point on the cathode ray tube used for evaluation and recording purposes, designated as 100 percent or scale 10.

6.1.21 Gain control. A control which varies the amplification of the ultrasonic system. Also considered the sensitivity control.

6.1.22 IIW block. A standard test block designed by the International Institute of Welding (IIW) to check the operation of the ultrasonic system and search units or transducers.

6.1.23 Indication. A signal caused by a beam being reflected from a discontinuity or a boundary surface.

MIL-STD-271F(SH)
27 June 1986

6.1.24 Initial pulse. The signal on the left side of the viewing screen caused by the reflections from the test surface or transducer face.

6.1.25 Interface. The boundary between two materials which are in contact with each other.

6.1.26 Linearity. The characteristic of an instrument that is revealed by a linear change in reflected signal amplitude and horizontal displacement. The vertical linearity is determined by plotting the change in ratios of signal amplitude from two reflecting areas. The horizontal linearity is determined by plotting the distance the signal is displaced along the sweep against the change in material thickness.

6.1.27 Longitudinal wave. Another name for compressional wave.

6.1.28 Megahertz (MHz). One million hertz.

6.1.29 Peak indication. The maximum height or amplitude of an indication received from any one reflective surface using a constant gain setting.

6.1.30 Reference calibration standard. A sample of material acoustically similar to the material to be tested containing known reflectors with which the ultrasonic system is calibrated and acceptance/rejection levels established.

6.1.31 Reflection. The phenomenon by which a wave strikes a boundary and changes the direction of its propagation.

6.1.32 Resolution. The ability to clearly distinguish signals obtained from two reflective surfaces with a minimum difference in depth. Near surface resolution is the ability to clearly distinguish a signal from a reflector at a minimum distance under the near surface without interference from the initial pulse signal. Far surface resolution is the ability to clearly distinguish signals from reflectors displaced a minimum distance from the back surface when the sound beam is normal to that back surface.

6.1.33 Scanning. The moving of the search unit (or units) along a test surface to transmit the sound beam into the material being tested.

6.1.34 Search unit. The transducer affixed to a suitable device to obtain the desired wave propagation.

6.1.35 Sensitivity. The measure of the ability of the ultrasonic equipment to detect discontinuities.

6.1.36 Shear waves. When the direction of propagation of a wave is perpendicular to the direction of vibration of particles of the medium in which the wave travels, the wave is said to be a transverse or shear wave.

MIL-STD-271F(SH)
27 June 1986

6.1.37 Skip distance angle beam testing. In parts having parallel surfaces, the distance between the point of sound beam entry and the first point where the bottom-reflected beam returns to the entrant surface (see figure 7).

6.1.38 Test surface. Any boundary of material under test.

6.1.39 Transducer. The element which transmits sound vibrations into the material to be tested and receives reflected vibrations. The active element of the transducer is defined as the effective transmitting area.

6.1.40 Ultrasonic test sensitivity. The sensitivity at which the test will be conducted.

6.1.41 Ultrasonically sound material. A material having no discontinuities which cause discernible ultrasonic indications at the required test sensitivity level.

6.2 Procedure and test methods. The test methods which follow apply to the inspection of forgings, castings, rolled or extruded shapes, bar stock, plate, weldments, pipe and tubing, bonded materials, and metal sheet. As described herein, the procedures are largely manual. Automation, however, may be applied to these methods when it serves to minimize operator induced variables. Testing can be performed more easily and reproducibly on parts which have the simple geometries associated with early stages of fabrication. Inspection methods other than those specified in this section may be used, provided approval is based on procedural qualification obtained from the authorized NAVSEA representative. All tests shall be performed in accordance with a written inspection procedure approved in accordance with 1.7.

6.2.1 Test method selection. The method or methods required for inspection of a component is specified by the equipment or material specification or other fabrication document. Selection of a test method or combination of methods shall be based upon the configuration and the orientation of expected discontinuities in the items to be inspected.

6.2.2 Surface finish. Surfaces of metals shall be clean and free of dirt, loose scale, loose paint, or other loose foreign matter. Surface finishes of material to be inspected by contact method shall have a finish of 250 ra or smoother. For materials to be inspected by the immersion method, the surface finish of the calibration standard shall not be any smoother than that of the material to be tested. Surface waviness shall not interfere with test.

6.2.3 Testing speed. Rotation or speed of the part or search unit shall be controlled as closely as possible and shall be consistent with operator readout capability. In any case, the test speed shall not exceed the maximum speed at which the calibration standard can be scanned to produce a clearly resolved indication.

6.2.4 Couplant. A couplant shall be used which causes acoustic coupling between the transducer and the part being inspected. This couplant shall not be injurious to the material. Glycerin or glycerin mixed with water or

MIL-STD-271F(SH)
27 June 1986

alcohol are some materials which may be used as a couplant. The couplant shall be removed from the part at the completion of the inspection.

6.2.5 Test symbols. Drawings specifying ultrasonic inspection shall employ symbols in accordance with AWS A2.4.

6.2.6 Calibration. Prior to any inspection, the equipment shall be calibrated, using the proper calibration standard, and shall be rechecked at least once per 8-hour shift, and at the completion of testing. If a recheck indicates recalibration is required, all items tested since the last instrument check shall be reinspected. During testing, any realignment of the search unit or any change in search unit, instrument settings or scanning speed from that used for calibration shall require recalibration.

6.3 Equipment. Ultrasonic equipment shall consist of the following:

- (a) Ultrasonic instrument. Electronic instrument capable of producing, receiving and displaying high frequency electrical pulses at the required frequencies and energy levels. The instrument shall have a demonstrable capability to meet the calibration requirements for specific tests.
- (b) Search units. Search units shall be capable of transforming electrical impulses to mechanical sound energy at specific frequencies. With the suitable couplant, it shall be capable of transmitting the sound into the material and receiving the returning sound energy, or both.
- (c) Master transducer (compressional wave only). The master transducer shall be one of a set of two similar transducers set apart to be used for equipment qualification only. These transducers shall be 1/2 inch in diameter and 2.25 MHz.
- (d) Calibration standards. To provide a basis for flaw evaluation in ultrasonic testing, calibration test standards shall be used for basic calibration of test equipment and to establish acceptance or rejection levels.

6.4 General requirements.

6.4.1 Equipment requirements.

6.4.1.1 Basic instrument qualification - pulse echo.

- (a) The vertical linearity shall be checked by positioning the master transducer over the depth resolution notch in an IIW block or equal, so that the signal from the notch is at a height of three scale divisions (30 percent screen height), and the signal from one of the back surfaces is at a height of six scale divisions (60 percent screen height). A curve is then plotted showing the deviations from the above established 2:1 ratio that occurs as the amplitude of the signal from the notch is raised in increments of one scale division until the back reflection signal reaches full scale, and then is lowered in increments of one scale division (10 percent) until the notch signal reaches one scale division. At each increment, the ratio

MIL-STD-271F(SH)
27 June 1986

of the two signals is determined. The ratios are plotted on the graph at the position corresponding to the larger signal. Between the limits of 20 and 80 percent (2 and 8 scale divisions) of the screen height, the ratio shall be within 10 percent of 2:1. Instrument settings used during inspection shall not cause variation outside the 10 percent limits established above. (See figure 8 for a typical plot.)

- (b) When the time-distance relationship (horizontal linearity) displayed on the sweep of the cathode ray tube is a function of the test, the distance shall be determined by plotting signal displacement against known thickness in the range of 1 to 5 inches in 1-inch increments, the limits to be within plus or minus 3 percent. As an alternative, multiple back reflections from 1-inch block may be used.
- (c) The resolution shall be determined using the IIW steel block or equivalent with the master transducer. The equipment must resolve to the base line an 80 percent of full scale indication from the large (50-millimeter (mm)) hole 5 mm from the surface for near field resolution and the depth resolution notch for far field.

6.4.1.2 Shear wave transducer. Shear wave search units shall have a refracted angle in the range as specified in 6.5.4.3.2, within the limits of plus or minus 3 degrees of the designated angle at $68 \pm 10^{\circ}\text{F}$, as determined by the steel IIW block.

6.4.1.3 Basic instrument qualification - thickness gauge. At least two readings shall be made on each of a series of test blocks representative of the ranges of the instrument. Variations between the true thickness and the determined thickness shall be reduced to plus or minus percentage variation and this value plotted on a graph. Plus or minus variation from zero shall be plotted on the horizontal axis and the percent of the readings plotted on the vertical axis. A sufficient number of readings shall be made to accurately determine the thickness testing characteristics of the instruments. At least 95 percent of the total number of readings shall be within plus or minus 3 percent of the true value. For thicknesses of 0.150 inch or less, the readings shall be within plus or minus 0.005 inch of the true value.

6.4.1.4 Frequency of basic instrument qualification. The basic instrument qualification shall be performed and documented at intervals not to exceed 6 months or whenever maintenance is performed which affects the equipment function.

6.4.2 Inspection procedure. The ultrasonic inspection procedures shall contain, as a minimum, the following information:

- (a) Materials, shapes, or sizes to be tested or to be exempt from test.
- (b) Automatic defect alarm and recording equipment or both.
- (c) Special search units, wedges, shoes, or saddles.
- (d) Rotating, revolving feeding mechanisms.
- (e) Stage of manufacture when test will be made.
- (f) The surface from which the test shall be performed.
- (g) Surface finish.
- (h) Couplant.

MIL-STD-271F(SH)
27 June 1986

- (i) Description of the calibration method.
- (j) Scanning.
- (k) Mode of transmission.
- (l) Transducer size and frequency.
- (m) Acceptance standards.
- (n) Method of recording inspection results.

6.4.2.1 Procedure requalification. Changes to the ultrasonic inspection procedure within the scope of this section that affects the technical aspect of the procedure shall be approved by the ultrasonic test examiner prior to use. Changes outside at the parameters of this section or a change to a material that is not acoustically similar to that for which the procedure has been qualified shall require requalification of the procedure.

6.4.3 Discontinuity evaluation. If discontinuities are detected, the search unit shall be directed to maximize the signal amplitude from the discontinuity for evaluation.

6.4.4 Records. Records of ultrasonic inspection shall contain the following:

- (a) Description and unique identification.
- (b) Approved procedure identification.
- (c) Instrument manufacturer and model number.
- (d) Transducer size and type.
- (e) Search beam angle.
- (f) Test frequency.
- (g) Couplant.
- (h) Calibration standard number.
- (i) Acceptance standard used.
- (j) Date of inspection.
- (k) Signature of inspectors.

6.5 Test methods.

6.5.1 Forgings, wrought and extruded material. Tests of forgings, wrought bars, and extruded material shall be made at the same frequency used to calibrate the equipment. Controls shall be set during the calibration and shall not be changed during the production test. Determination of the size of discontinuities shall be made by comparison to the reference standard holes as specified in 6.5.1.1.

6.5.1.1 Test calibration, longitudinal wave. Unless otherwise specified, when testing forgings, including ring, rectangular rounded, multisided disc or pancake and all wrought bars using longitudinal waves, the calibration criteria of table VI shall apply.

MIL-STD-271F(SH)

27 June 1986

TABLE VI. Calibration hole size for longitudinal test.

Section thickness (inches)	Diameter of flat bottomed hole (FBH) (inches \pm 0.005)
Less than 1/2	1/32
1/2 to less than 1-1/2	1/16
1-1/2 to less than 2-1/2	3/32
2-1/2 to less than 3-1/2	1/8
3-1/2 to less than 4-1/2	5/32
4-1/2 to less than 5-1/2	3/16
5-1/2 to less than 6-1/2	7/32
6-1/2 and over	1/4

NOTES:

- All flat bottomed holes shall have bottoms parallel to the entrant or to the tangent of the entrant surface.
- The calibration standard shall be wide enough to permit sound transmission to the flat bottomed hole without side effects.
- The calibration standard material shall be acoustically similar and within 1/8 inch of the material thickness to be inspected and shall be ultrasonically sound. Ultrasonically sound material is defined as a material which is capable of exhibiting an 80 percent of full scale reflected signal amplitude from a specified FBH with no more than 20 percent of full scale extraneous signal amplitude. The surface finish and curvature shall be similar to the test surface.
- Flat bottomed holes for test standards shall be drilled to a depth of one-half the thickness or 1 inch whichever is less.
- The test frequency shall be the same as the calibration frequency.
- The couplant used for calibration shall be the same as that used for inspection.
- The use of distance amplitude correction curves is permitted for calibration.

6.5.1.2 Ring forgings.

6.5.1.2.1 Test calibration, shear wave. The calibration standard for the ring forgings with wall thicknesses that do not exceed 20 percent of the outside diameter shall have two notches cut axially, one on the inside surface and one on the outside surface of the test standard. They shall be located so that their sides are smooth and parallel to the axis of the forging and that readily distinguishable individual ultrasonic indications are obtained from each notch. Shear wave inspection shall be performed at 3 percent notch sensitivity. The notch shall be U- or V-shaped. The dimensions of the notch shall comply with table VII. Scan until the notch indication from the inside diameter appears at the farthest position to the left at which it is readable. Move the search unit away from the inside diameter notch until the indication

MIL-STD-271F(SH)

27 June 1986

from this notch reappears along the horizontal trace. Mark these two positions on the face of the scope. Scan until the notch indication from the outside diameter is produced at maximum amplitude between these two marks. The amplitude of this notch indication shall be marked on the face of the scope. When the test instrument incorporates distance-amplitude controls it is recommended that they be used where possible to equalize these indication amplitudes to form an ARL at a minimum of 50 percent of full screen height. If this is not possible, or if the instrument is not equipped with a distance amplitude connection circuit, a distance amplitude curve shall be constructed on the screen with the lowest point at a minimum of 20 percent full screen height. Ring forgings with wall thicknesses exceeding 20 percent of their diameters cannot be inspected by circumferential shear wave scan where both inside and outside notches must be monitored. Alternate ultrasonic inspection methods for these forgings shall be specified.

6.5.1.2.2 Test. The ring shall be continuously scanned and circumferentially scanned for the entire outer surface. Unless otherwise specified, the test shall be performed in two opposing directions. Size and locations of indications in excess of that received from the calibration notches in accordance with table VII shall be marked on the material.

6.5.1.2.3 Longitudinal wave tests of ring forgings.

6.5.1.2.3.1 Test calibration, longitudinal wave. Sound transmission into the ring shall be confirmed by observing the first back reflection obtained from the ring. Sensitivity of the instrument shall be adjusted until the indication from the flat bottomed hole in the standard is 80 percent of full screen height. The calibration standard shall conform to the requirements of table VI.

6.5.1.2.3.2 Testing - longitudinal wave. The ring shall be tested using the continuous method by directing the sound beam radially and axially. The axial beam direction scan shall be performed when not restricted by configuration or geometry of the material under test. The first back reflection shall be positioned on the screen to verify sound transmission and any defect indication shall appear between the initial pulse and the first back reflection.

6.5.1.3 Rectangular forgings.

6.5.1.3.1 Test calibration, longitudinal wave. Sound transmission into the forging shall be confirmed by observing the first back reflection obtained from the forging. Sensitivity of the instrument shall be adjusted until the indication from the specified reference calibration standard is at 80 percent of full screen height. The reference standard shall conform to the requirements of table VI.

6.5.1.3.2 Testing - longitudinal wave. Rectangular forgings shall be tested using the continuous scanning method on surfaces such that three major planes shall be covered. Scanning with the sound beam directed axially shall be performed when not restricted by configuration or geometry of the material

MIL-STD-271F(SH)
27 June 1986

under test. The first back reflection shall be positioned on the screen to verify sound transmission. Suspect areas disclosed under these conditions shall be further evaluated from the side opposite to that which was originally inspected to determine maximum flaw signal amplitude.

6.5.1.4 Round and multisided forged or wrought bars including disc or pancake forgings.

6.5.1.4.1 Test calibration, longitudinal wave. Sound transmission into the forging shall be confirmed by observing the first back reflection obtained from the forging. Sensitivity of the instrument shall be adjusted until the indication from the specified reference calibration standard is at 80 percent of full screen height. The reference standard shall conform to the requirements of table VI.

6.5.1.4.2 Testing - longitudinal wave. Each bar or forging shall be tested using the continuous scanning method on surfaces such that all major planes shall be covered. For bars, scanning with the sound beam directed axially shall be performed only when specified.

6.5.2 Plate and sheet.

6.5.2.1 Surface preparation. The test surface shall be free of all loose dirt, rust or any foreign substance which may interfere with the test. The surfaces may have one coat of primer.

6.5.2.2 Shear wave testing technique. Shear wave testing shall be performed only when specified.

6.5.2.2.1 Test calibration. When specified, shear wave inspection shall be performed to a 3-percent notch sensitivity. Using any suitable means, a calibration reference notch shall be formed in the test surface of the plate being inspected or acoustically similar test piece. An angle beam search unit, capable of transmitting a shear wave at an angle of 45 degrees in the material being tested, and a frequency of 2.25 MHz shall be used. The instrument shall be adjusted to display signals from the reference notch specified in table VII at one-half and full skip distance. The amplitude of the reflected signal from the reference standard at the half skip distance shall be adjusted to 80 percent of full screen height. The amplitude of the signal from the reference standard at full skip distance shall be marked on the viewing screen. A line shall be drawn from the peak signal at half skip to the peak signal at full skip distance. Flaws in the plate or sheet being inspected shall be evaluated to the test sensitivity as established by this line.

TABLE VII. Calibration reference notch dimensions of square and "U" bottom notch.

Depth (percent of thickness)	3 ± 1/2 percent or 0.005 inch, whichever is greater
Width Length	2 X depth (approximate) 1 inch (minimum)

MIL-STD-271F(SH)
27 June 1986

6.5.2.2.2 Grid test procedure. When grid shear wave testing is specified, it shall be performed by scanning one major surface in two directions, causing the sound beam to travel parallel to and perpendicular to the longitudinal axis or direction of rolling of the plate. In the case of square cross rolled plate, either direction is acceptable. The search unit shall be moved in parallel paths on a 6-inch grid. If an indication is obtained which has an amplitude of 50 percent or greater of that established in 6.5.2.2.1, the adjacent area shall be scanned by the continuous scanning method sufficiently to establish the size and location of the discontinuity.

6.5.2.2.3 Continuous scanning procedure. When continuous shear wave testing is specified, it shall be performed by continuously scanning one major surface completely in two directions, causing the sound beam to travel parallel to, and perpendicular to the longitudinal axis or direction of rolling of the plate. The search unit shall be moved in parallel paths to accomplish continuous scanning until the entire dimension is traversed.

6.5.2.3 Longitudinal wave testing technique.

6.5.2.3.1 Testing calibration. A compressional wave search unit having a dimension of 1 inch square or 1 inch in diameter, operating at a frequency of 2.25 MHz, unless otherwise specified, shall be placed on a defect free area. (A defect free area is defined as an area which has been evaluated at the highest ultrasonic sensitivity applicable for the test.) The ultrasonic instrument gain shall be adjusted to display the first back reflection at full screen height. This sensitivity level shall be used to evaluate the plate.

6.5.2.3.2 Test procedures.

6.5.2.3.2.1 Continuous method. Continuous scan method testing shall be performed by scanning one major surface 100 percent, only when specified.

6.5.2.3.2.2 Static method. Testing shall be performed by interpreting the cathode ray tube presentation when the search unit has been statically placed at each intersecting grid line on one major surface of the plate. The grid pattern shall consist of a maximum of 2-foot squares for all plate and sheet over 1/2 inch to and including 2-1/2 inches thick. For plates over 2-1/2 inches, the grid pattern shall be 8 inches square. Grid patterns as specified herein shall prevail unless modified by the contract, order, or material specification. If an indication is obtained, the adjacent area shall be scanned in a 1-foot radius circle by the continuous method to determine the extent and magnitude of the defective condition.

6.5.3 Pipes and tubes - seamless.

6.5.3.1 Pipe and tube shall be tested, using the continuous scan method for radial type discontinuities extending longitudinally. Transverse discontinuity tests and additional circular tests shall be performed only when and as specified. When specifically invoked, 6.4.1.1 shall apply.

MIL-STD-271F(SH)
27 June 1986

6.5.3.2 Test calibration, radial defects detection. Select a length of pipe or tube of acoustically similar material and the same nominal size to be tested for use as a calibration standard. For calibration in testing for radial defects, two notches shall be cut; one on the inside surface and one on the outside surface as specified in 6.5.1.2.1. The notches shall be located approximately 1-1/2 inches from one end of sample. The notch shall be cut in such a manner that its sides are smooth, radial and extend parallel to each other and to the longitudinal axis of the pipe or tube. Magnitude of the indication for the notches shall be determined by directing sound waves circumferentially toward the notches with the search unit located at a suitable radial arc displacement using at least one full skip technique where possible (see figure 7). If the indications from the inside and outside notches are unequal, small adjustments shall be made in the angle of incidence to equalize them. If the indications cannot be equalized, the smaller indication shall be used as the basis for evaluation.

6.5.3.3 Test, radial defects. When testing pipe and tubes, they shall be set with their longitudinal axis in a horizontal position on motorized rollers or other suitable mounting which shall permit rotation of the pipe or tube about their longitudinal axis. Rotation shall be controlled at a fairly uniform speed, depending upon the repetition rates established for the test unit being employed. In any case, the peripheral speed shall not exceed the maximum speed at which the calibration standard is rotated for clear definite resolution of the notch being presented. When the immersion method is used, the test conditions shall duplicate calibration conditions especially in regard to keeping the tube bore filled or dry during test. In general, excluding the immersion fluid from the tube bore improves the reproducibility of test results. Each pipe shall be continuously scanned.

6.5.4 Ultrasonic inspection of weldments.

6.5.4.1 Scope. This section contains the minimum requirements for the inspection of structural butt, corner, and tee welds to insure joint integrity as required by specifications, contracts and acquisition documents.

6.5.4.2 General requirements.

6.5.4.2.1 Scanning. Scanning shall be as required to insure complete coverage of the inspection zone (see figure 7A). If full coverage is not possible due to configuration, accessibility or base metal discontinuity, actual coverage shall be recorded and the reason noted for incomplete coverage.

6.5.4.2.2 Surface finish. The scanning surfaces shall be 250 ra or smoother and free of any foreign substance which would interfere with the test. Welds may be inspected in the as-welded condition, provided the required test sensitivity and inspection coverage can be maintained. The weld reinforcement shall be ground flush to provide a flat surface when ultrasonic inspection is to be accomplished by scanning on the weld surface. The test surface may have one coat of primer.

6.5.4.2.3 Limitations. The requirements of this section were developed for the inspection of welded joints in ship hull structures. These joints consist of butt, corner and tee design in HY-80, HTS and acoustically similar

MIL-STD-271F(SH)

27 June 1986

materials ranging from 1/2 to 4 inches in thickness. The use of these requirements on other thicknesses and joint designs shall be reviewed for applicability of test sensitivity and technique by the examiner and demonstrated to the NAVSEA authorized representative.

6.5.4.2.4 Reference calibration standards.

6.5.4.2.4.1 Butt welds, corner welds and tee welds for discontinuities into the through member. The calibration standards shall be acoustically similar material as that to be inspected, and shall be ultrasonically sound. They shall be capable of providing constant reference sensitivity levels for all angles of search and inspection depth. The standard reflecting surface shall be a 3/64-inch diameter hole drilled through a 1-1/4 inch wide block. The surface of the test block shall be approximately 125 ra as compared to surface finish standards. See figure 9 for a typical reference calibration standard.

6.5.4.2.4.2 Detection of lack of penetration in full penetration tee welds. The calibration standard shall be the through member upon which the inspection is being performed.

6.5.4.3 Specific requirements for butt and corner welds.

6.5.4.3.1 Instrument. The instrument shall have circuitry to provide a continuously increasing amplification with respect to time. This circuitry compensates for the signal losses with depth as a result of sound beam divergence and its attenuation in material.

6.5.4.3.2 Search units. The maximum dimension of the transducer active element shall not exceed 1 inch. The nominal frequency should not be less than 2.0 MHz. The transducers used for shear wave tests shall be affixed to a suitable wedge designed to induce shear waves in the material under test at the desired angles. The inspection angle shall be selected using the plate thickness as the primary consideration as follows:

- (a) For plate thicknesses 1/2 inch to, but not including, 1-1/2 inches: a 60- to 70-degree shear wave.
- (b) For plate thicknesses 1-1/2 inches to, but not including, 2-1/2 inches: a 45- to 60-degree shear wave.
- (c) For plate thicknesses 2-1/2 inches and over, a 45-degree shear wave.

Search units with beam angles other than those listed may be used to complement the required search units for the detection and evaluation of discontinuities.

6.5.4.3.3 Calibration. The instrument range and delay controls shall be adjusted to display signals from the reference calibration holes on the viewing screen for the range of depths to be inspected. The attenuation-correction controls shall be adjusted to compensate for the signal losses due to depth.

6.5.4.3.3.1 Class I welds. When a decibel control is used, the instrument gain shall be adjusted to peak all signals from the reference calibration holes within the range of the test at a minimum of 20 percent of full screen height. The corresponding depth and location of the peaked signals from the reference

MIL-STD-271F(SH)
27 June 1986

calibration standard shall be marked along the base line of the viewing screen. The gain shall be increased by 12 dB. At this gain setting, the line established by the original signal height on the viewing screen is the DRL and the ARL is 12 dB above this line. For evaluation of indications above the DRL, the dB control is used (see figure 10). When a dB control is not used, the instrument gain shall be adjusted to peak all signals within the range of test at a minimum of 80 percent of full screen. The corresponding depth and location of the peaked signals from the reference calibration standard shall be marked along the base line of the viewing screen. The screen shall be divided by two horizontal lines at 20 percent (the DRL) and 80 percent (the ARL) of full screen height (see figure 11).

6.5.4.3.3.2 Class II and III welds. When a dB control is used; the instrument gain shall be adjusted to peak all signals from the reference calibration holes within the range of test at a minimum of 40 percent of full screen height. The corresponding depth and location of the peaked signals from the reference calibration standard shall be marked along the base line of the viewing screen. The gain shall be increased 6 dB. At this gain setting, the 40 percent line on the viewing screen is the DRL, and the ARL is 6 dB above this line. For evaluation of indications above the DRL, the dB control is used. When a decibel control is not used, the instrument gain shall be adjusted to peak all signals within the range of test at a minimum of 80 percent of full screen. The corresponding depth and location of the peaked signals from the reference calibration standard shall be marked along the base line of the viewing screen. The screen shall be divided by two horizontal lines at 40 percent (the DRL) and 80 percent (the ARL) of full screen height.

6.5.4.3.4 Procedure. The entire weld volume (excluding the weld reinforcement) and heat affected zone (up to 1/2 inch of base material measured from each weld toe) is the inspection zone and shall be scanned with shear waves by directing the sound beam toward, or across, and along the weld axis.

6.5.4.3.4.1 Longitudinal discontinuities. To detect longitudinal discontinuities, the axis of the sound beam shall traverse the inspection zone in two opposing directions (see figure 12). For welds where two-directional scanning is impracticable, a minimum of one-direction scanning may be approved by the examiner on a case basis. The search unit shall be oscillated to the left and right with an included angle of approximately 30 degrees in a radial motion while continuously scanning perpendicularly toward and away from the weld.

6.5.4.3.4.2 Transverse discontinuities. To detect transverse discontinuities for welds not ground flush, the sound unit shall be placed on the base metal surface at the weld edge. The sound beam shall be directed by angling the search unit approximately 15 degrees toward the weld from the longitudinal weld axis. Scanning shall be performed by moving the search unit along the weld edge from both sides on one surface and from two opposing directions. To detect transverse discontinuities for welds ground flush, the search unit shall be oscillated to the left and right, with an included angle of approximately 30 degrees in a radial motion, while scanning along the top of the weld from two opposing directions. If the weld width exceeds the width of the transducer, continuous scanning shall be performed.

MIL-STD-271F(SH)
27 June 1986

6.5.4.3.4.3 Compressional wave. If compressional wave testing is employed, calibration shall be accomplished in accordance with 6.5.4.3.3. The weld shall be scanned continuously.

6.5.4.3.4.4 Discontinuity evaluation. If discontinuities are detected, the sound beam shall be directed to maximize the signal amplitude. To determine the length of a discontinuity, the search unit shall be moved parallel to the discontinuity axis in both directions from the position of maximum signal amplitude. One half the amplitude from a point where the discontinuity signal drops rapidly to the baseline shall be defined as the extremity of the discontinuity. At this point, the scanning surface is marked at the position indicated by the center of the transducer. This shall be repeated to determine the other extremity. When the half amplitude signal from the end of the discontinuity as determined by this method is below the DRL, the end of the discontinuity shall be defined where the signal crosses 20 percent of full screen height. The length of the discontinuity shall be defined as the distance between these two marks. The maximum signal amplitude, length, depth, and position within the inspection zone shall be determined and reported for discontinuities yielding a signal amplitude equal to or exceeding the DRL.

6.5.4.4 Specific requirements for welds of tee joints.

6.5.4.4.1 Detection of lack of penetration in full penetration tee welds. This section specifies the procedures to be used for the ultrasonic inspection of tee welds for discontinuities in the root area. The depth of the inspection zone shall be limited to through member plate thickness plus 1/4 inch minus 1/8 inch. The width of the inspection zone shall be limited to the thickness of the attachment member (see figure 13). The inspection shall employ the pulse-echo compressional wave testing technique.

6.5.4.4.1.1 Search units. The size of the transducer used for inspection shall be 3/4 inch diameter maximum; however, it shall not exceed the thickness of the attachment member. The inspection frequency shall be a minimum of 2.0 MHz.

6.5.4.4.1.2 Calibration. The instrument range and delay controls shall be adjusted to discriminate and indicate signals on the viewing screen from the inspection zone. The sweep line shall be marked indicating through member plate thickness minus 1/8 inch and plate thickness plus 1/4 inch. The instrument gain shall be adjusted to peak the first back reflection from the plate adjacent to the weld at least once each foot along the length of the weld as specified hereafter. When a dB control is used, the instrument shall be adjusted to peak the first back reflection at a minimum of 20 percent of full screen. The gain shall be increased 12 dB. At this setting, the 20-percent line on the screen is the DRL, and the ARL is 10 dB above this line (see figure 14). When a dB control is not used, the viewing screen shall be divided into three zones with horizontal lines at 20 percent (the DRL) and 65 percent (the ARL) of full screen height. The instrument gain control shall be adjusted so that the peak of the first back reflection coincides with the 80 percent line (see figures 14 and 15).

MIL-STD-271F(SH)
27 June 1986

6.5.4.4.1.3 Procedure. The width of the inspection zone shall be located and marked on the test surface determined by ultrasonic or mechanical means. The weld shall be continuously scanned within the width of the inspection zone (see figure 13). If a discontinuity is located, the equipment gain shall be recalibrated on the through member plate adjacent to the discontinuity. The search unit shall then be positioned to maximize the discontinuity signal. To determine the length of a discontinuity, the search unit shall be moved along the axis of the discontinuity in one direction from the position of maximum signal amplitude. When the amplitude drops below the DRL, the scanning surface shall be marked at the position indicated by the center of the search unit. This shall be one extremity of the discontinuity. The process shall be repeated to determine the other extremity. The length of the discontinuity shall be the distance between these two marks. The maximum signal amplitude and length of discontinuities within the inspection zone shall be determined and reported for discontinuities yielding a signal amplitude equal to or exceeding the DRL.

6.5.4.4.2 Detection of discontinuities into the through member. This section specifies the ultrasonic inspection procedure to be used for the detection of discontinuities extending into the through member of full and partial penetration tee welds.

6.5.4.4.2.1 Inspection zone. The depth of the inspection zone shall be from the through member surface into the through member 1/4 inch inclusive. The depth of the inspection zone shall be expanded to determine the maximum depth of discontinuities extending into the through member. The width of the inspection zone shall be limited to the thickness of the attachment member plus the fillet reinforcement (see figure 17). If the particular configuration to be inspected is not discussed in the standard, a method should be used which assures that complete coverage of the inspection zone will be obtained.

6.5.4.4.2.2 Search units. The diameter or length or width of the transducer shall not exceed 1 inch. The frequency shall not be less than 2.0 MHz. The transducers used for shear wave tests shall be affixed to suitable wedges designed to induce shear waves in the material under test at a specific angle from 45 to and including 60 degrees. Supplemental beam angles may be used for the detection and evaluation of discontinuities.

6.5.4.4.2.3 Calibration. The instrument range and delay controls shall be adjusted to discriminate and indicate signals on the viewing screen from the depth of the inspection zone. The instrument gain shall be adjusted to peak the signal from the calibration hole at a minimum of 20 percent of full screen height. The gain shall then be increased by 12 dB. At this setting, the line established by the original signal height on the viewing screen is the DRL and the ARL is 12 dB above this line. When a dB control is not used, the instrument gain shall be adjusted to peak the signal from the calibration hole that is not more than plus or minus 1/4 inch from the through member thickness to a minimum of 80 percent of full screen. The corresponding depth and location of the peaked signals from the reference calibration standard shall be marked along the base line of the viewing screen. The screen shall be divided by two horizontal lines at 20 percent (the DRL) and 80 percent (the ARL) of full screen height.

MIL-STD-271F(SH)

27 June 1986

6.5.4.4.2.4 Procedure. Shear wave scanning for discontinuities into the through member in any tee weld configuration shall be performed as shown on figure 16 whenever the surface opposite the attachment member is accessible. If the surface opposite the weld is not accessible and the side adjacent is accessible, the scanning shall be accomplished as shown on figure 17: however there shall be no attachments in the area where the reflection of the wave occurs. Coverage in each direction, as illustrated on figures 16 and 17, shall be from the nearest toe of the weld to beyond the center of the weld, thus avoiding the necessity of interpreting indications from the surface of the far fillet. The shear wave search unit shall be placed on the scanning surface and directed toward the particular inspection zone. The search unit shall be oscillated to the left and right with an included angle of approximately 30 degrees in a radial motion while scanning perpendicularly toward the inspection zone. The inspection zones are specified in 6.5.4.4.2.1. Continuous scanning shall be used. When any indication is noted from a discontinuity within the inspection zone, the sound beam shall be directed to maximize the indication. The maximum signal amplitude, length, depth, and position shall be determined and reported for discontinuities yielding a signal amplitude equal to, or exceeding, the DRL. The length of discontinuities shall be determined in accordance with 6.5.4.4.1.3. The recorded depth of a discontinuity shall be the minimum and maximum perpendicular distances of the discontinuity from the through member surface. This should be determined in the following manner:

- (a) Maximize the indication from the discontinuity.
- (b) For discontinuities extending to a surface, move the search unit toward the discontinuity and record the depth from the viewing screen at which the indication begins to drop rapidly toward the base line.
- (c) In addition, for discontinuities which do not extend to the surface, repeat the above and move the search unit away from the discontinuity to determine the other limit of depth at the point where the indication again begins to drop rapidly toward the base line.

6.5.4.5 Record of inspection results. The record data sheet for inspection results of welds shall contain as a minimum the following information (for suggested forms see figure 18):

- (a) Ship/item identification.
- (b) Location (frame, side of ship, and so forth).
- (c) Type of material.
- (d) Thickness of material.
- (e) Joint identification.
- (f) Type of weld joint (weld design).
- (g) Weld length inspected.
- (h) Operational procedure identification.
- (i) Equipment used for inspection (instrument and search unit).
- (j) Reference block identification.
- (k) Discontinuities that exceed the DRL.
- (l) Acceptance or rejection.

MIL-STD-271F(SH)
27 June 1986

- (m) Signature of inspection personnel.
- (n) Date.
- (o) If supplemental ultrasonic inspection techniques are used that contribute to the final inspection results, they shall be recorded.

6.6 Thickness measurements.

6.6.1 Scope. Variations in wall thickness may be measured by either pulse-echo instruments or resonant frequency instruments, which have been qualified in accordance with 6.4.1.2.

6.6.2 Calibration. The instrument shall be calibrated on a standard of the same basic material as that being inspected, using the minimum acceptable wall thickness or thicknesses above and below the minimum acceptable wall thickness (flat standards may be used for pipe and tubing 3/4-inch nominal diameter and over). The instrument shall be calibrated prior to each use or after any interruption in power supply.

6.6.3 Method. The number and location of ultrasonic thickness measurements taken shall be as specified in the applicable material specification, fabrication document or work authorization document. Measurements may be made manually or by automated equipment that meets the requirements of 6.4.1.1 and 6.4.1.3.

6.7 Bonding.

6.7.1 Scope. This subsection only describes the requirements for the ultrasonic inspection of the bond of weld deposited overlay cladding to base material. Specific requirements due to special shapes of manufacturing processes shall be as specified in the appropriate specifications.

6.7.1.1 Method. Inspection of the bond of weld deposited overlay cladding to base material shall be by the contact method. The transducer may be fitted with appropriate shoes, wedges, or saddles for testing on curved surfaces or at desired angles.

6.7.2 Transducers. Transducers shall not be larger than 1 inch square or 1-1/8 inch diameter, and shall operate within a range of 2.25 to 10.0 MHz.

6.7.3 Calibration of test equipment. Calibration of ultrasonic test equipment shall be performed on a reference calibration block to establish adequate sensitivity for testing. The calibration blocks shall meet the surface finish requirements of 6.2.2. The calibration blocks shall be prepared by weld deposited cladding, pads, or buttering onto a block of the same S-number base material as the production part (S-1 and S-3 are considered equivalent). The weld deposited metal used must be of the same A-number as that on the production part to be examined and may be deposited by any approved welding process. In addition, the following requirements in (a) through (f) shall be met (the S-numbers and A-numbers for base metal and weld metal are defined in MIL-STD-278):

MIL-STD-271F(SH)

27 June 1986

- (a) The microinch surface finish of the calibration block shall be equal to or greater than the production part to be inspected.
- (b) The calibration block base material shall be equal in thickness to the production part base material except that, for thicknesses exceeding 1 inch, the calibration block base material may be 1 inch or greater. For welding large flat, or essentially flat surfaces, a 6-inch square shall be the minimum acceptable calibration block.
- (c) The weld metal thickness of the calibration block shall be within plus or minus 25 percent of that on the production part.
- (d) The transducer contact area of the production part shall be equal to or greater than the transducer contact area on the calibration block.
- (e) For convex production surfaces, the calibration block shall be convex with a radius of curvature equal to or less than the production surface to be examined.
- (f) For concave production surfaces, the calibration block may be flat or concave with a radius of curvature equal to or greater than the production surface to be examined.
- (g) An area of the block approximately 2 inches square shall have the backing material removed, leaving only the cladding. An ultrasonic thickness measurement at 2.25 MHz shall be established in this area, representing unbond. The thickness pattern obtained in the area of integral cladding and base material shall represent good bond and the first clearly visible reflection from the opposite side of the block shall not exceed full screen amplitude. Calibration shall be obtained with the search unit moving across the surface at approximately the same speed as that to be used during the inspection.

6.7.4 Scanning. Scanning shall be performed manually or automatically by moving the search unit in a directed path or by moving the material in a directed path with the search unit stationary. Scanning shall be performed at a uniform rate of speed determined during calibration, so that any indication relative to the quality of the material shall be detected.

6.7.4.1 Continuous scanning. Unless otherwise specified in the appropriate specifications, the continuous scanning procedure shall be followed. All testing shall be performed with the search unit in contact with the clad surface. Sound transmission into the base material shall be confirmed by observing the composite thickness pattern as obtained from the good bond area of the calibration block. When the back reflection is lost due to nonparallel surfaces of the base materials, transmission shall be confirmed by the test specified in 6.7.4.3.

6.7.4.2 Intermittent scanning. Scanning shall be performed along special paths or on grid lines. The distance between paths or lines shall be as specified in the appropriate specification when the method is required.

MIL-STD-271F(SH)
27 June 1986

6.7.4.3 Calibration for ultrasonic testing of nonparallel surfaces. Test equipment shall be calibrated with the same calibration block as specified in 6.7.3. The thickness pattern shall be observed by scanning over the clad surface where the backing material has been removed, and the equipment shall be set to demonstrate a full screen back reflection. Using these settings, the operator shall scan over the composite thickness of the cladding and the backing material and note the normal back reflection from the good bond.

6.7.4.4 Continuous scanning of nonparallel surface. Unless otherwise specified in the applicable specifications, each pass across the test surface shall overlap 25 percent of the previous pass until the entire surface has been scanned. The equipment settings established in 6.7.4.3 calibration shall be used.

6.7.5 Marking. When an indication in excess of acceptance standards occurs, the material shall be appropriately marked.

6.7.6 Flaw plotting. Each defect shall be explored ultrasonically to determine its size. The edge of the defect shall be determined by moving the search unit toward the defect and noting the position of the leading edge of the transducer when the defect first appears. The length of the defect shall be determined by continuing to move the search unit across the defective area and noting the trailing edge of the transducer when the indication disappears. The distance between defects shall be determined by measuring the shortest distance between their edges regardless of indication amplitude at these points.

7. EDDY CURRENT TESTING

7.1 Scope. The inspection process covered is for the detection of surface cracks of ferromagnetic and nonferromagnetic materials. This method may only be used when authorized by the fabrication document, military specification, or other NAVSEA approval.

7.2 Definitions. The definitions specified in 7.2.1 through 7.2.3 are applicable to eddy current testing.

7.2.1 End (edge) effect. The masking of measurement data caused by distortion of the magnetic field when the probe is near any test specimen-to-air boundary, for example, ends, holes, and edges.

7.2.2 Lift-off effect. The effect to the test system output due to a change in magnetic coupling between a test specimen and the probe coil, whenever the distance of separation between them is varied.

7.2.3 Stand-off. The overall distance between the probe and the surface of the test specimen, that is, the protective tape thickness plus the thickness of the paint or rust.

MIL-STD-271F(SH)
27 June 19867.3 Eddy current inspection requirements.7.3.1 General requirements.

7.3.1.1 Method. The overall inspection process shall consist of applying the eddy current test (ET) technique to detect surface cracks in the item inspected. Any portions of the item which produce ET flow indications that equal or exceed the indication produced from the performance verification block shall be inspected by magnetic particle inspection for ferrous materials or liquid penetrant inspection for non-ferrous materials, acceptance/rejection shall be to the MT/PT criteria established by 1.3.

7.3.1.2 Surface finish. The surface for the eddy current test scanning does not require paint removal, but it shall be reasonably smooth and clean. It shall be free of any substance that might inhibit free movement of the probe along the scan path.

7.3.2 Procedure. Eddy current inspection procedures shall contain, as a minimum, the following information.

- (a) Material to be tested.
- (b) Summary of process used.
- (c) Equipment description.
- (d) Performance verification description.
- (e) Personnel qualifications.
- (f) Surface preparation.
- (g) Calibration/standardization technique.
- (h) Scanning technique.
- (i) Readout technique.
- (j) Evaluation criteria.
- (k) Recording and reporting requirements.

7.3.3 Records. Records of eddy current inspection shall contain the following:

- (a) Description and unique identification of item inspected.
- (b) Approved procedure identification.
- (c) Instrument manufacturer and model number.
- (d) Probe description.
- (e) Material type.
- (f) Acceptance standard used.
- (g) Date of inspection.
- (h) Signatures of inspectors.

7.4 Equipment requirements. The inspection equipment shall include the eddy current instrument, probe, probe coaxial cable and a performance verification reference block.

MIL-STD-271F(SH)
27 June 1986

7.4.1 Eddy current instrument. The instrumentation shall be capable of signal evaluation by both visual (meter readout) and audio sound pitch variations through connecting headphones or an X-Y storage display oscilloscope. The circuits shall provide a means for eliminating the total stand off (lift off) variable in the evaluation of test results. It shall be capable of detecting the notch in the performance verification block being used.

7.4.2 Performance verification reference block. A block of the same material type that is to be inspected. The block may be any convenient size provided that it does not present an edge-effect problem. The block shall contain a notch that is 0.015 inch deep by 0.250 inch long with a width of 0.010 inch (maximum dimensions). Blocks used for inspection of welds in the as-welded condition shall be of the same as-welded condition with the notches positioned on the weld.

7.5 On-site verification/standardization.

7.5.1 Verification. Prior to standardization, perform instrument verification test using performance verification block. This test shall produce a useable response for both audio and meter outputs or oscilloscope display, as applicable.

7.5.2 Standardization. The eddy current instrumentation shall be standardized (test calibration) on site at an experimentally determined defect-free area representative of the item to be inspected. Standardization shall be accomplished as follows:

- (a) Immediately prior to starting an inspection.
- (b) Whenever an inspection has been interrupted by the equipment being turned off or left unattended by the inspector.
- (c) Whenever the inspector has reason to suspect that conditions affecting the standardization have changed.
- (d) When in use, at least every 4 hours.

7.6 Test technique.

7.6.1 Toe of weld scan. With the probe oriented parallel to the weld longitudinal axis, scan along each toe of the weld. Ensure that the probe is maintained at a constant attitude to the toe of the weld, keeping the working edge of the probe in full contact. Monitor the weld condition by noting the varying response of the meter and the audio signal or oscilloscope display. Avoid rocking the probe or tilting it in a position other than as used in the standardization (see figure 19 for optimum positioning).

7.6.2 Weld scan. With the probe oriented parallel to one weld toe scan along the weld for the desired distance. Repeat this scanning process along the weld crown until opposite toe is reached. Each scan of the probe along the weld crown shall not be greater than 1/8 inch from the previous scan. The weld should also be scanned in the transverse direction.

MIL-STD-271F(SH)
27 June 1986

7.6.3 Inspection of surfaces other than welds. With the probe oriented at a consistent attitude to the work piece, keep the working face of the probe in full contact with the work piece at all times during scanning. To ensure detection of linear indications having axis in any direction, at least two separate scans shall be made in each area, the second scan shall be at right angles to that used in the first. Each scan of the probe shall not be greater than 1/8 inch from the previous scan.

8. VISUAL INSPECTION

8.1 Scope. The visual inspection process is to determine that all welds and adjacent base materials be inspected as required to comply with applicable procedures, drawings, and fabrication documents.

8.2 Reference standard. Visual inspection reference standards, as referred to in this section, refer to those devices that are used as an aid to visual inspection such as workmanship samples and sketches or photographs of welds or surfaces. Each activity shall be responsible for preparation of the reference standards specified in that activity's visual inspection procedure.

8.3 Procedure requirements. The visual inspection procedure shall contain, as a minimum, the following information:

- (a) Personnel qualification requirements.
- (b) Type of welds or surfaces to be inspected.
- (c) Measuring devices, visual aids, or reference or working standards.
- (d) List of inspection attributes (visual characteristics).
- (e) Lighting requirements.
- (f) Acceptance criteria and classification of defects.
- (g) Record requirements.

8.4 Inspection techniques. Visual inspection need not be performed employing magnification, unless otherwise specified in the applicable fabrication document. When a reference standard is required and magnification, such as a borescope or magnifying glass is employed, evaluation and acceptance shall be based upon comparison with a reference standard where both magnified and unmagnified appearance can be determined.

8.5 Dimensional inspection accuracy. Each activity shall insure that the dimensional inspection techniques, including measuring devices, visual aids, and reference or working standards, are capable of measuring the specified dimensions of the items under inspection, with the required precision.

8.6 Lighting. The inspection area shall be adequately illuminated for proper evaluation.

MIL-STD-271F(SH)
27 June 1986

9. NOTES


9.1 Subject term (key word) listing.

Circular magnetization
Compressional wave
Continuous scanning
Eddy current testing
Intermittent scanning
Liquid penetrant testing
Longitudinal magnetization
Longitudinal wave
Magnetic particle testing
Material thickness
Multiple film technique
Penetrameter
Radiographic inspection
Radiographic shooting sketch
Radioisotope radiography
Shear wave
Specimen thickness
Ultrasonic testing
Visual inspection
X-ray radiography
Yoke magnetization

9.2 Changes from previous issue. Asterisks are not used in this revision to identify changes with respect to the previous issue due to the extensiveness of the changes.


Preparing activity:
Navy - SH
(Project NDTI-N048)

MIL-STD-271F(SH)
27 June 1986

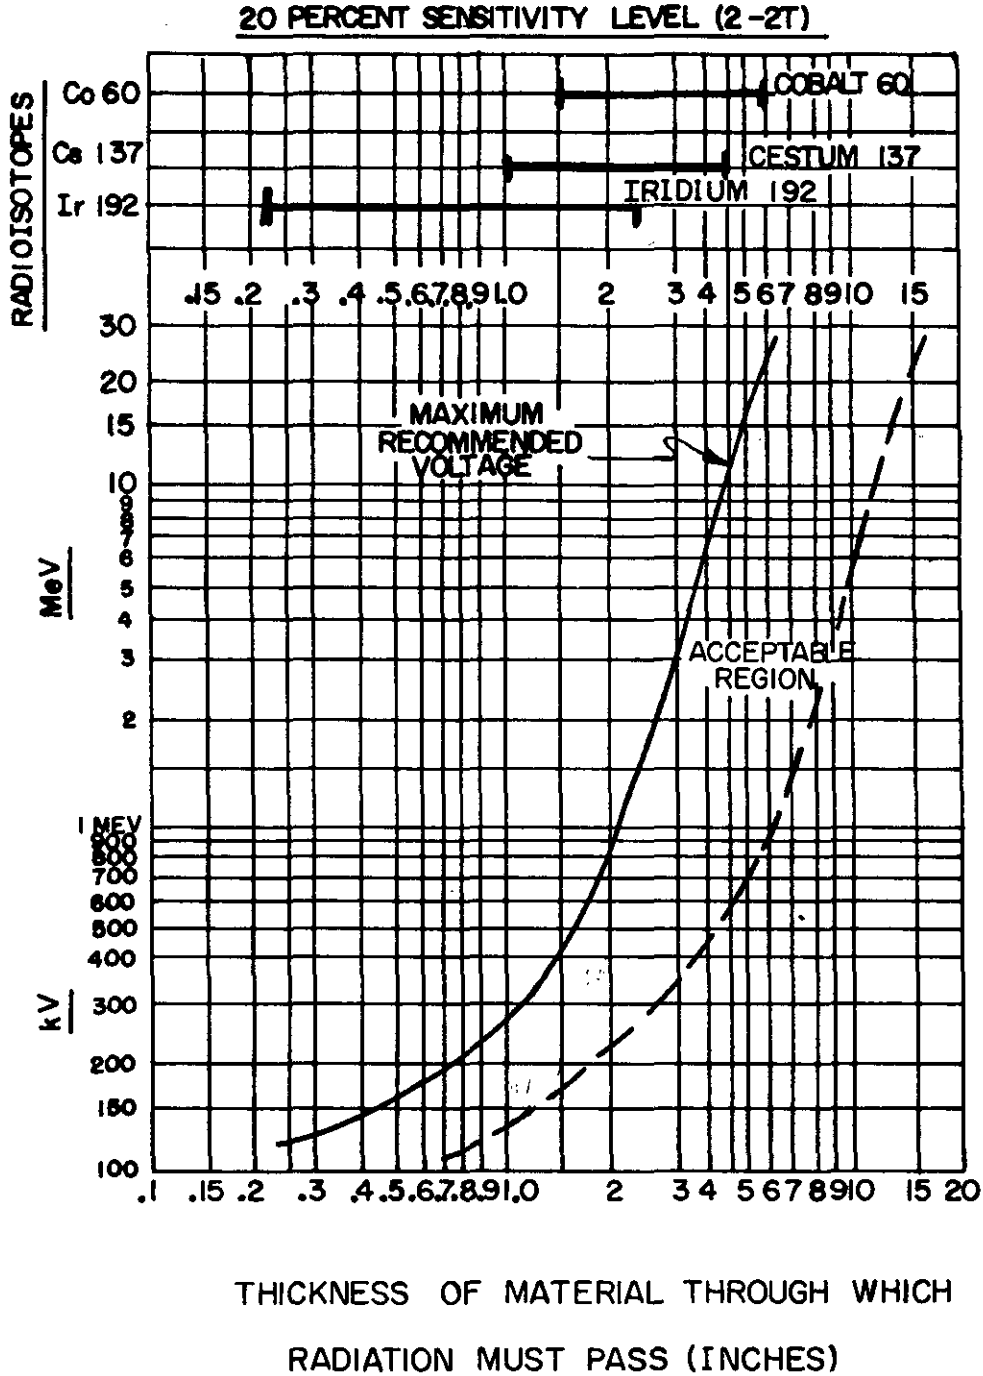

SH 13202656


FIGURE 1. Recommended X-ray voltage settings and radioisotope sources to be used with various steel and similar alloys.

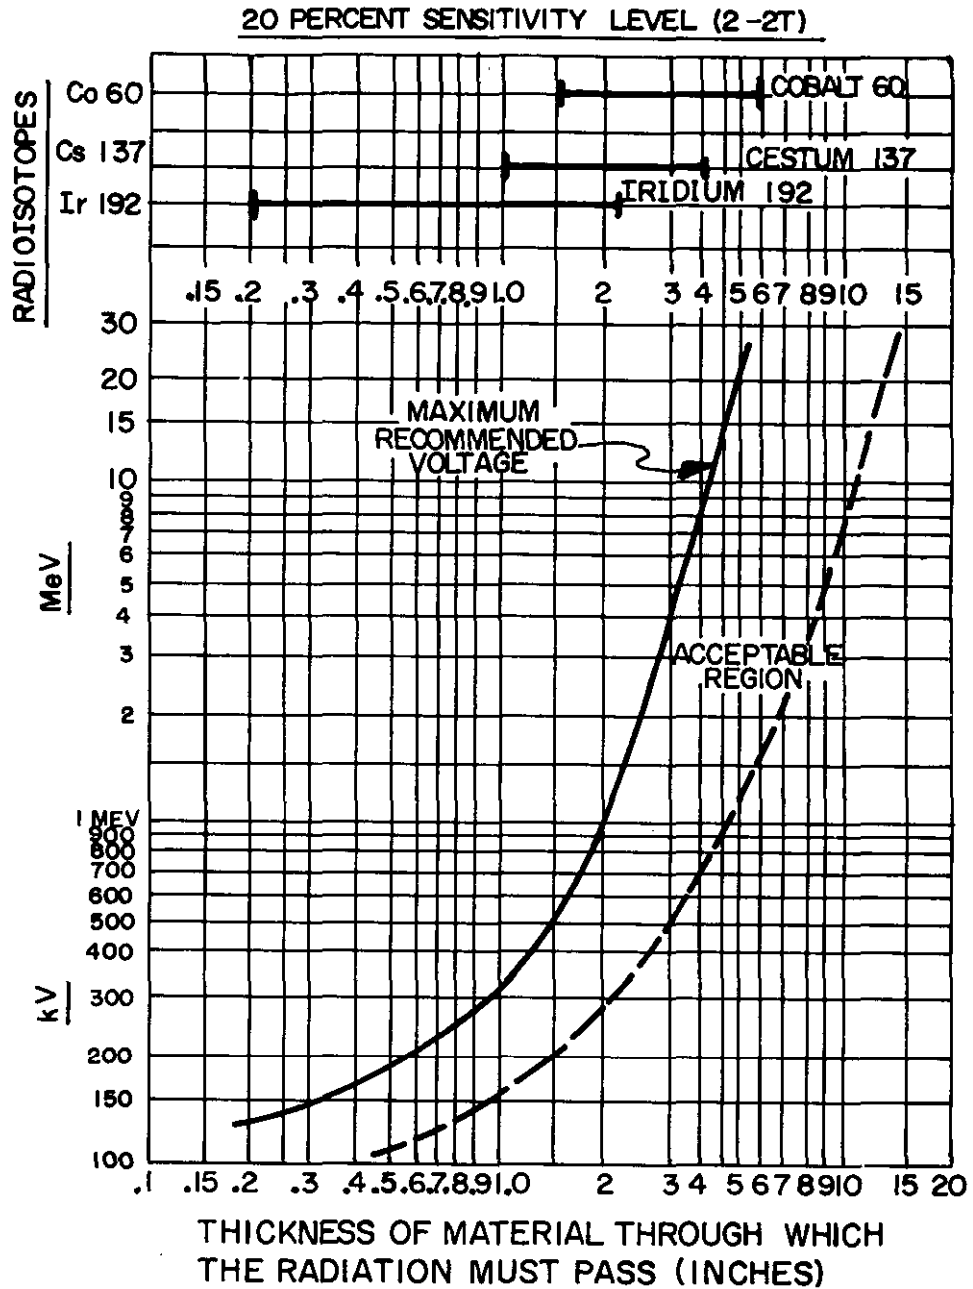

SH 13202657

FIGURE 2. Recommended X-ray voltage settings and radioisotope sources to be used with various copper-base and similar alloys.

MIL-STD-271F(SH)
27 June 1986

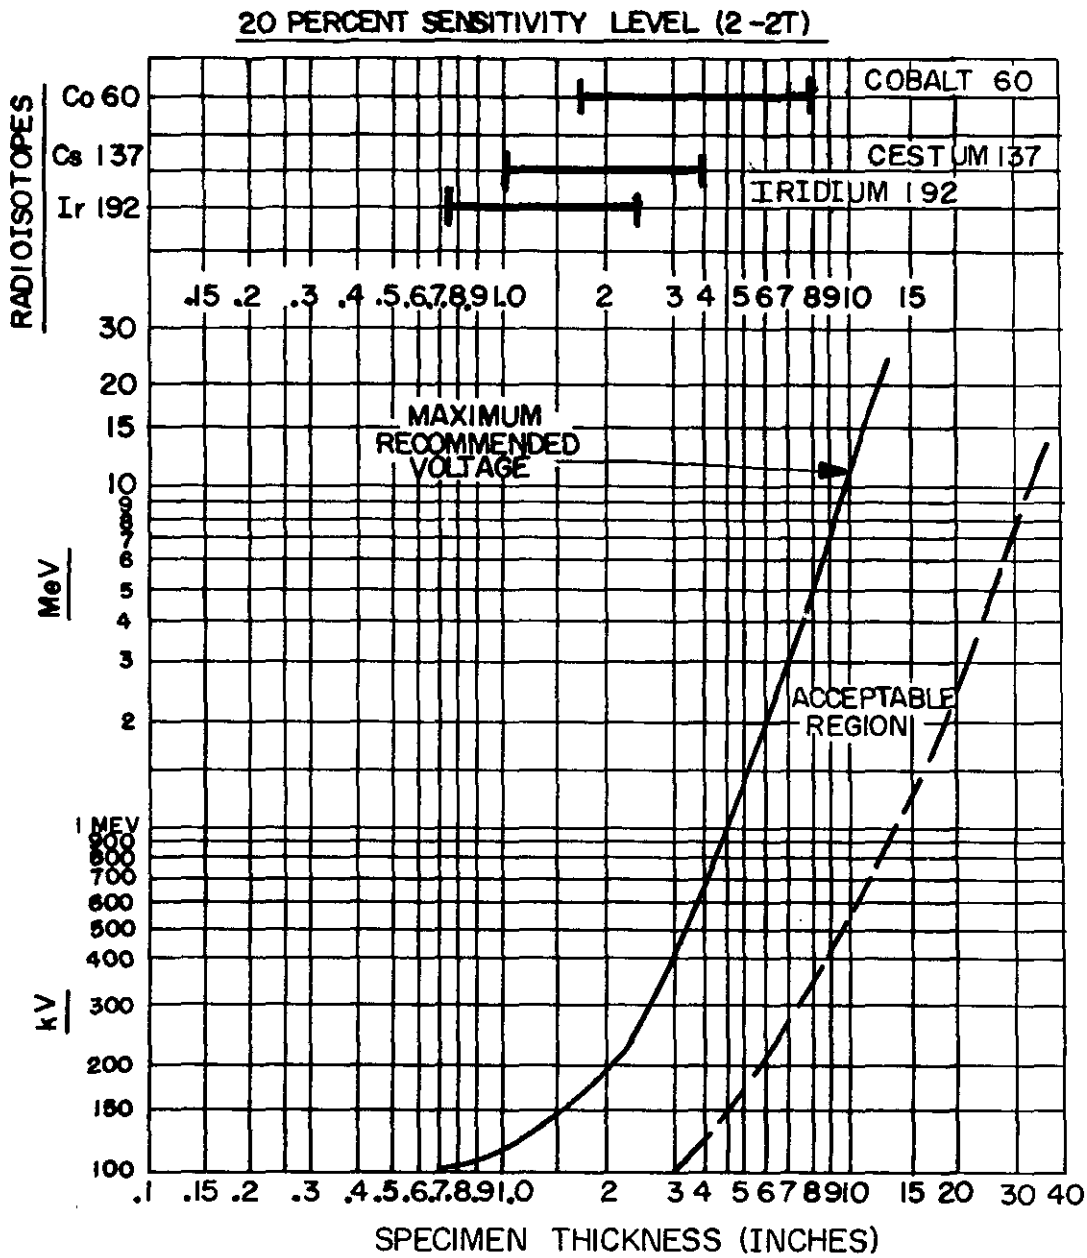

SH 13202658


FIGURE 3. Recommended X-ray voltage settings and radioisotope sources to be used with various aluminum, magnesium and similar alloys.

**A THICKNESS OF PENETRATOR =
0.005 IN. TO AND INCLUDING 0.050 IN.**

MIN PENETRATOR THICKNESS (T) 0.005 IN.
 MIN DIA FOR 1T HOLE 0.010 IN.
 MIN DIA FOR 2T HOLE 0.020 IN.
 MIN DIA FOR 4T HOLE 0.040 IN.

HOLES SHALL BE TRUE AND NORMAL TO
 THE SURFACE OF THE PENETRATOR
DO NOT CHAMFER

PLACE IDENTIFICATION
 NUMBERS HERE

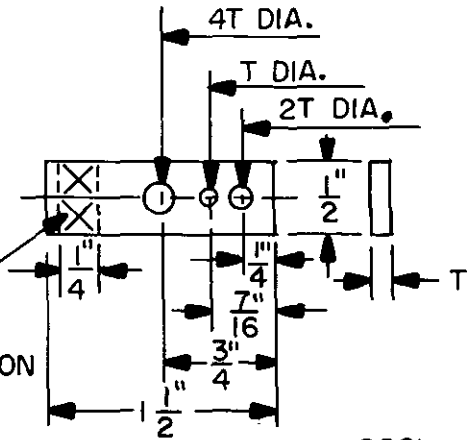


FROM 0.005 IN TO 0.020 IN
 FROM 0.020 IN TO 0.050 IN.

TOLERANCE ON (T) $+0.0001$ IN.
 -0.001 IN.
 TOLERANCE ON (T) ± 0.0025 IN.

**B THICKNESS OF PENETRATOR =
OVER 0.050 IN. TO AND INCLUDING 0.160 IN.**


PLACE IDENTIFICATION
 NUMBERS HERE

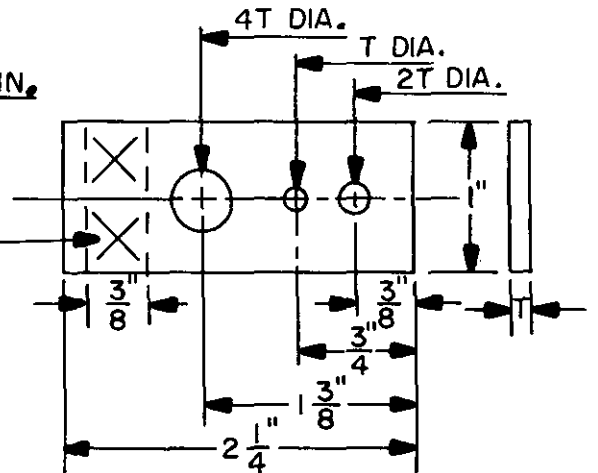

TOLERANCE ON THICKNESS (T) ± 0.005 IN.

**C THICKNESS OF PENETRATOR =
OVER 0.160 IN.**

TOLERANCE ON THICKNESS (T) ± 0.010 IN.


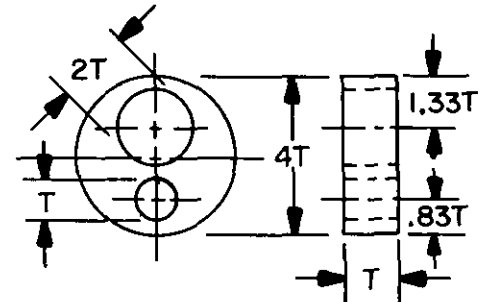


DIMENSIONAL TOLERANCES

LENGTH AND WIDTH OR DIAMETER $\pm 1/64$ IN.
 HOLE DIAMETER ± 10 PERCENT
 HOLE LOCATION $\pm 1/64$ IN.

SH 13202626

FIGURE 4. Penetrator designs.

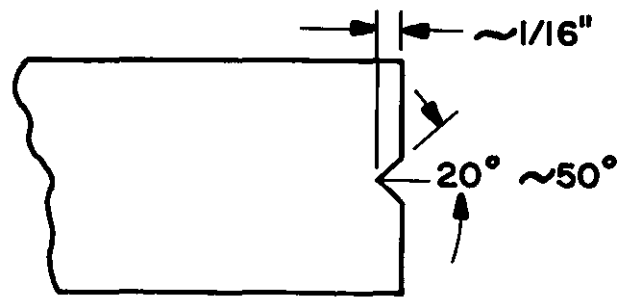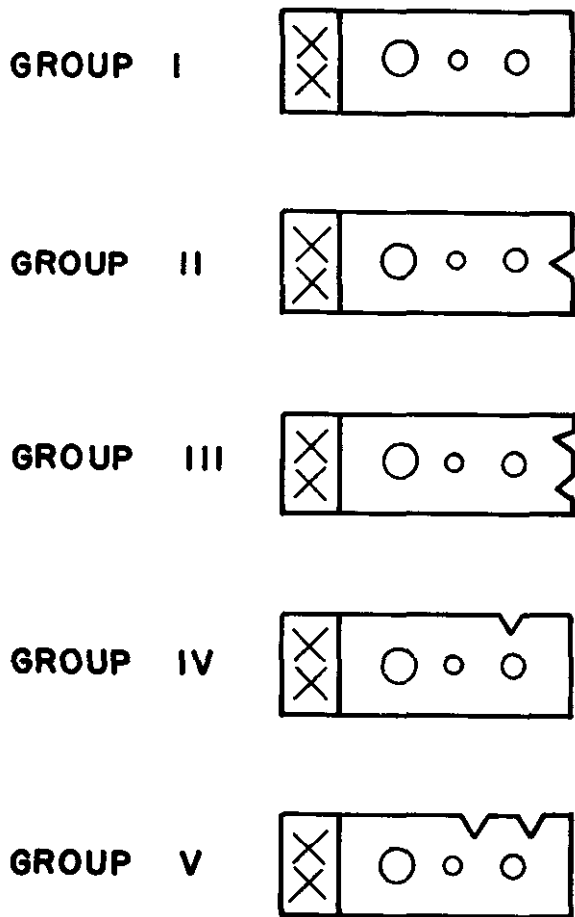


DETAIL OF NOTCHES

SH 13202627

FIGURE 4A. Penetrameter identification notching.

67

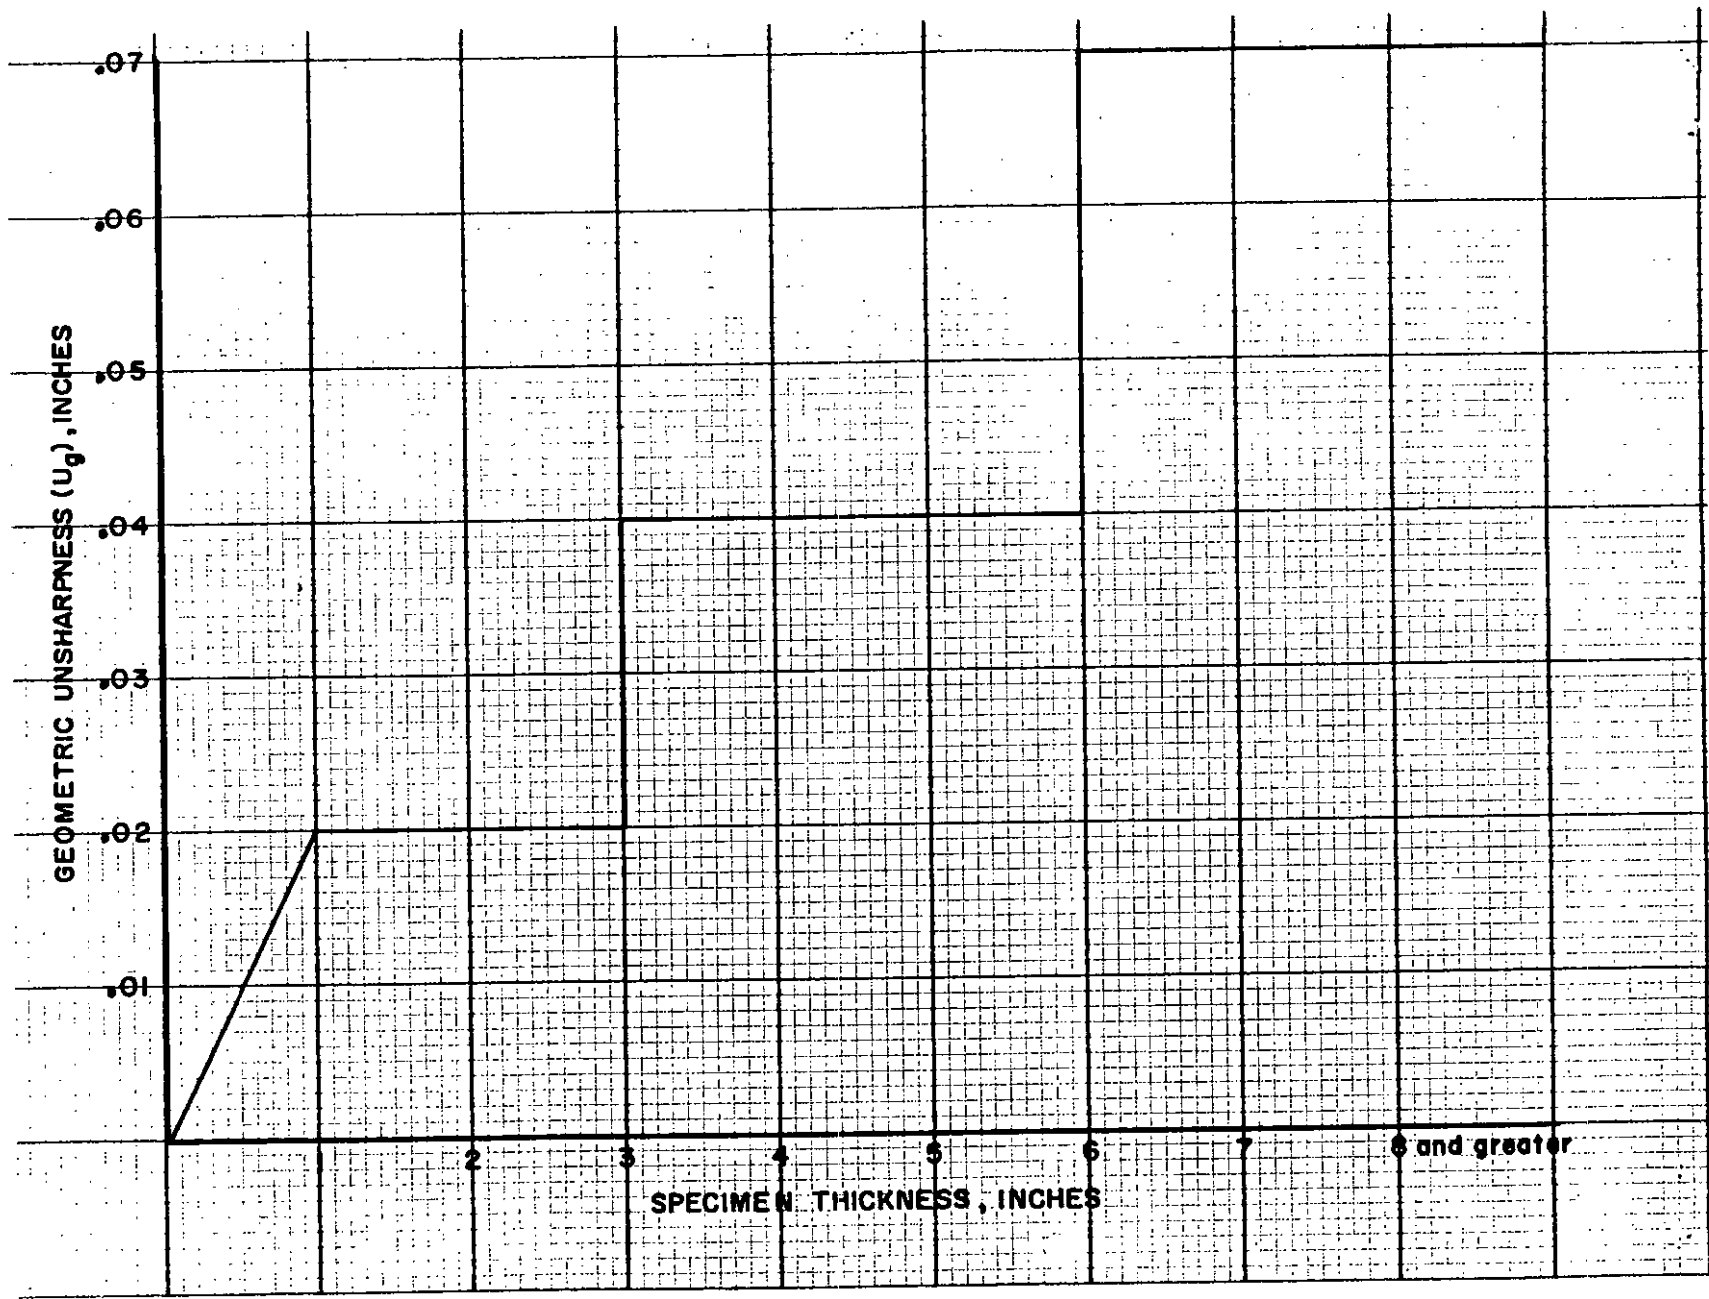


MIL-STD-271F(SH)
27 June 1986

SH 13202628

FIGURE 4B. Maximum allowed U_g .

MIL-STD-271F(SH)
27 June 1986

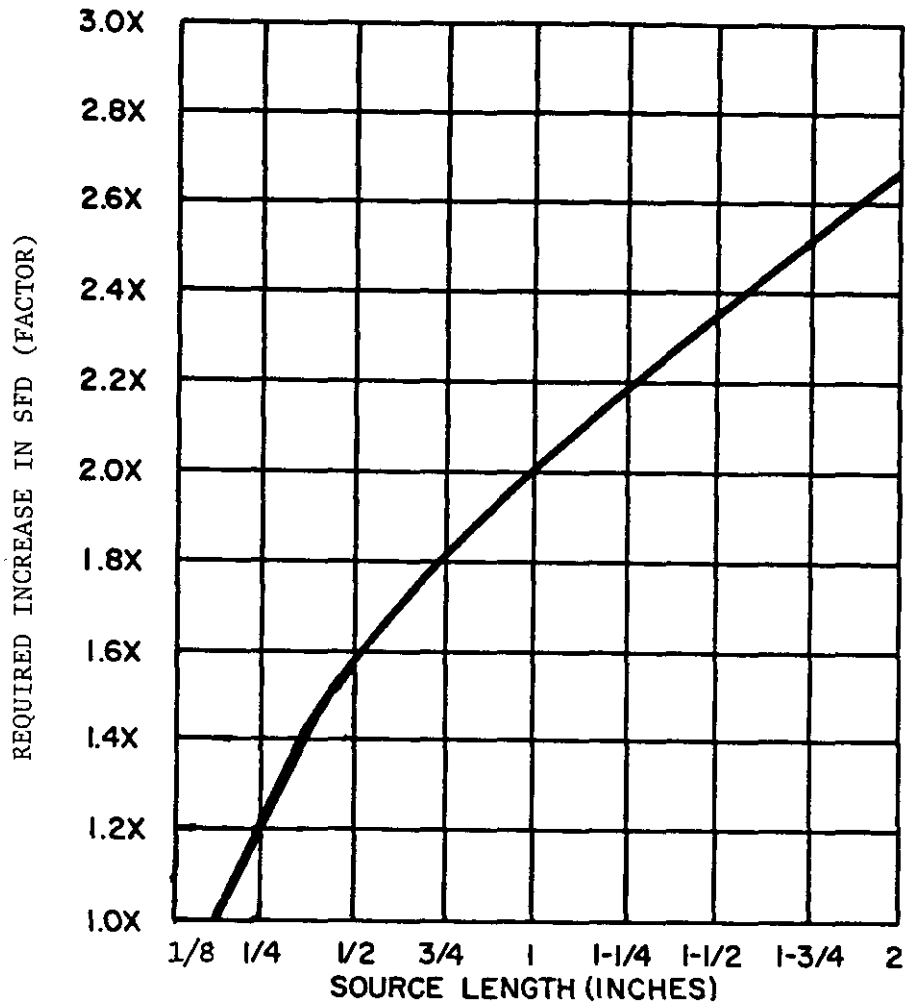


SH 12546

NOTE: To find the SFD to use with a given source, find the minimum SFD from 3.3.6, and multiply this value by the length-factor from the above curve.

FIGURE 4C. Recommended increase in source-to-film distance for various radioisotope sources with lengths greater than 1/8 inch.

MIL-STD-271F(SH)
27 June 1986

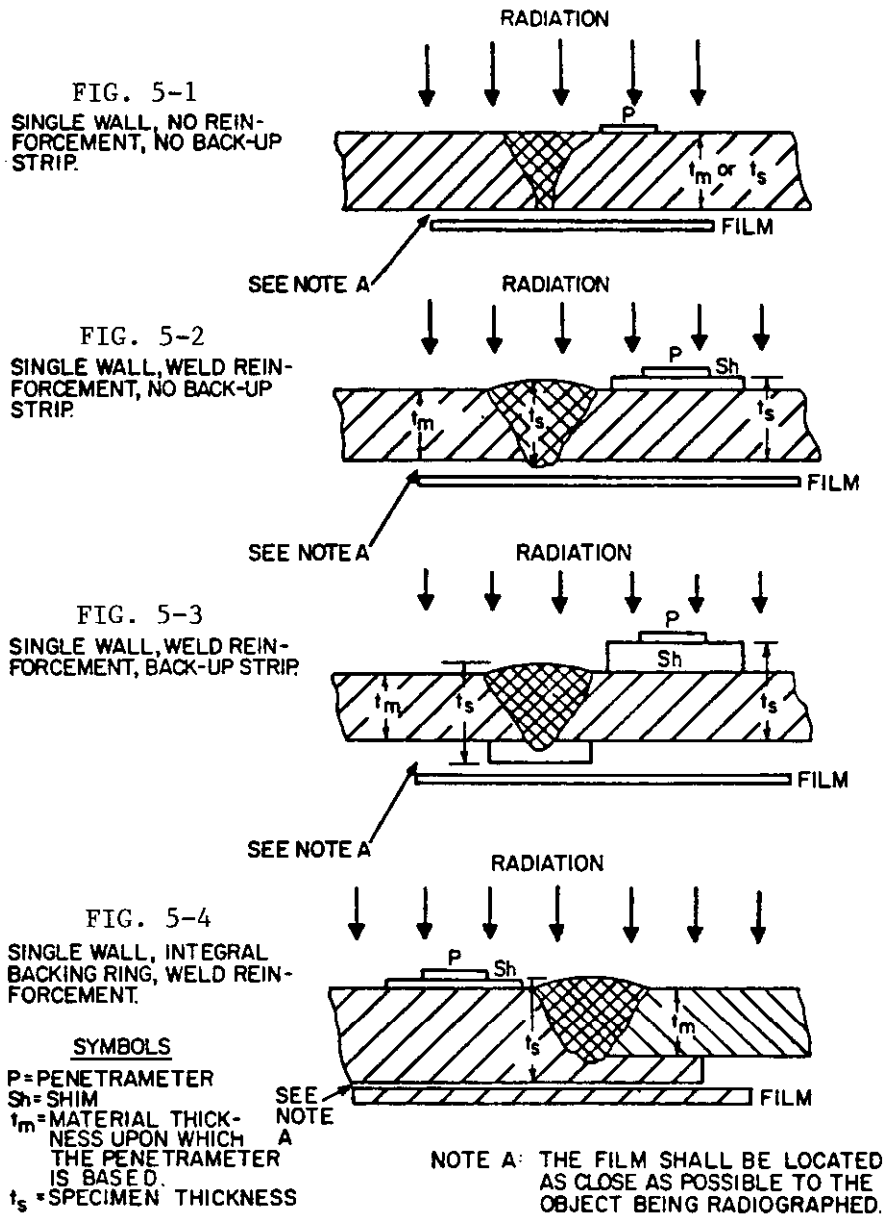


SH 12549

FIGURE 5. Examples of material thickness (T_m) and specimen thickness (T_s).

MIL-STD-271F(SH)
27 June 1986

FIG. 5-5
SINGLE WALL, WELD REINFORCEMENT,
CLADDING REDEPOSITED OVER WELD IN
BASE METAL.

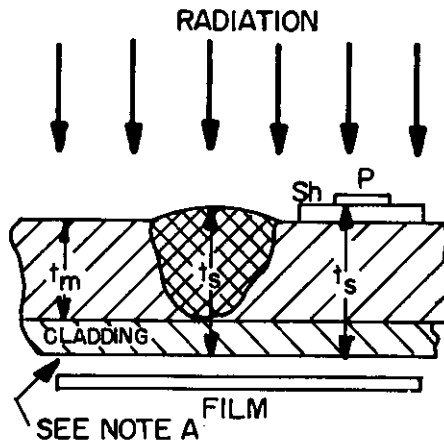

NOTE B.


EVEN THOUGH THE BASE MATERIAL
MAY BE CLADDIED ON BOTH SIDES, THE
THICKNESS ON WHICH THE PENETRA-
METER IS BASED IS STILL THE ORIGINAL
THICKNESS OF THE BASE MATERIAL.

FIG. 5-6

DOUBLE WALL, DOUBLE WALL
VIEWING, WELD REINFORCEMENT
AND BACK-UP STRIP. PENETRAMETER
IS BASED ON THE DOUBLE WALL
THICKNESS. SEE TABLE IV.

* 2% OF $2t_m$ FOR 2-LEVEL, 1% OF
 $2t_m$ FOR 1-LEVEL, AND 4% OF $2t_m$
FOR 4-LEVEL RADIOGRAPHY.

RADIATION

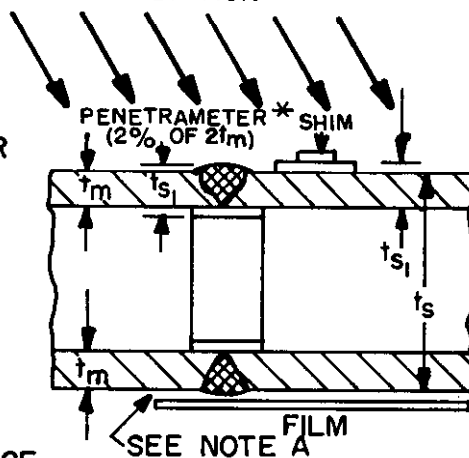

NOTE C.

THE THICKNESS OF THE SHIM FOR
RADIOGRAPHY OF A CONSUMABLE IN-
SERT WELD SHALL BE IN ACCORDANCE
WITH FIG. 5-2.

NOTE A.

THE FILM SHALL BE LOCATED AS CLOSE AS
POSSIBLE TO THE OBJECT BEING RADIOGRAPHED.

SH 12549

FIGURE 5. Examples of material thickness (T_m) and specimen
thickness (T_s). - Continued

MIL-STD-271F(SH)
27 June 1986

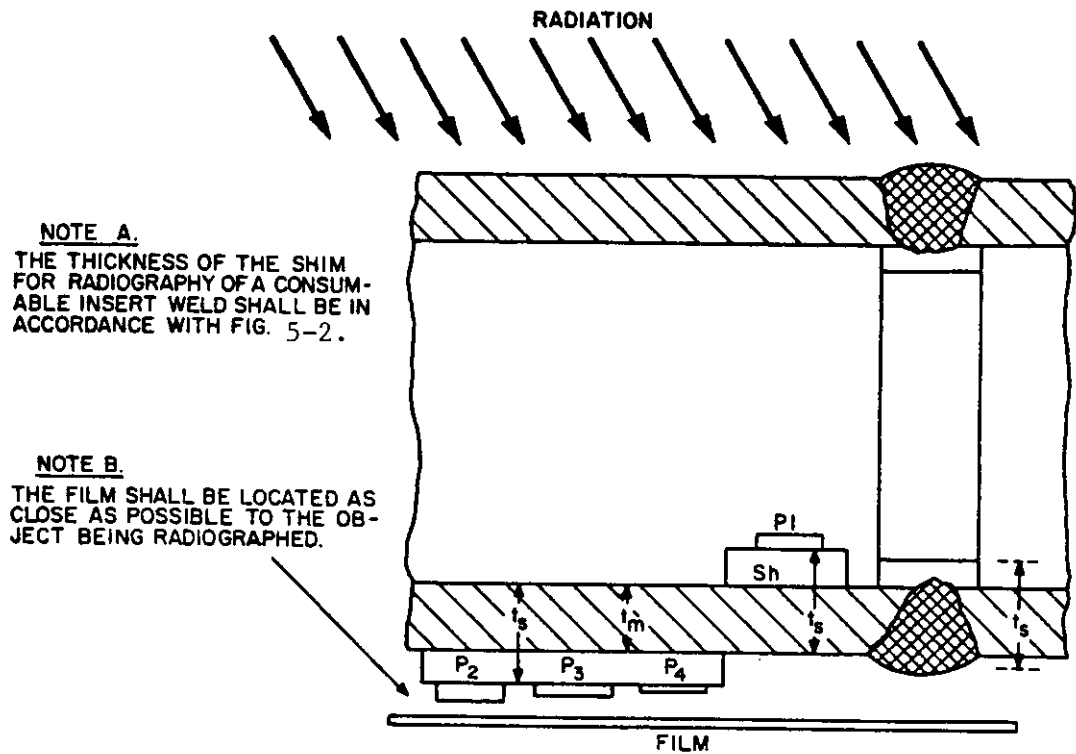


FIGURE 5-7
DOUBLE WALL, SINGLE WALL VIEWING

ONLY THE PORTION OF THE WELD NEXT TO THE FILM IS TO BE VIEWED. PENETRATOR (PI) MAY BE PLACED INSIDE OF PIPE FOR EACH EXPOSURE, OR A TECHNIQUE SHOT, AS SHOWN, MAY ESTABLISH WHICH FILM-SIDE PENETRATOR (P₂, P₃, OR P₄) SHALL BE USED IN SUBSEQUENT EXPOSURES, IF INSIDE OF PIPE IS NOT ACCESSIBLE.

SH 12549

FIGURE 5. Examples of material thickness (T_m) and specimen thickness (T_s). - Continued

MIL-STD-271F(SH)
27 June 1986

NOTE A

THE FILM SHALL BE LOCATED AS CLOSE AS POSSIBLE TO THE OBJECT BEING RADIOGRAPHED

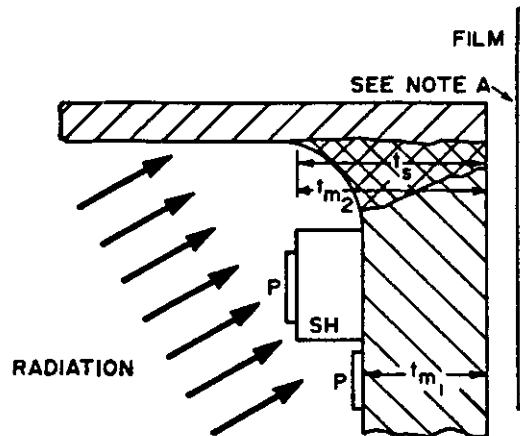


FIGURE 5-8
PENETRATION WELD, SINGLE WALL (SEE NOTE C)

NOTE B

THE FILM MAY BE LOCATED INSIDE THE VESSEL IF A TRIAL EXPOSURE DEMONSTRATES THAT THE REQUIRED QUALITY LEVEL CAN BE OBTAINED

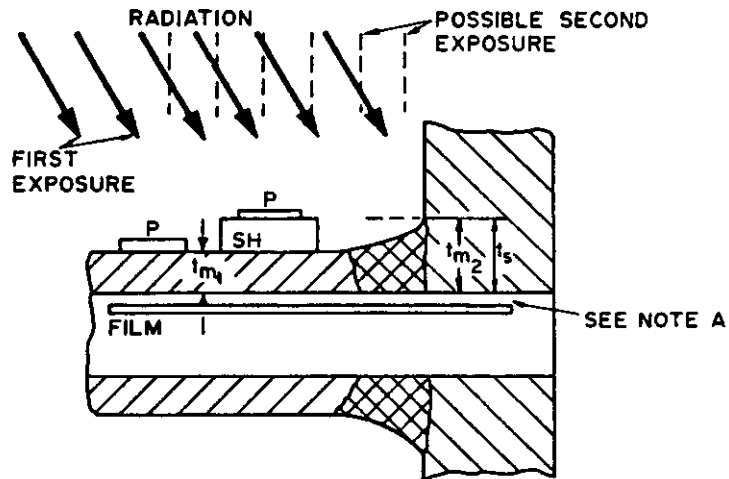


FIGURE 5-9
ROOT CONNECTION WELD, SINGLE WALL (SEE NOTE C)


NOTE C

PENETRATORS, BASED ON WELD THICKNESS (t_{m1} AND t_{m2}) TO QUALIFY VARIOUS THICKNESSES OF WELD. THIRD PENETRATORS, BASED ON AVERAGE THICKNESS OF WELD TO BE USED IF REQUIRED. MULTIPLE EXPOSURE IF NECESSARY TO OBTAIN READABLE DENSITY OVER COMPLETE WIDTH OF WELD.

SH 12549

FIGURE 5. Examples of material thickness (T_m) and specimen thickness (T_s). - Continued


MIL-STD-271F(SH)
27 June 1986

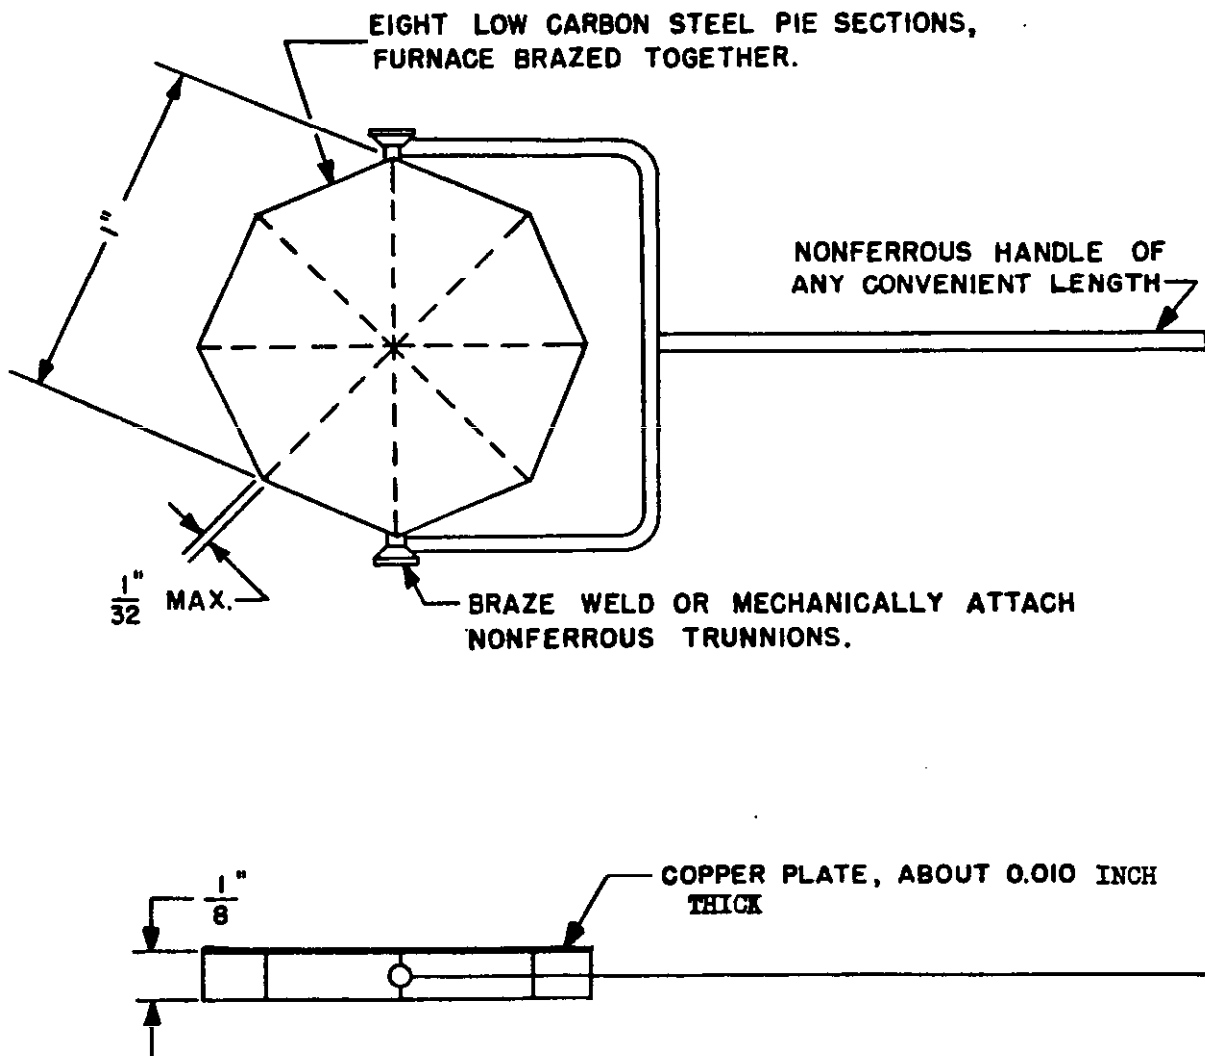

SH 12550

FIGURE 6. Magnetic field indicator.


MIL-STD-271F(SH)
27 June 1986

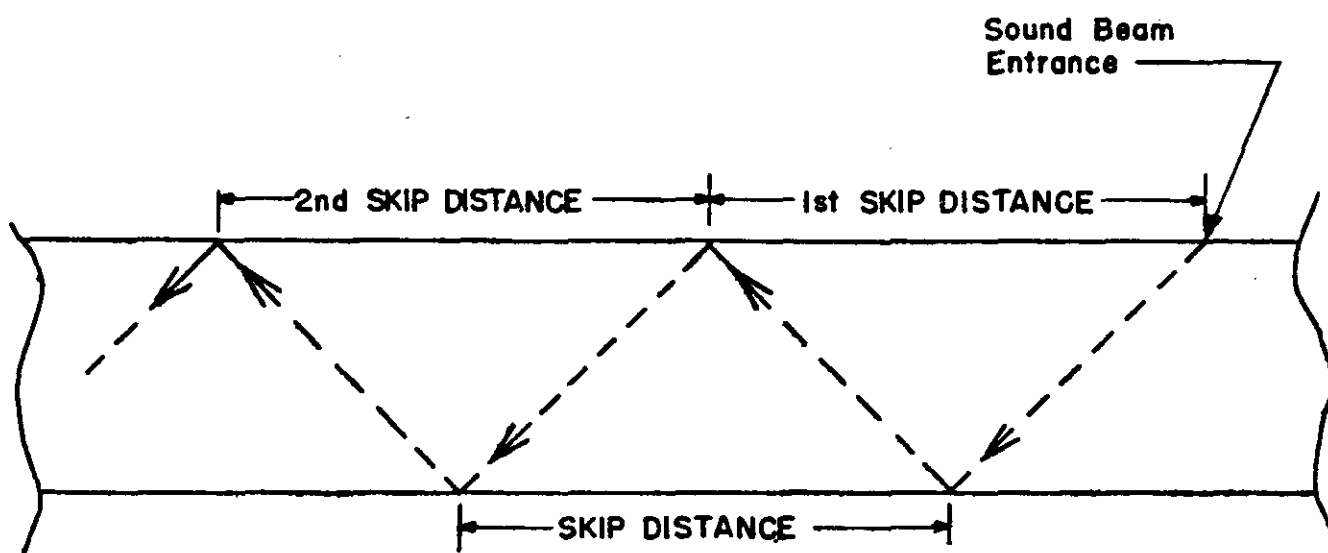

SH 12551

FIGURE 7. Skip distance example.


MIL-STD-271F(SH)
27 June 1986

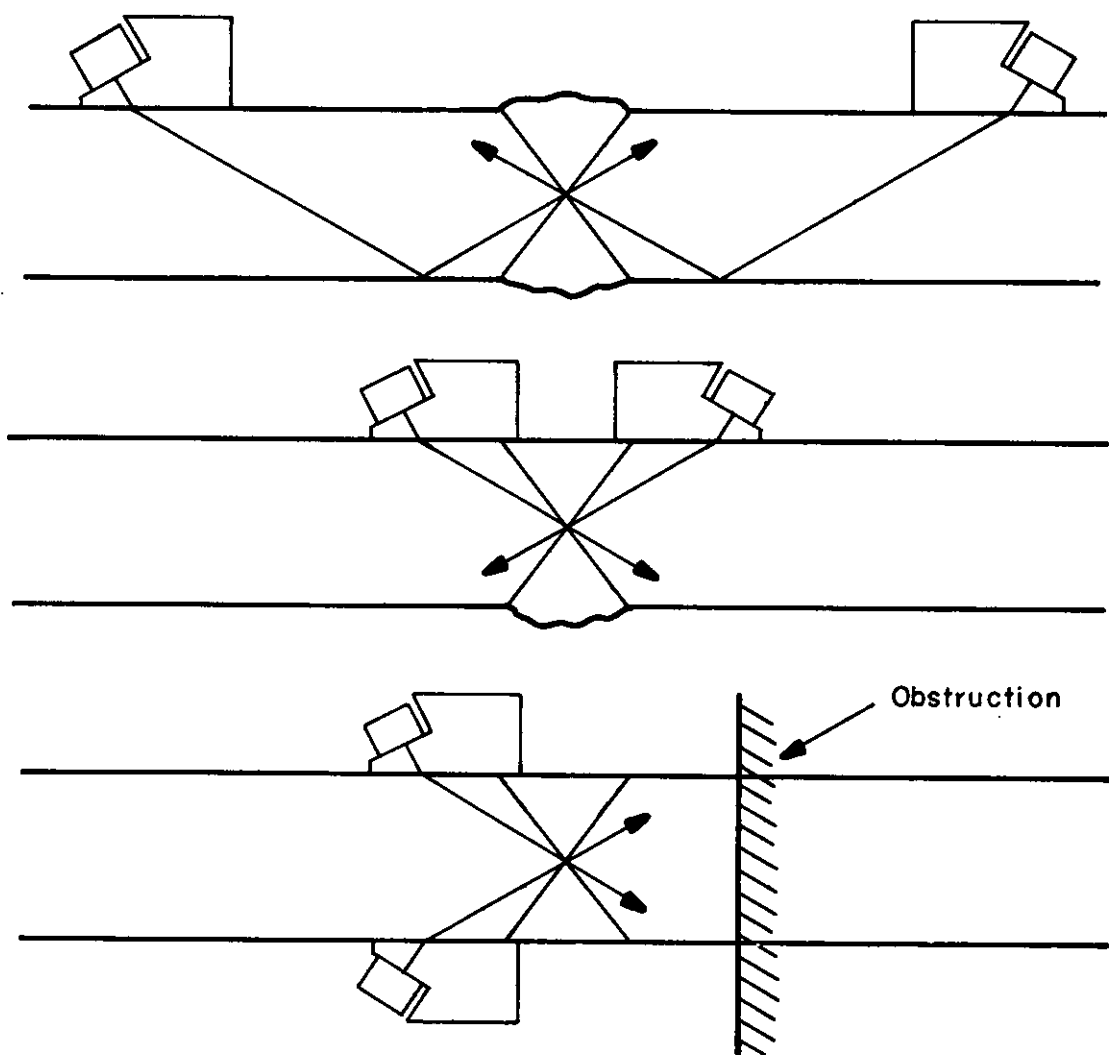

SH 13202629

FIGURE 7A. Accepted scanning techniques for butt welds.

MIL-STD-271F(SH)
27 June 1986

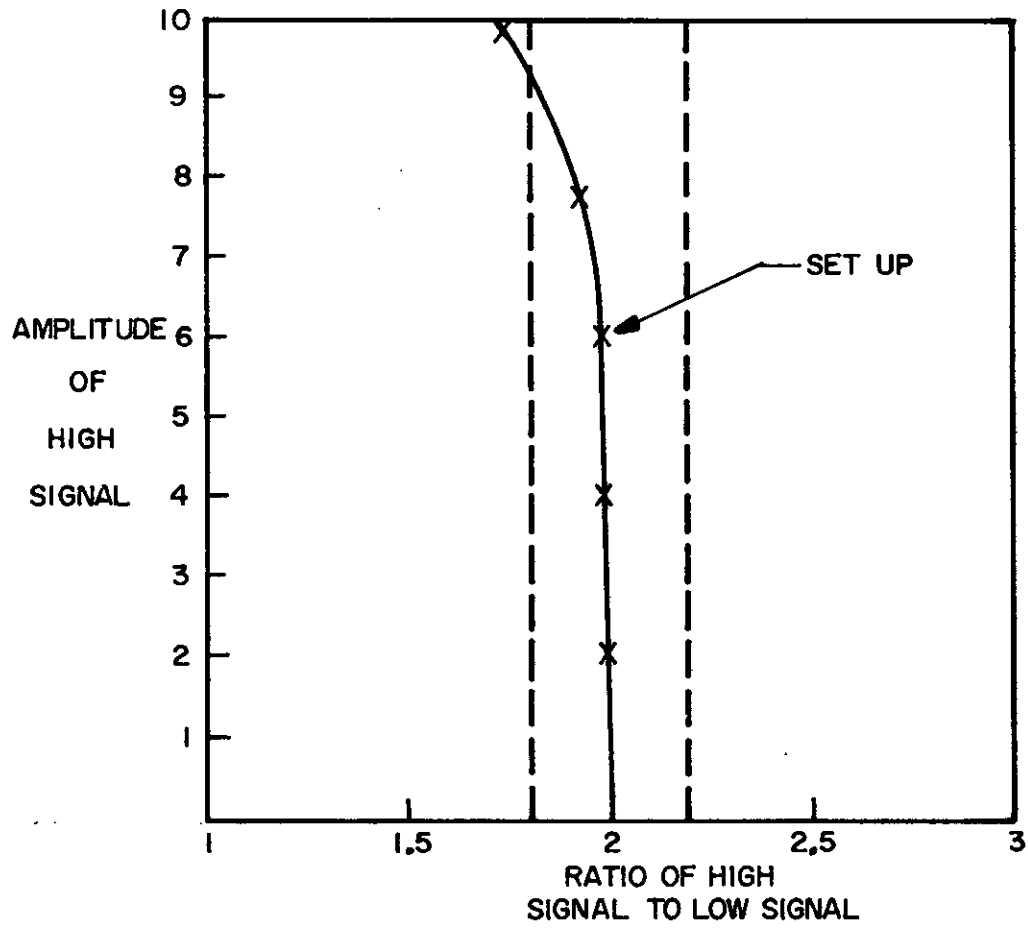


SH 13202630

FIGURE 8. Typical ultrasonic calibration plot for vertical linearity.

MIL-STD-271F(SH)
27 June 1986

SURFACE FINISH TO BE APPROXIMATELY 125_{ra} AS COMPARED TO SURFACE
FINISH STANDARDS 6-3/64 DIA THROUGH HOLES

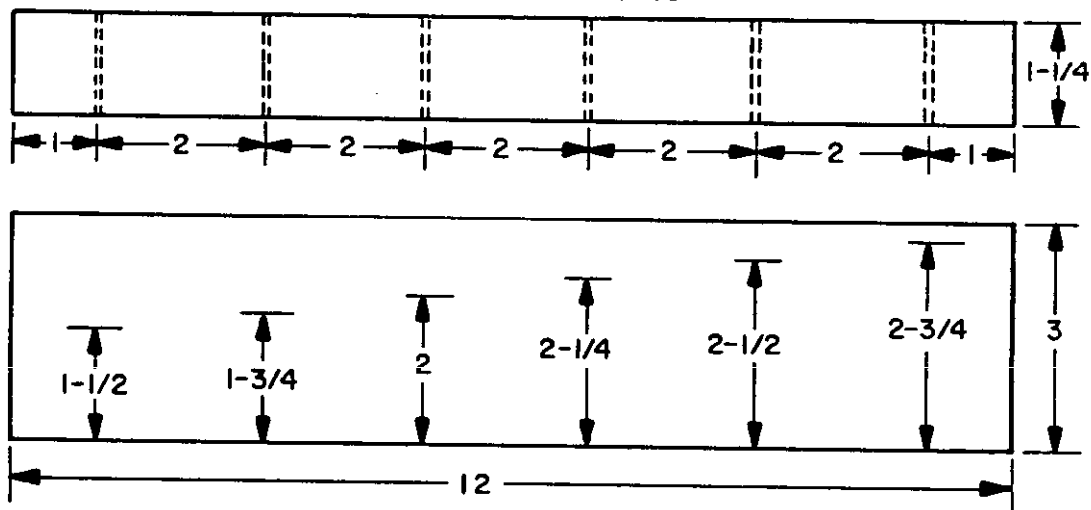


All dimensions in inches.

SH 12553

FIGURE 9. Typical reference calibration standard (sensitivity).


MIL-STD-271F(SH)
27 June 1986

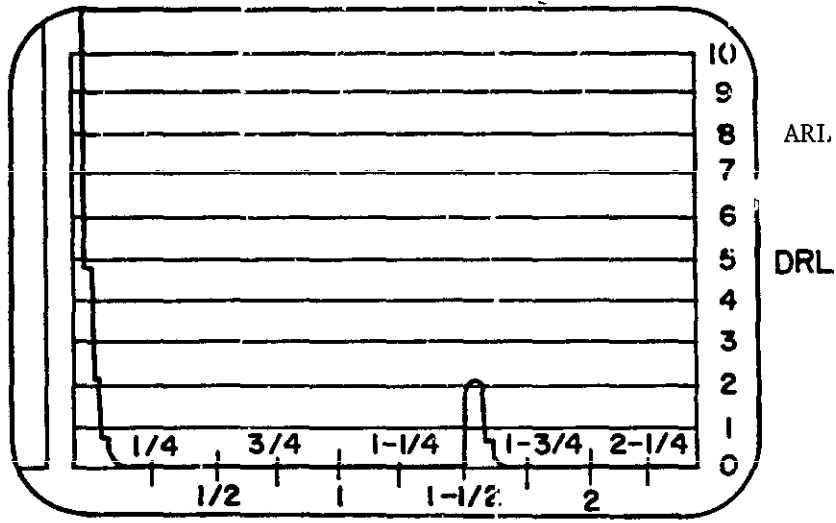

All dimensions in inches.

SH 12554

FIGURE 10. Typical viewing screen calibration (butt welds)
(with dB control).

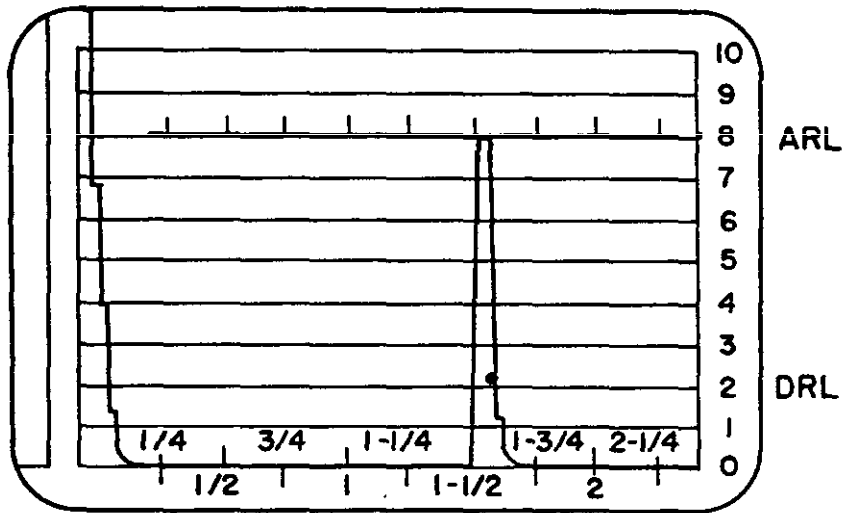


All dimensions in inches.


SH 12555

FIGURE 11. Typical viewing screen calibration (butt welds)
(without dB control).

MIL-STD-271F(SH)
27 June 1986

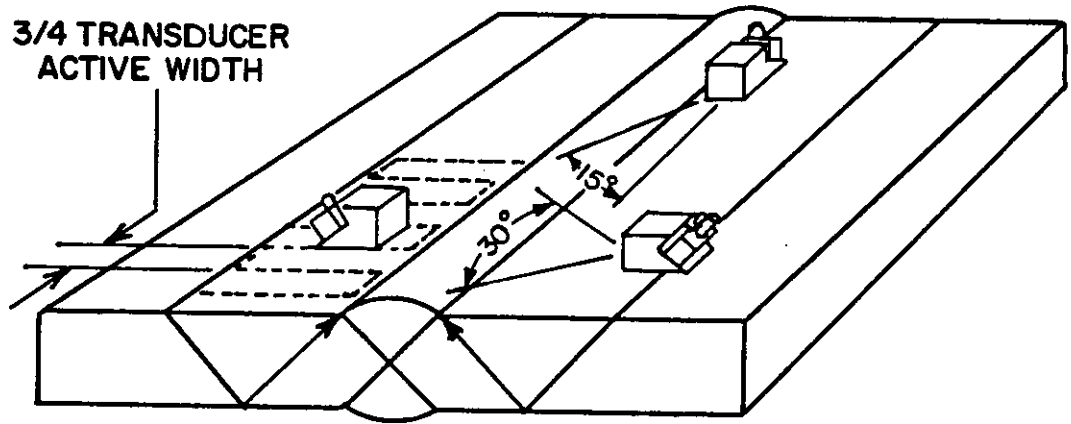

SCANNING PROCEDURES FOR WELDS NOT GROUND FLUSH

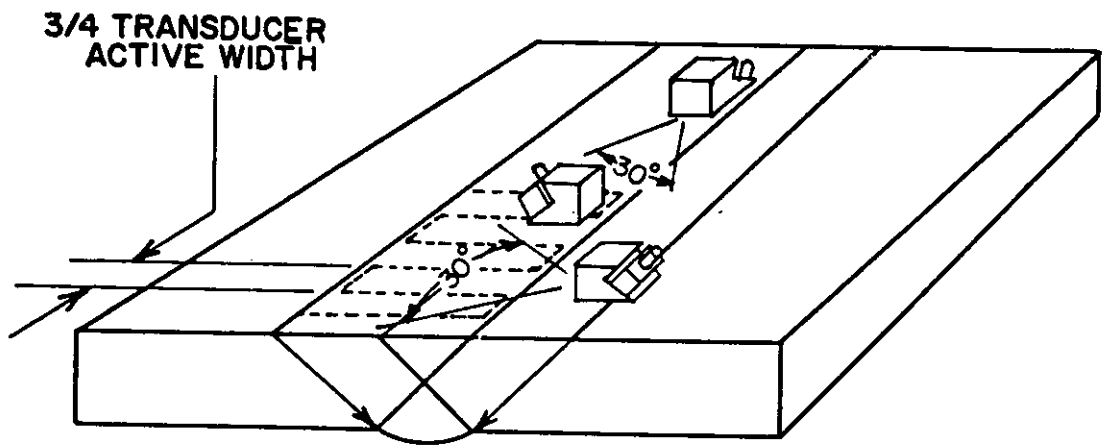


SCANNING PROCEDURES FOR WELDS GROUND FLUSH

SH 12556

FIGURE 12. Scanning procedures for welds.

MIL-STD-271F(SH)
27 June 1986

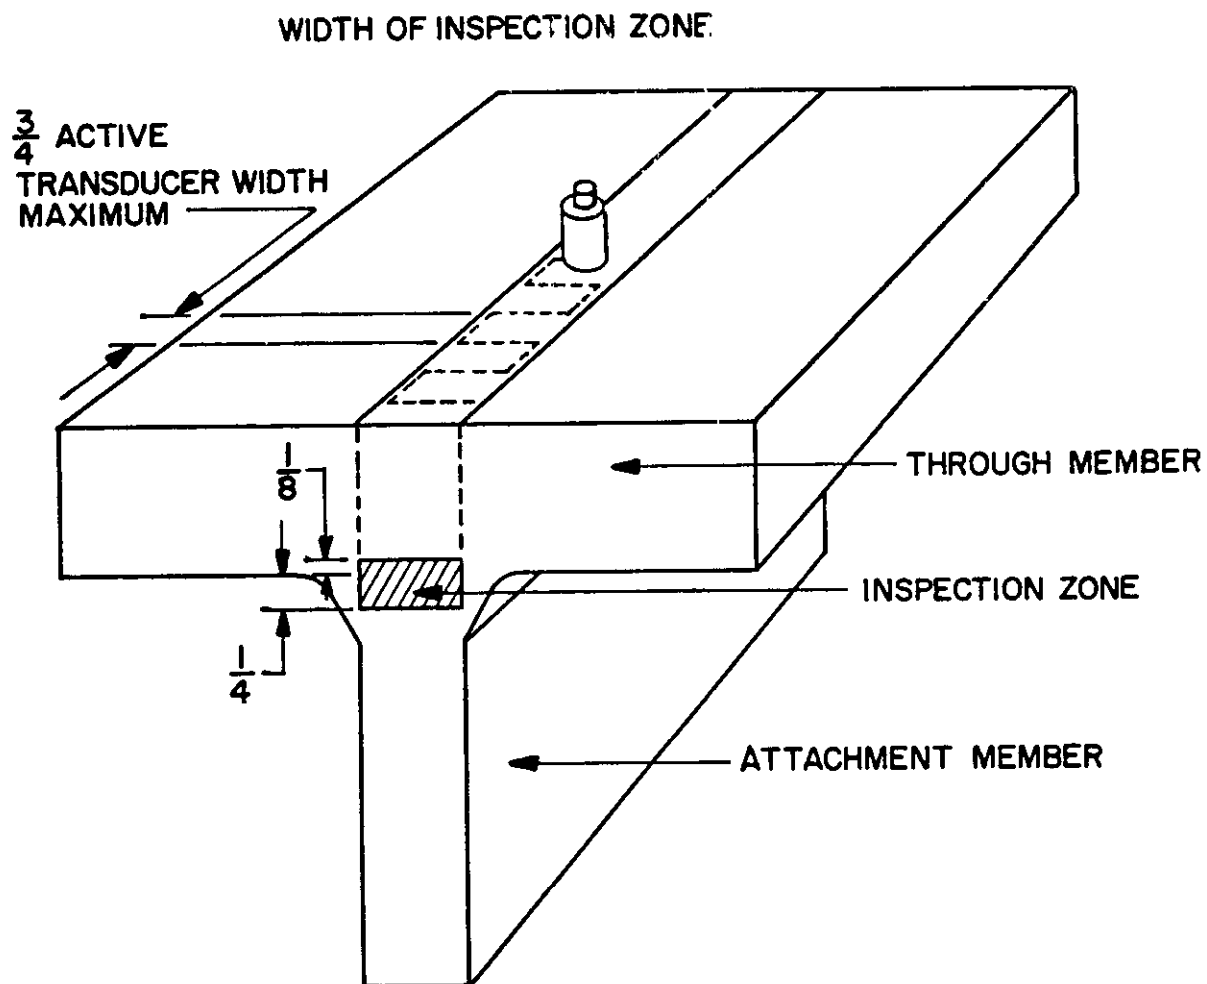


All dimensions in inches.

SH 12557

FIGURE 13. Scanning procedure for tee welds.


MIL-STD-271F(SH)
27 June 1986

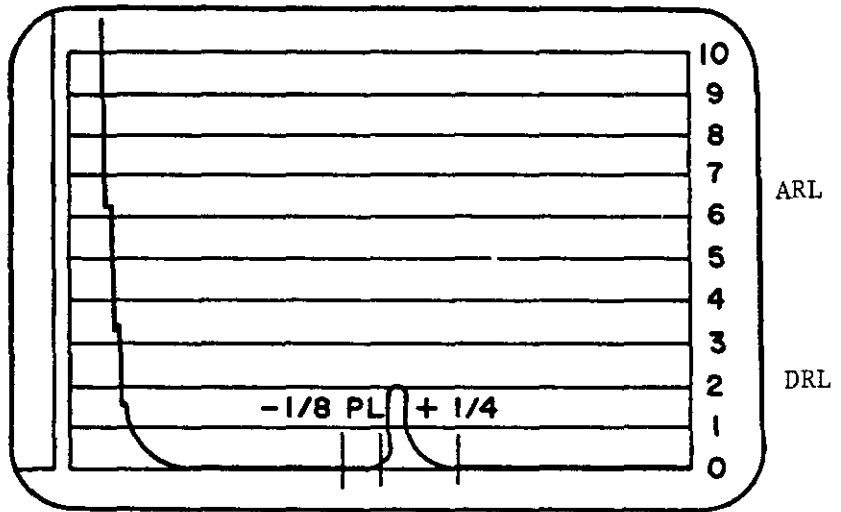

All dimensions in inches.
PL = Plate thickness.

SH 12558

FIGURE 14. Typical viewing screen calibration (tee welds)
(with dB control).

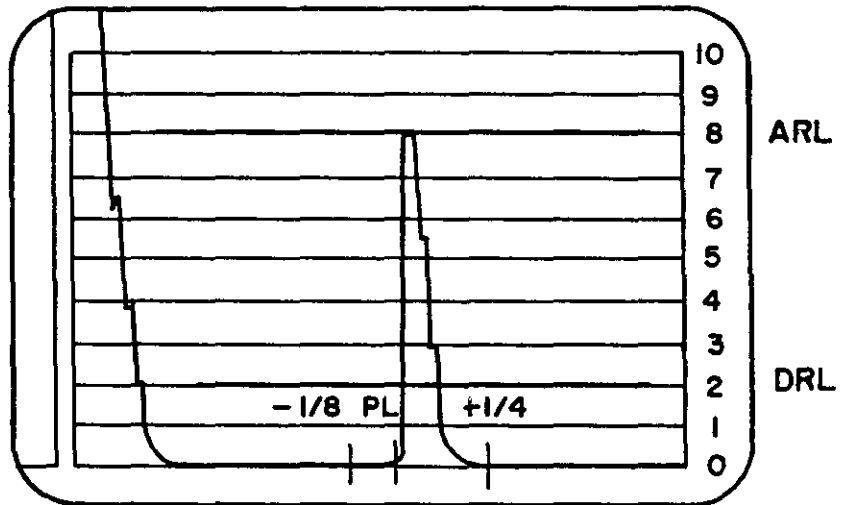


All dimensions in inches.
PL = Plate thickness.

SH 12559


FIGURE 15. Typical viewing screen calibration (tee welds)
(without dB control).

MIL-STD-271F(SH)
27 June 1986

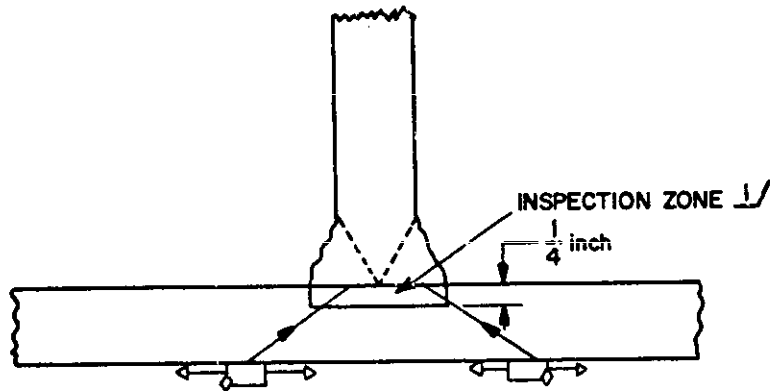

SH 12560

FIGURE 16. Surface opposite attachment member accessible.

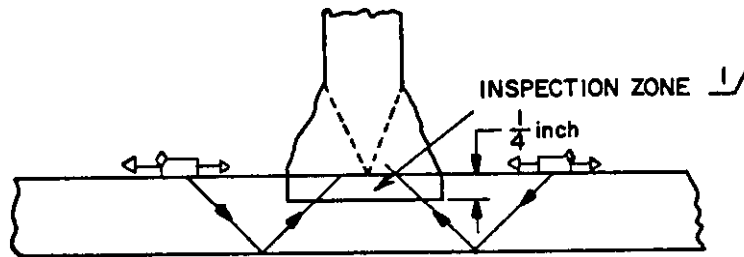

1/ THE INSPECTION ZONE MAY BE EXPANDED AS NECESSARY WITHIN THE PLATE OR WELD. THE SAME SCANNING PROCEDURES MAY BE APPLIED TO PARTIAL PENETRATION TEE WELDS.

SH 12561

FIGURE 17. Surface opposite attachment member not accessible.


MIL-STD-271F(SH)
27 June 1986

SHIP		WELD IDENTIFICATION				DISCONTINUITIES								
FRAME	<input type="checkbox"/> PORT <input type="checkbox"/> STBD		STATION	<input type="checkbox"/> DOT. <input type="checkbox"/> OTHER		NO.	DISTANCE		LENGTH	DEPTH		AMPL.	BEAM DIR.	ACC. or REJ.
							From A	From B		MIN.	MAX.			
<input type="checkbox"/> FULL SKIP <input type="checkbox"/> HALF SKIP		<input type="checkbox"/> COMP <input type="checkbox"/> OTHER		UT IN LIEU OF <input type="checkbox"/> MT <input type="checkbox"/> RT <input type="checkbox"/> OTHER <input type="checkbox"/> N/A										
Inspection Surface														
<input type="checkbox"/> ACCEPTABLE <input type="checkbox"/> UNACCEPTABLE		<input type="checkbox"/> INSIDE <input type="checkbox"/> OUTSIDE <input type="checkbox"/> OTHER												
PLATE MATERIAL		PLATE THICKNESS		WELD WIDTH										
Instrument														
MFR. and MODEL NUMBER				SERIAL NO.										
Transducer														
FREQUENCY	SIZE	SERIAL NO.		ANGLE										
COUPLANT				CALIBRATION STD. NO.										
TEST PROCEDURE				ACCEPTANCE STD.										
INSPECTED BY		RECEIVED BY		DATE	JOB ORDER NO.	WELD LENGTH REQUESTED		WELD LENGTH INSPECTED		<input type="checkbox"/> ACCEPT <input type="checkbox"/> REJECT				
WELD JOINT DETAIL -														
REMARKS														

SH 12562

FIGURE 18. Ultrasonic weld inspection record.

MIL-STD-271F(SH)
27 June 1986

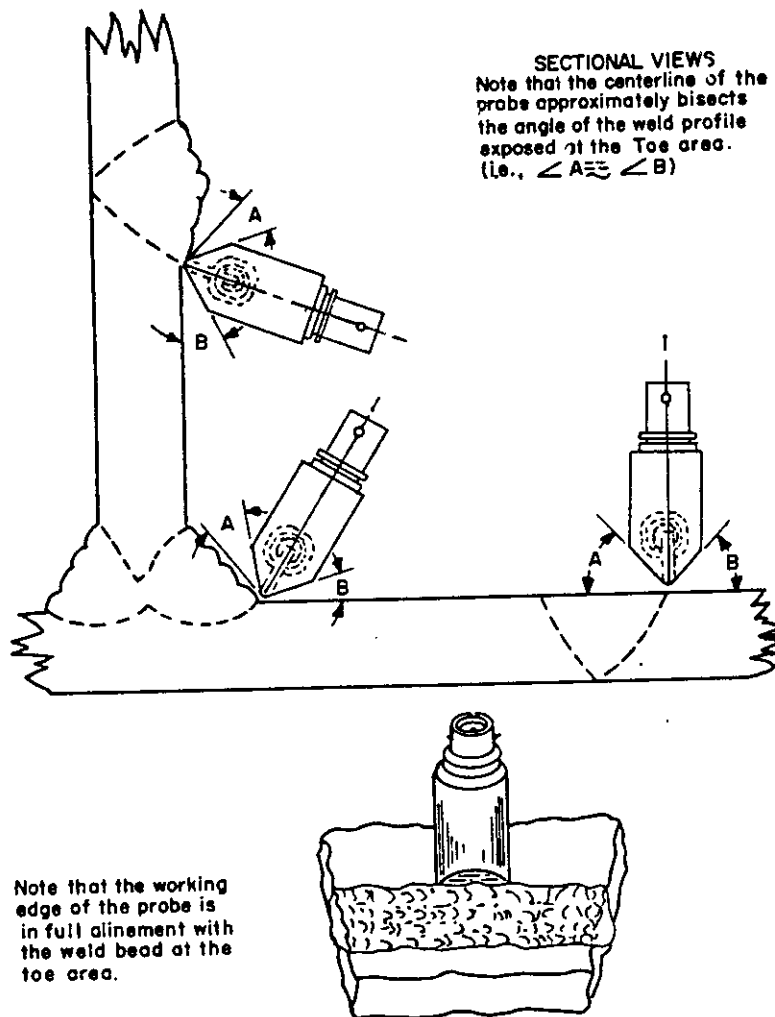

SH 12563

FIGURE 19. Recommended probe-to-weld attitude for eddy current standardization and scanning operations.

STANDARDIZATION DOCUMENT IMPROVEMENT PROPOSAL

(See Instructions - Reverse Side)

1. DOCUMENT NUMBER MIL-STD-271F(SH)		2. DOCUMENT TITLE Requirements for Nondestructive Testing Methods	
3a. NAME OF SUBMITTING ORGANIZATION		4. TYPE OF ORGANIZATION (Mark one)	
b. ADDRESS (Street, City, State, ZIP Code)		<input type="checkbox"/> VENDOR <input type="checkbox"/> USER <input type="checkbox"/> MANUFACTURER <input type="checkbox"/> OTHER (Specify): _____	
5. PROBLEM AREAS			
a. Paragraph Number and Wording:			
b. Recommended Wording:			
c. Reason/Rationale for Recommendation:			
6. REMARKS			
7a. NAME OF SUBMITTER (Last, First, MI) - Optional		b. WORK TELEPHONE NUMBER (Include Area Code) - Optional	
c. MAILING ADDRESS (Street, City, State, ZIP Code) - Optional		8. DATE OF SUBMISSION (YYMMDD)	

DD FORM 1426
82 MAR

PREVIOUS EDITION IS OBSOLETE.

TO DETACH THIS FORM, CUT ALONG THIS LINE.)